

FEM Modelling of the Evolution of Corrosion Cracks in Reinforced Concrete Structures

Thoft-Christensen, Palle

Publication date:
2003

Document Version
Publisher's PDF, also known as Version of record

[Link to publication from Aalborg University](#)

Citation for published version (APA):
Thoft-Christensen, P. (2003). *FEM Modelling of the Evolution of Corrosion Cracks in Reinforced Concrete Structures*. Dept. of Building Technology and Structural Engineering. Structural Reliability Theory Vol. R0302 No. 231

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

Take down policy

If you believe that this document breaches copyright please contact us at vbn@aub.aau.dk providing details, and we will remove access to the work immediately and investigate your claim.

The ***Structural Reliability Theory*** papers are issued for early dissemination of research results from the Structural Reliability Group at the Department of Building Technology and Structural Engineering, Aalborg University. These papers are generally submitted to scientific meetings, conferences or journals and should therefore not be widely distributed. Whenever possible reference should be given to the final publications (proceedings, journals, etc.) and not to the Structural Reliability Theory papers.

FEM Modelling of the Evolution of Corrosion Cracks in Reinforced Concrete Structures

P. Thoft-Christensen

FEM modelling of the evolution of corrosion cracks in reinforced concrete structures

P. Thoft-Christensen

Aalborg University, Aalborg, Denmark

ABSTRACT: Corrosion cracks are caused by the increased volume of corrosion products during the corrosion of the reinforcement. After corrosion initiation the rust products from the corroded reinforcement will initially fill the porous zone near the reinforcement and then result in an expansion of the concrete near the reinforcement. Tensile stresses are then initiated in the concrete. With increasing corrosion, the tensile stresses will at a certain time reach a critical value and cracks will be developed. The increase of the crack width after formation of the initial crack is the subject of this paper. New results based on a Finite Element Analysis (FEM) are presented.

1. INTRODUCTION

Only chloride induced corrosion of the reinforcement is considered. If the rate of chloride penetration into concrete is modelled by Fick's law of diffusion, then it can be shown that the time T_{corr} to initiation of reinforcement corrosion is

$$T_{corr} = \frac{d^2}{4D} \left(\operatorname{erf}^{-1} \left(\frac{C_{cr} - C_0}{C_i - C_0} \right) \right)^{-2} \quad (1)$$

where d is the concrete cover, D is the diffusion coefficient, C_{cr} is the critical chloride concentration at the site of the reinforcement, C_0 is the equilibrium chloride concentration on the concrete surface, C_i is the initial chloride concentration in the concrete, erf is the error function. All the parameters mentioned above are modelled by stochastic variables or stochastic processes; see Thoft-Christensen (2001).

With increasing corrosion the tensile stresses will reach a critical value and cracks will be developed. During this process the volume of the corrosion products at initial cracking of the concrete W_{crit} will occupy three volumes, namely the porous zone W_{porous} , the expansion of the concrete due to rust pressure W_{expan} , and the space of the corroded steel W_{steel} . With this modelling and some minor simplifications it can then be shown that the time from corrosion initiation to crack initiation is; see Liu & Weyers (1998)

$$\Delta t_{crack} = \frac{1}{2 \times 0.383 \times 10^{-3} D_{bar} i_{corr}} \left(\frac{\rho_{steel}}{\rho_{steel} - 0.57 \rho_{rust}} (W_{porous} + W_{expan}) \right)^2 \quad (2)$$

where D_{bar} is the diameter of the reinforcement bar, i_{corr} is the annual mean corrosion rate, ρ_{steel} is the density of the steel, and ρ_{rust} is the density of the rust products. In the derivation of (2) it is assumed that the diameter $D_{bar}(t)$ of the reinforcement bar at the time t is modelled by

$$D_{bar}(t) = D_{bar}(T_{corr}) - c_{corr} i_{corr} (t - T_{corr}) \quad (3)$$

where c_{corr} is a corrosion coefficient.

2. SERVICE-LIFE DEFINITIONS

Several different service-life definitions have been proposed in the literature. Four types of definition are:

- (i) Corrosion initiation based definitions
- (ii) Corrosion crack initiation based definitions
- (iii) Corrosion crack width based definitions
- (iv) Spalling based definitions.

All four definitions are illustrated on figure 1 where a deterioration profile and a crack profile are sketched.

Definition (i) is based on an estimation of the corrosion initiation time T_{corr} and may be written

$$T_{service}^1 = T_{corr} \quad (4)$$

Definition (ii) is based on an estimation of the corrosion crack initiation time T_{crack} and may be written

$$T_{service}^2 = T_{crack} = T_{corr} + \Delta T_{crack} \quad (5)$$

where ΔT_{crack} is the time from corrosion initiation to formation of the first corrosion crack.

Definition (iii) is based on an estimation of the time to formation of a certain corrosion crack width $T_{crack\ width}$ and may be written

$$T_{service}^3 = T_{crack\ width} = T_{corr} + \Delta T_{crack} + \Delta T_{crack\ width} \quad (6)$$

where $\Delta T_{crack\ width}$ is the time from corrosion crack initiation to formation of a given critical corrosion crack width.

Definition (iiii) is based on an estimation of the time to first spalling $T_{spalling}$ and may be written

$$T_{service}^4 = T_{spalling} = T_{corr} + \Delta T_{crack} + \Delta T_{spalling} \quad (7)$$

where $\Delta T_{spalling}$ is the time from corrosion crack initiation to first spalling.

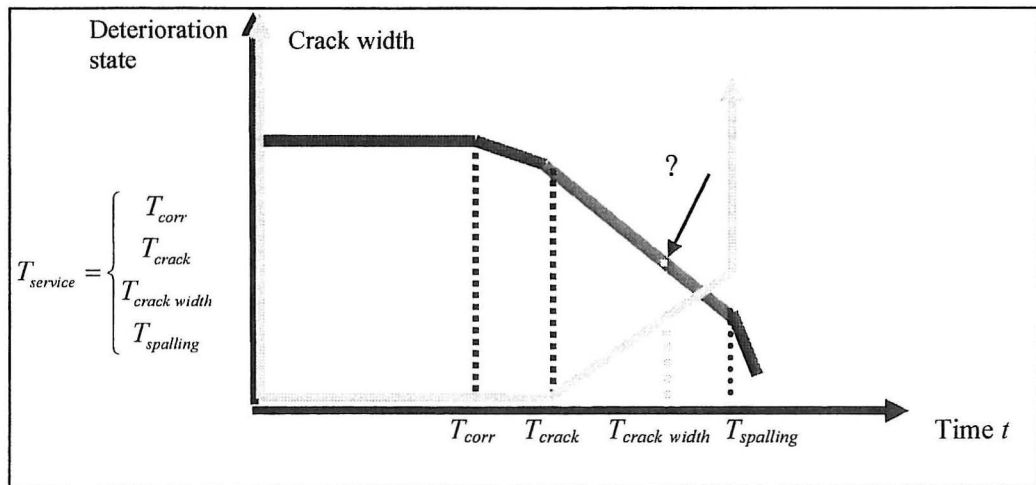


Figure 1. Service-life definitions. ? indicates the area of major interest in this paper.

3. CORROSION CRACK EVOLUTION

After formation of the initial crack the rebar cross-section is further reduced due to the continued corrosion, and the crack width w_{crack} is increased. Several researchers have investigated the evolution of corrosion cracks in reinforced concrete beams experimentally. In most experiments, see e.g. Andrade, Alonso & Molina (1993), the function between the reduction of the rebar diameter ΔD_{bar} and the increase of crack width Δw_{crack} measured at the surface of the concrete specimen can be approximated by a linear function.

$$\Delta w_{crack} = \gamma \Delta D_{bar} \quad (8)$$

where γ is the crack width coefficient.

Andrade, Alonso & Molina (1993) have investigated experimentally the evolution of corrosion cracks in reinforced concrete beams. In the paper four simple test specimens have been investigated. In all four experiments the function between the reduction of the rebar diameter and the maximum crack width measured in the surface of the concrete specimen can be approximated by a linear function, see figure 2. The crack width coefficient γ depends on the cross-sectional data and is of the order 1.5 to 5.

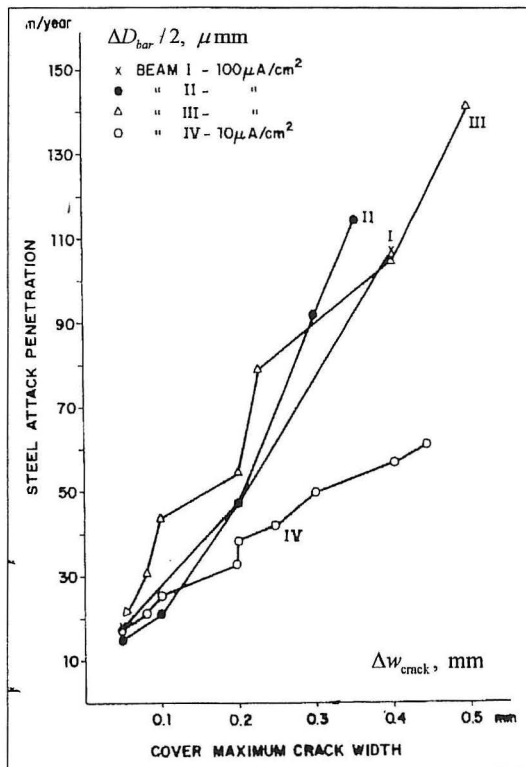


Figure 2. Loss in rebar diameter ΔD_{bar} versus the crack width Δw_{crack} . Andrade, Alonso & Molina (1993).

4. FEM ESTIMATION OF THE CRACK WIDTH COEFFICIENT γ

4.1 FEM estimation in Thoft-Christensen (2003)

For illustration purposes the coefficient γ in equation (4) was estimated using FEM analysis by Thoft-Christensen (2003) using FEMLAB/MATLAB. A rectangular beam cross-section with

only one reinforcement bar was considered, see figure 2. The diameter of the hole around the rebar at the time of crack initiation is $D_{hole} = 20$ mm and that the cover is $c = 10$ mm. The initial crack width is 0.01 mm.

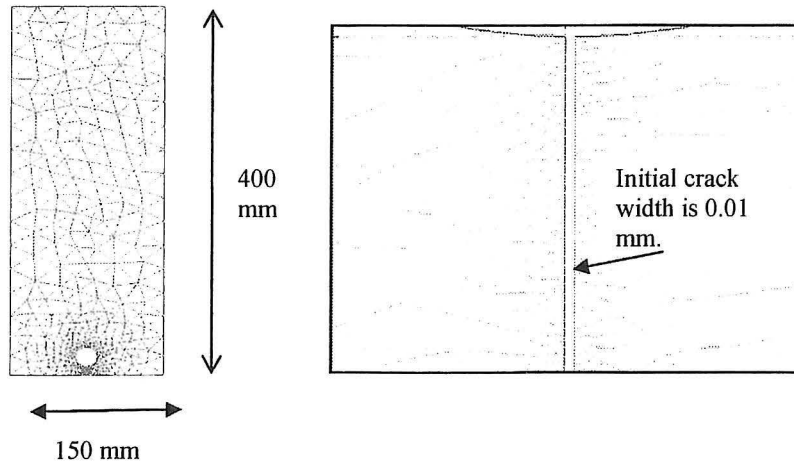


Figure 3. FEM net. The total net to the left and the local net near the crack to the right.

In the FEM modelling the rectangular cross-section is assumed to have a hole at the location of the reinforcement and a crack (0.01 mm) from the hole to the boundary. The number of constant strain elements is 5580 and there are 3066 nodes. The material is assumed to be linear elastic with the elasticity module $E = 25 \times 10^9$ Pa and the pressure from the increasing corrosion products is modelled as a uniform loading (pressure) $p = 1 \times 10^8$ N/m at the boundary of the hole. The result of the analysis is shown in figure 3. The increase in the crack width in the considered time interval Δt is $\Delta w_{crack} = 0.67$ mm and the average increase in the hole diameter is $\Delta D_{hole} = 0.31$ mm.

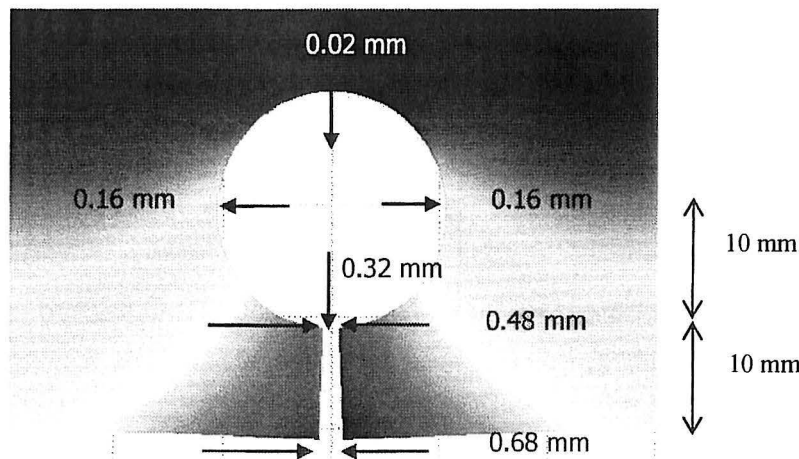


Figure 4. Displacements at four points of the circular hole and at the ends of the crack. Magnification factor is 3.

The produced volume (area) of the corrosion products W_{rust} is related to the corroded steel volume (area) W_{steel} by $W_{rust} = \alpha W_{steel}$, where $\alpha = \rho_{rust} / \rho_{steel}$ (the relation between the densities of the rust product and the steel) depends on the type of corrosion products. Typical values are 2 - 4. Therefore,

$$\begin{aligned}
(\alpha - 1)\pi\Delta D &= \pi\Delta D_{hole} + \varepsilon \Rightarrow (\alpha - 1)\pi\gamma^{-1}\Delta w = \pi\eta^{-1}\Delta w + \varepsilon \\
\text{so } \gamma &< (\alpha - 1)\eta \\
\text{and } \gamma &\approx (\alpha - 1)\eta \text{ for small } \varepsilon
\end{aligned}
\tag{9}$$

where ε is the amount of rust in the increased crack.

For the example shown in figure 3 one gets

$$\begin{aligned}
0.67 &= \eta \times 0.31 \Rightarrow \eta = 2.2 \\
\gamma &< (\alpha - 1) \times 2.2 = \begin{cases} 1.1 \times 2.2 = 2.4 \text{ for black rust } \text{Fe}_3\text{O}_4 \\ 3.1 \times 2.2 = 6.8 \text{ for brown rust } \text{Fe}(\text{OH})_3 \end{cases}
\end{aligned}
\tag{10}$$

These γ -values are of the same magnitude as the experimental values presented in section 2.

4.2 Rectangular beam with one symmetrical rebar

In this section the results of FEM analysis of the cross-section illustrated in figure 5 are presented with 10 different combinations of the cover c and the diameter D of the hole.

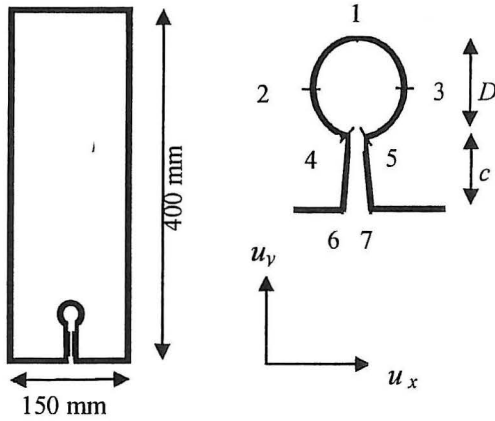


Figure 5. Cross-section geometry and numbering of points where displacements are estimated.

The 10 designs A-J are defined and the displacements of the points 1-7 for each design are shown in table 1. The estimates of the coefficients η and γ are shown in table 2.

Table 1. Estimated displacement of points 1-7 in designs A-J.

Design	D	c	1		2 and 3		4 and 5		6 and 7	
			u_x	u_y	u_x	u_y	u_x	u_y	u_x	u_y
A	10	10	0	0.00	-0.06	-0.40	-0.07	-0.10	-0.10	-0.09
B	15	10	0	-0.01	-0.11	-0.70	-0.14	-0.19	-0.20	-0.18
C	20	10	0	-0.03	-0.16	-0.11	-0.23	-0.32	-0.34	-0.31
D	25	10	0	-0.04	-0.24	-0.15	-0.35	-0.50	-0.52	-0.49
E	15	15	0	-0.01	-0.10	-0.06	-0.13	-0.16	-0.19	-0.14
F	20	15	0	-0.24	-0.16	-0.10	-0.22	-0.26	-0.32	-0.24
G	25	15	0	-0.04	-0.22	-0.15	-0.32	-0.41	-0.48	-0.40
H	20	20	0	-0.02	-0.17	-0.10	-0.22	-0.24	-0.33	-0.22
I	25	20	0	-0.04	-0.24	-0.15	-0.34	-0.37	-0.52	-0.35
J	25	25	0	-0.04	-0.25	-0.15	-0.34	-0.35	-0.53	-0.33

Table 2. Estimated values for η and γ in the case of black rust.

	A	B	C	D	E	F	G	H	I	J
η	1.73	1.95	2.16	2.19	2.18	2.25	2.38	2.32	2.58	2.63
γ_{black}	1.90	2.15	2.38	2.41	2.40	2.48	2.62	2.55	2.84	2.89

In figure 5 is to the left shown values of γ (black rust) for fixed diameter d as a function of the cover c . γ increases with the cover c . To the right is shown values of γ (black rust) for fixed cover c as a function of the diameter d . γ increases with the diameter d .

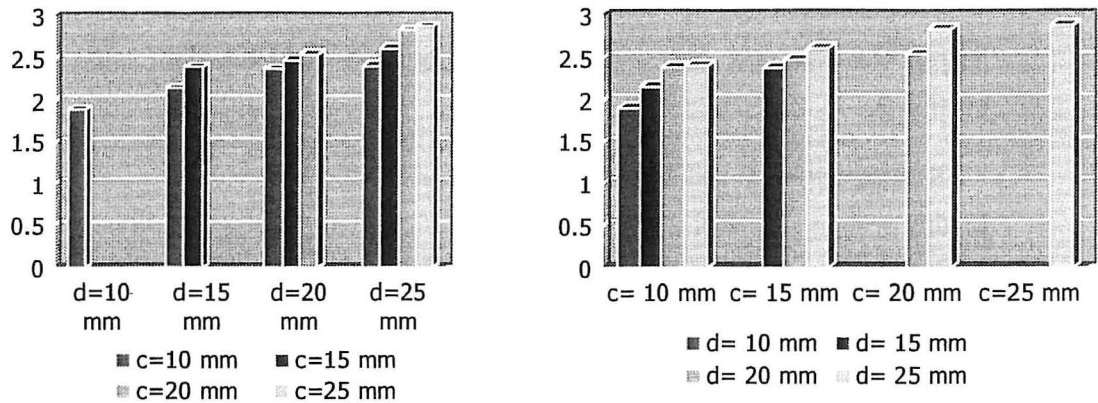


Figure 6. γ for black rust.

5. SPALLING

In this section it is shown on the basis of a number of examples how FEM analysis may help in estimating how and where new corrosion cracks are established with continuing corrosion after the initial (first) crack is formed.

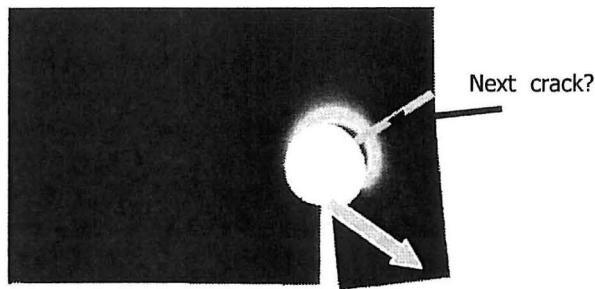


Figure 7. Beam with non-symmetrical rebar.

In figure 7 a beam with a single non-symmetrical rebar and an initial crack from the rebar to the lower side of the beam is considered. The FEM method is used similarly to the examples shown earlier. The maximum tensile stress at the boundary of the hole occurs in the NE direction indicating that the next crack may occur in that direction. In figure 8 the same beam is shown, but now with two symmetrical rebars. New corrosion cracks seem to occur in the same direction as shown in figure 7 resulting in spalling at the two corners, see the picture in the middle where the first principal stresses are shown. The picture to the right shows the stresses in the y -direction (vertical direction). They seem to show that the next spalling will be a vertical displacement of the middle section.


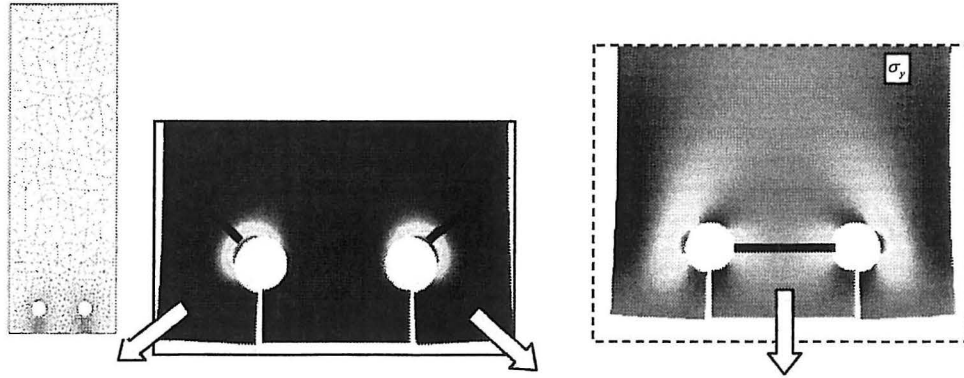


Figure 8. Beam with two symmetrical rebars.

In figure 9 is shown a similar case as in figure 8 is shown ,but now with three rebars. Again, the analysis seems to indicate that the spalling will first occur at the two corners and then at the two middle sections.

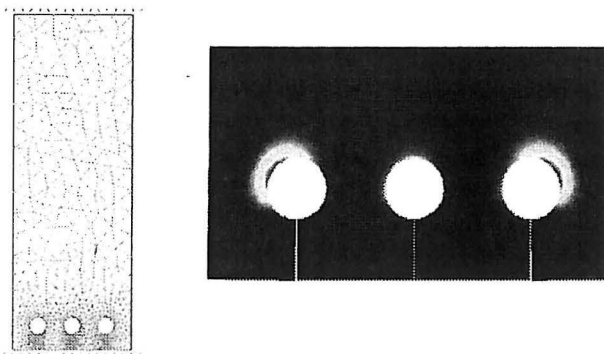

In the last example a reinforced concrete bridge deck with six rebars is considered, see figure 9. The analysis seems to indicate again that the spalling will first occur at the two corners and then at the five middle sections.

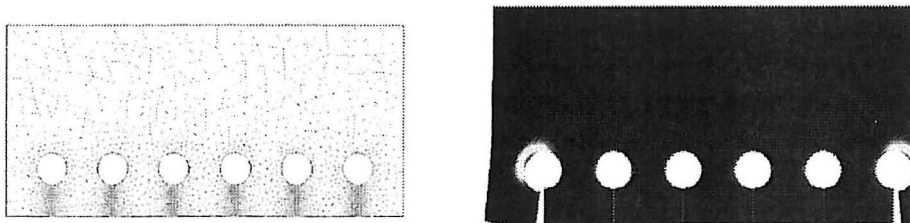


Figure 10. Reinforced concrete bridge deck with six rebars.

6. CONCLUSIONS

Modelling of corrosion crack initiation and corrosion crack evolution is presented with special emphasis on modelling of the crack evolution. Experiments and FEM analysis seem to show that the function between the reduction of the rebar diameter ΔD_{bar} and the corresponding increase in crack width Δw_{crack} in a given time interval Δt measured on the surface of the

concrete specimen can be approximated by a linear function, and it is demonstrated how the crack width coefficient γ can be estimated using FEM analysis.

ACKNOWLEDGEMENT. The author is grateful to Professor Staffan Svensson, Aalborg University for assistance with the FEM analyses.

REFERENCES

- Andrade C., Alonso, C. & Molina, F.J. (1993). *Cover Cracking as a Function of Bar Corrosion: Part 1-Experimental Test*. Materials and Structures, Vol. 26, pp. 453-464, 1993.
- Liu, Y. & R.E. Weyers (1998). Modelling of the Time to Corrosion Cracking in Chloride Contaminated Reinforced Concrete Structures. *ACI Materials Journal*, Vol. 95, pp. 675-681.
- Thoft-Christensen, P. (2001). *What Happens with Reinforced Concrete Structures when the Reinforcement Corrodes?* Keynote Speech at the 2nd International Workshop on “Life-Cycle Cost Analysis and Design of Civil Infrastructure Systems”, Ube, Yamaguchi, Japan, September 27-29, 2001. Proceedings: Maintaining the Safety of Deteriorating Civil Infrastructures, pp. 293-304.
- Thoft-Christensen, P. (2003). *Modelling Corrosion Cracks*. IFIP TC7 Conference on “System Modeling and Optimization”, Sophia Antipolis, France, July 21-25, 2003.

STRUCTURAL RELIABILITY THEORY SERIES

PAPER NO. 231: P. Thoft-Christensen: FEM Modelling of the Evolution of Corrosion Cracks in Reinforced Concrete Structures. Presented at the IFIP WG 7.5 Conference on "Reliability and Optimization of Structural Systems", Banff, Alberta, Canada, November 2-5, 2003 (8 pages). (ISSN 1395-7953 R0302).

PAPER NO. 230: P. Thoft-Christensen: Modelling of Corrosion Cracks. Presented at the IFIP TC 7 Conference on "System Modeling and Optimization", Sophia Antipolis, France, July 21-25, 2003 (6 pages). (ISSN 1395-7953 R0305).

PAPER NO. 229: P. Thoft-Christensen: Stochastic Modelling and Optimization of Complex Infrastructure Systems. Presented at the IFIP TC 7 Conference on "System Modeling and Optimization", Sophia Antipolis, France, July 21-25, 2003. (14 pages). (ISSN 1395-7953 R0306).

PAPER NO. 228: P. Thoft-Christensen: Corrosion and Cracking of Reinforced Concrete. In proceedings of the 3rd IABMAS Workshop on Life-Cycle Cost Analysis and Design of Infrastructure Systems, Lausanne, March 2003: Life-Cycle Performance of Deteriorating Structures (edited by D.M. Frangopol, E. Brühwiler, M.H. Faber, B. Adey). ISBN 0-7844-0707-X. Printed by ASCE, USA, 2003, pp. 26-36. (ISSN 1395-7953 R0313).

PAPER NO. 227: Sørensen, J.D. : Brandstrup, J.D.: Stochastic Models for Directional Maximum Wave Height. ISSN 1395-7953 R0312 (25 pages).

PAPER NO. 226^E: Sørensen, J.D. : Damkilde, L.: Load-Bearing Capacity of Roof Trusses. (12 pages). (ISSN 1395-7953 R0309).

PAPER NO. 225: Sørensen, J.D. : Tarp-Johansen, N.J.: Cost- and Reliability-Based Optimization of Wind Turbines. ISSN 1395-7953 R0308 (25 pages).

PAPER NO. 224: P. Thoft-Christensen: Risk Analysis in Civil Engineering. Module 1 of a textbook used for a short course on Risk and Reliability in Civil Engineering at the International Conference on Safety, Risk and Reliability - Trends in Engineering, (IABSE), Malta, March 21, 2001 (43 pages). (ISSN 1395-7953 R0163).

PAPER NO. 223: Thoft-Christensen, P.: Service Life and Maintenance Modelling of Reinforced Concrete Bridge Decks. In Proceedings ACI Workshop, Cancun, Mexico, December 2002. (8 pages). (ISSN 1395-7953 R0224).

PAPER NO. 222: Sørensen, J. D. ; Stang, Birgitte Dela ; Svensson, Staffan: Calibration of Load Duration Factor k_{mod} . (25 pages). (ISSN 1395-7953 R0223).

PAPER NO. 221: Thoft-Christensen, P.: Stochastic Modelling of the Diffusion Coefficient for Concrete. . Presented at the IFIP Working Conference, Osaka, Japan, March 2002 (10 pages). (ISSN 1395-7953 R0204).

PAPER NO. 220: Sørensen, J.D. ; Faber, M.H.: Optimal, Generic Planning of Maintenance and Inspection of Steel Bridges. Submitted to IABMAS 2002, Barcelona, July 2002 (8 pages).

E = Electronic version, see address below

A full list of papers can be seen from <http://www.bt.aau.dk/publ/srlist.html>

COMMEE

ISSN 1395-7953 R0302

Dept. of Building Technology and Structural Engineering

Aalborg University, November 2003

Sohngaardsholmsvej 57, DK-9000 Aalborg, Denmark

Phone: +45 9635 8080 Fax: +45 9814 8243

www.bt.aau.dk