



AALBORG UNIVERSITY
DENMARK

Aalborg Universitet

Mechanical Properties of Alginate Hydrogels Cross-Linked with Multivalent Cations

Malektaj, Haniyeh; Drozdov, Aleksey D.; Christiansen, Jesper deClaville

Published in:
Polymers

DOI (link to publication from Publisher):
[10.3390/polym15143012](https://doi.org/10.3390/polym15143012)

Creative Commons License
CC BY 4.0

Publication date:
2023

Document Version
Publisher's PDF, also known as Version of record

[Link to publication from Aalborg University](#)

Citation for published version (APA):
Malektaj, H., Drozdov, A. D., & Christiansen, J. D. (2023). Mechanical Properties of Alginate Hydrogels Cross-Linked with Multivalent Cations. *Polymers*, 15(14), Article 3012. <https://doi.org/10.3390/polym15143012>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

Take down policy

If you believe that this document breaches copyright please contact us at vbn@aub.aau.dk providing details, and we will remove access to the work immediately and investigate your claim.

Article

Mechanical Properties of Alginate Hydrogels Cross-Linked with Multivalent Cations

Haniyeh Malektaj * , Aleksey D. Drozdov  and Jesper deClaville Christiansen 

Department of Materials and Production, Aalborg University, Fibigerstraede 16, 9220 Aalborg, Denmark; aleksey@mp.aau.dk (A.D.D.); jc@mp.aau.dk (J.d.C.)

* Correspondence: haniyehm@mp.aau.dk

Abstract: Ionically, cross-linked alginate gels have a potential to be used in a wide range of biomedical, environmental and catalytic applications. The study deals with preparation of alginate hydrogels cross-linked with various cations and the analysis of their equilibrium swelling and mechanical properties. It is shown that the type of cations used in the cross-linking process affects the elastic moduli and the equilibrium degree of swelling of the gels. The experimental data in small-amplitude oscillatory tests are fitted with a model that involves two material parameters: the elastic modulus of a polymer network and a measure of its inhomogeneity. The influence of cations on these quantities is studied numerically. It is revealed that the dependence of the elastic modulus of ionically cross-linked alginate gels on their equilibrium degree of swelling differs from that predicted by the conventional theory for covalently cross-linked gels.

Keywords: alginate; hydrogel; multivalent cations; mechanical properties; equilibrium swelling



Citation: Malektaj, H.; Drozdov, A.D.; deClaville Christiansen, J.

Mechanical Properties of Alginate Hydrogels Cross-Linked with Multivalent Cations. *Polymers* **2023**, *15*, 3012. <https://doi.org/10.3390/polym15143012>

Academic Editor: Mikyung Shin

Received: 24 June 2023

Revised: 8 July 2023

Accepted: 11 July 2023

Published: 12 July 2023



Copyright: © 2023 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Alginate is a natural polysaccharide with excellent biodegradability and biocompatibility. Alginate-based hydrogels have found numerous applications in regenerative medicine [1–3], drug delivery [4,5], cell carriers [6], wound healing [7], tissue regeneration [8,9], as well as in environmental applications [10,11], flexible electronics [12,13], and food industry [14–16].

Alginate is composed of irregular blocks of β -d-mannuronic acid (M) and α -l-guluronic acid (G) residues [1]. CaCl_2 is a commonly used salt to cross-link alginate hydrogels. However, it causes fast gelation that leads to heterogenous cross-linking of the gels [17]. Alginate hydrogels with slower gelation show better structural uniformity and a higher elastic modulus than rapidly formed hydrogels [18]. Calcium salts with low solubility in pure water (CaCO_3 and CaSO_4) can become soluble using chemical reactions, resulting in uniform distribution of Ca^{2+} ions and gradual gelation of alginate hydrogels. The slow gelation of alginate was reported by the in situ release of Ca^{2+} from CaCO_3 and CaSO_4 particles induced by hydrolysis of GDL (d-glucono- δ -lactone) to reduce pH [19,20], which led to the formation of gels with a uniform structure and superior mechanical properties as scaffold materials. Characterization of the mechanical properties of gels made with CaCO_3 -GDL showed that compressive modulus and strength increased with calcium content due to an increase in the cross-linking density [18].

Mechanical properties play a crucial role in determining the suitability of hydrogels for various applications. The type of cations that are used for cross-linking and the strength of interactions between ions and alginate chains influence significantly the mechanical properties of the ionically cross-linked alginate hydrogel. Aqueous solution of alginate can be cross-linked by various divalent and trivalent cations such as Ca^{2+} , Sr^{2+} , Ba^{2+} , Cu^{2+} , Zn^{2+} , Mn^{2+} , Fe^{2+} , Cr^{3+} , and Fe^{3+} [21–24]. Alginate hydrogels cross-linked with Ca^{2+} ions exhibit typically the elastic moduli in the range of 1–100 kPa [25,26]. Their values depend on the concentration of cations and the composition of alginate chains. The

mechanical properties of alginate gels cross-linked by multivalent cations can be tuned by changing the type of cations [27]. The elastic moduli of Ca–alginate and Ba–alginate hydrogels prepared from 2 wt.% alginate solution in water with the same concentration of CaCl_2 or BaCl_2 cations (ranged from 0.5 to 10 wt.%) change in the intervals between 5 and 12 kPa, and between 7 and 20 kPa, respectively [28]. The degree of swelling can also be controlled by adjusting the concentration and type of multivalent cations used in the cross-linking process. Marcus et al. [29] showed that alginate microgels cross-linked with Ca^{2+} ions had a higher degree of swelling compared with those prepared with Ba^{2+} cations. The control over swelling behavior provides an opportunity to design hydrogels with tailored properties, such as targeted release of encapsulated cargos or responsiveness to environmental stimuli [30].

To widen applications of alginate hydrogels, some researchers combined Ca^{2+} with other metal ions such as Ba^{2+} and Al^{3+} [24,31]. An important opportunity in the preparation of alginate gels is to select and mix ions based on their biological effects. In [32], strontium was employed in combination with calcium to cross-link alginate chains in order to enhance the osteogenic differentiation. Alginate gels cross-linked with Zn^{2+} ions are highly toxic. An addition of calcium ions to zinc ions reduces toxicity of alginate gels. Alginate gels cross-linked with a mixture of zinc and calcium ions are efficient in protecting surfaces by blocking adhesion of microalgae [33]. Wang et al. [34] revealed that alginate fibers prepared by using Ca–Cu, Ca–Ba, and Ca–Zn ionic systems exhibited a substantial decrease in bacterial growth in comparison to alginate fibers cross-linked with Ca ions. Moreover, alginate fibers cross-linked with hybrid ions demonstrated superior mechanical strength and toughness compared with Ca–alginate fibers. Shaheen et al. [35] explored the effect of direct conjugation of two metal ions on the rheological and swelling properties of an alginate gel as compared to their single metal ion counterparts. It was observed that the bimetallic hydrogels usually possess superior self-healing ability, swelling properties, water retention capability, and mechanical strength as compared to the monometallic alginate hydrogels.

The mechanical properties of ionically cross-linked alginate hydrogels are changed when gels are exposed to physiological media. The hydrogels disintegrate in the presence of chelating agents, monovalent ions, and non-cross-linking divalent ions found in tissue culture medium and fluids [36,37]. It was also reported that alginate hydrogels cross-linked with various cations can be prepared by using seawater instead of pure water without losing their mechanical properties. This provides an advantage in large-scale hydrogel production by saving pure water [38].

In [21], a two-step cross-linking process was used to prepare an ionically cross-linked Ca–alginate gel. This method ensures uniform cross-linking of polymer chains, resulting in stable gels that can withstand degradation in a 0–0.2 M NaCl solution. A similar approach is used in the present work. At the first step, alginate chains are weakly cross-linked by Ca^{2+} in an aqueous solution with a low pH. At the next step, the gels are immersed into a strong solution of various salts to complete the cross-linking process.

The objective of this study is to investigate the mechanical properties and the equilibrium swelling of homogeneous alginate hydrogels cross-linked with various divalent and trivalent ions (Ca^{2+} , Sr^{2+} , Cu^{2+} , Zn^{2+} , and Fe^{3+}). In previous works, mechanical and swelling properties were not analyzed simultaneously. Dynamic mechanical analysis (DMA) is used to characterize the mechanical properties of hydrogels. It was found that the trivalent cation (Fe^{3+}) has a stronger effect on the mechanical properties than divalent cations. The mechanical properties of the hydrogels cross-linked with divalent ions are noticeably affected by the affinity of cations to alginate chains (the interactions between cations and M and G blocks of alginate chains). The hydrogels under investigation have potential applications in artificial tissues and structural materials.

2. Materials and Methods

2.1. Materials

Alginic acid sodium salt from brown algae was purchased from Acros Organics (Geel, Belgium). Calcium chloride (CaCl_2) was provided by Merck, Burlington, MA, USA. Copper chloride (CuCl_2), and iron III chloride hexahydrate ($\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$) were purchased from Sigma-Aldrich, St. Louis, MO, USA. Strontium chloride hexahydrate ($\text{SrCl}_2 \cdot 6\text{H}_2\text{O}$) was provided by Strem Chemicals, Newburyport, MA, USA. Zinc chloride (ZnCl_2) was provided by Honeywell, Seelze, Germany. Hydrochloric acid (HCl), 37% (v/v), was supplied by VWR International (Rosny-sous-Bois, France). Deionized water was used in preparation and testing of hydrogels.

2.2. Preparation of Hydrogels

Several series of ionically cross-linked alginate gels were prepared with different salts by a method described previously in [21]. First, pH of an alginate solution (1 wt.%) was reduced to 3.5 by the addition of HCl in order to reduce the ionization of carboxyl groups at the alginate backbone. The alginate solution was mixed with 50 mM of CaCl_2 solution in proportion 28:1 (v/v). The mixture was poured into a mold and kept at room temperature overnight to prepare a weak gel. These weak hydrogels were immersed into a CaCl_2 (1 M), CaCl_2 (0.1 M), SrCl_2 (1 M), CuCl_2 (1 M), ZnCl_2 (1 M), or FeCl_3 (0.1 M) solutions for 2 days to complete the cross-linking process. Afterwards, all hydrogels were immersed into neutral water overnight to remove unreacted moieties.

2.3. Mechanical Tests

The DMA Q800 V20.9 (TA Instruments, New Castle, DE, USA) was used to measure the storage modulus E' and the loss modulus E'' in small-amplitude compressive oscillatory tests at temperature $T = 22^\circ\text{C}$ with strain amplitude of 0.5% and frequency f ranged from 0.1 to 60 Hz. The measurements were conducted three times on disc-shape samples with a diameter of 8.5 mm and height of 4.5 mm. The standard deviations of the data did not exceed 5% of their mean values.

2.4. Swelling Tests

Equilibrium swelling tests were conducted on alginate hydrogels immersed in 1 L aqueous solutions with $\text{pH} = 7$ at temperature $T = 22^\circ\text{C}$. Pre-weighted disc samples with diameter of 8.5 mm and height of 2.5 mm were immersed in aqueous solution with $\text{pH} = 7$, and their equilibrium weights were measured after three days. This duration exceeds the time (assessed in [21]) necessary for the samples to reach their equilibrium. The equilibrium degree of swelling Q_∞ was determined by the formula:

$$Q_\infty = \frac{w_\infty - w_0}{w_0} \quad (1)$$

where w_0 and w_∞ stand for the weight of a dry sample and its weight under equilibrium, respectively.

The measurements were repeated five times on different disc-shape samples. The experimental data are presented as the mean values. The scatter of the data is relatively small, with the standard deviations that do not exceed 5% of the mean values.

3. Results

3.1. The Mechanical Properties of Alginate Hydrogels

To assess the effect of cations on the mechanical properties of alginate hydrogels, the storage modulus E' and loss modulus E'' were measured in small-amplitude oscillatory tests. The effect of frequency f on the storage E' and loss E'' moduli of gels prepared with 1 M divalent cations is illustrated in Figure 1A. Since the gels prepared with 1 M FeCl_3 had very low stretchability and could not maintain their structural integrity (results not shown) [35], a lower concentration (0.1 M) of FeCl_3 was chosen. At higher concentrations,

aggregation of FeCl_3 occurs, leading to the destruction of bonds [39]. For comparison, the storage E' and loss E'' moduli of Ca–alginate prepared with 0.1 M CaCl_2 were presented in Figure 1B. The storage E' and loss E'' moduli of the gels prepared with various divalent cations decrease in the order Cu–alginate > Sr–alginate > Ca–alginate > Zn–alginate in the entire frequency f range between 0.1 and 60 Hz. Compared to divalent cations, Fe^{3+} ions induce a strong increase in the storage and loss moduli.

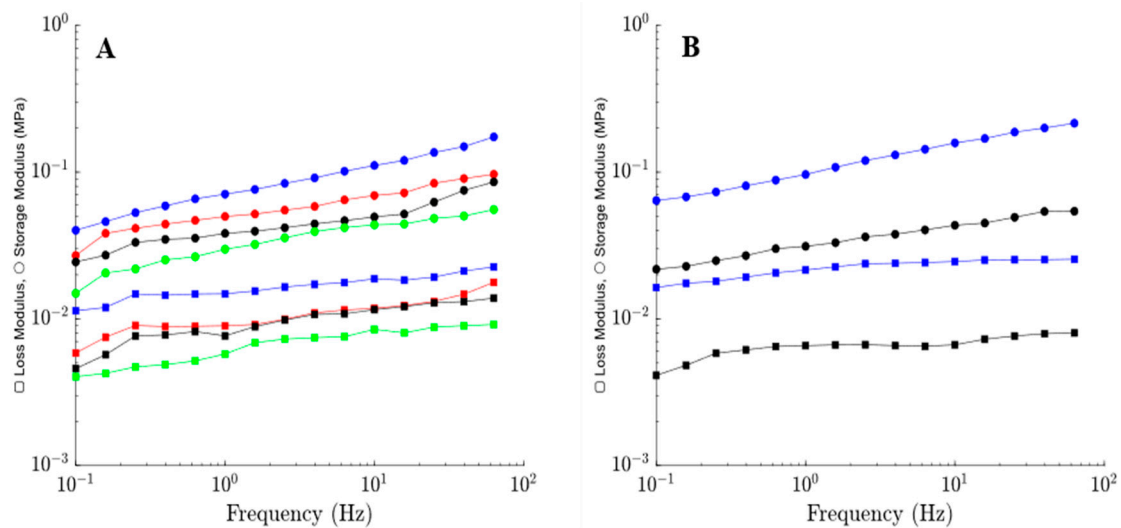


Figure 1. Storage modulus E' (circles) and loss modulus E'' (squares) versus frequency f for alginate hydrogels cross-linked with (A) 1 M of CuCl_2 (blue), SrCl_2 (red), CaCl_2 (black), ZnCl_2 (green), and (B) 0.1 M of FeCl_3 (blue), CaCl_2 (black).

Each set of data in Figure 1A,B was fitted separately by using the model discussed in [40]. The storage $E'(\omega)$ and loss $E''(\omega)$ moduli are given by

$$E'(\omega) = E \int_0^{\infty} f(v) \frac{\omega^2}{\Gamma^2(v) + \omega^2} dv \quad (2)$$

$$E''(\omega) = E \int_0^{\infty} f(v) \frac{\Gamma(v)\omega}{\Gamma^2(v) + \omega^2} dv \quad (3)$$

The rate of rearrangement of reversible bonds between chains $\Gamma(v)$ is determined by the Eyring formula:

$$\Gamma(v) = \Gamma_0 \exp(-v) \quad (4)$$

where v is a dimensionless activation energy, and Γ_0 is a pre-factor, which is considered to be constant 15.000 s^{-1} .

The inhomogeneity of a polymer network is characterized by the probability density $f(v)$ to find a reversible bond with an activation energy v . The latter is described by the quasi-Gaussian formula:

$$f(v) = f_0 \exp\left(-\frac{v^2}{2\Sigma^2}\right) \quad (5)$$

where Σ is a measure of inhomogeneity.

The model treats a gel as a temporary network of flexible polymer chains connected by reversible bonds. The bonds can break and reform at random instants. Rearrangement of transient bonds occurs due to thermal fluctuations. Each bond is characterized by the activation energy v necessary for its breakage. The distribution of bonds with various activation energies is determined by the function $f(v)$ given by Equation (5), where Σ characterizes the inhomogeneity of the network. When a temporary bond breaks, the stresses in chains connected by this bond vanish. When a new temporary bond is formed,

the initial state of the chains merged by this bond coincides with the current state of the network. In accord with the “egg-box” model for ionically cross-linked alginate gels [41], the inhomogeneity of a polymer network is affected by the number of cations and G-blocks forming a particular zipping structure between two nearby chains, as well as the strength of ionic interactions between them.

Given an angular frequency $\omega = 2\pi f$, Equations (2) and (3) together with Equation (4) for $\Gamma(v)$ and Equation (5) for $f(v)$ involve two material parameters: (i) E stands for the elastic modulus of a gel, and (ii) Σ is a measure of inhomogeneity of the polymer network. These coefficients are found by fitting experimental data depicted in Figure 2. Each set of observations is matched separately by means of the nonlinear regression method. Figure 2 demonstrates an acceptable agreement between the experimental data and results of numerical simulation.

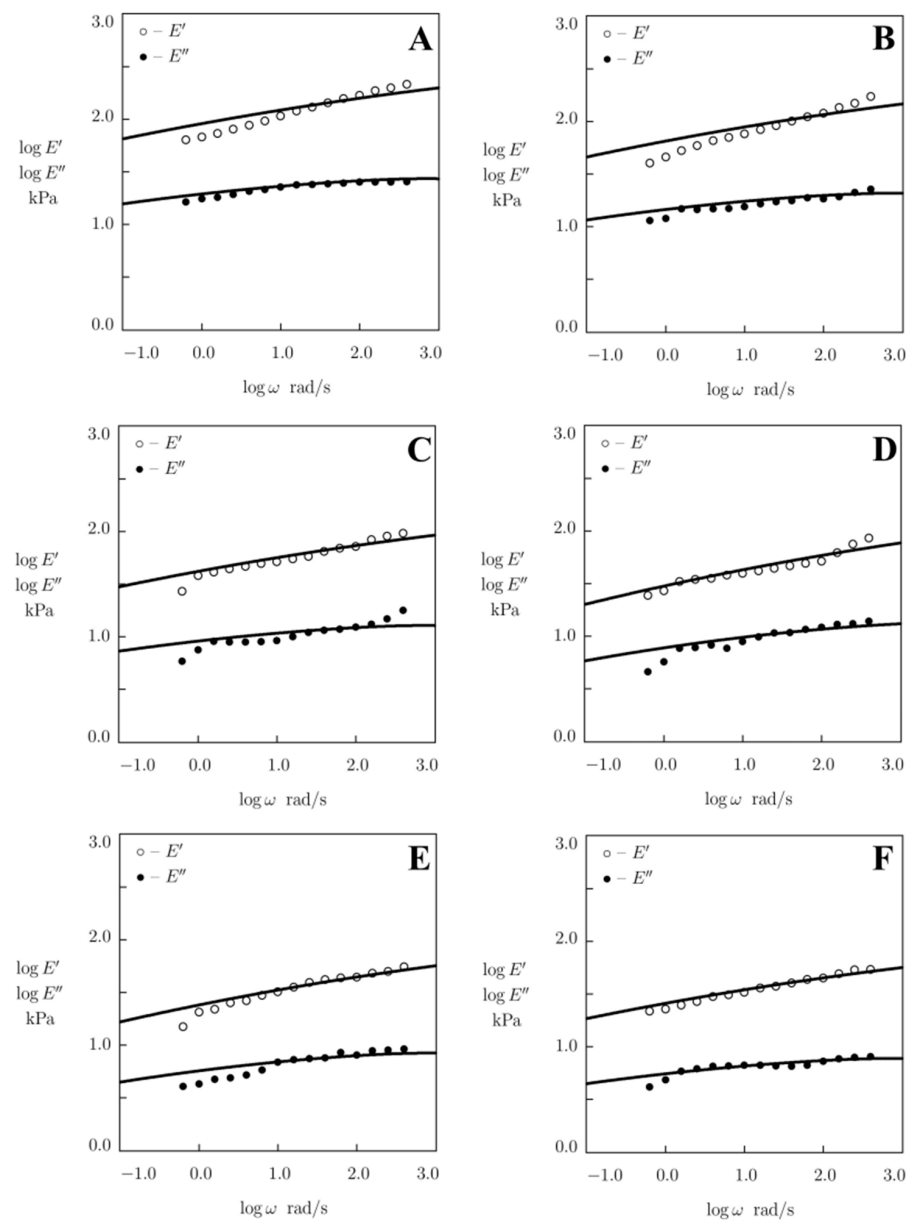


Figure 2. Storage modulus E' and loss modulus E'' versus angular frequency ω . Symbols: experimental data on alginate gels cross-linked with (A) Fe^{3+} ions (0.1 M), (B) Cu^{2+} ions (1 M), (C) Sr^{2+} ions (1 M), (D) Ca^{2+} ions (1 M), (E) Zn^{2+} ions (1 M), and (F) Ca^{2+} ions (0.1 M). Solid lines: results of numerical analysis.

The values of E and Σ for all gels under consideration are presented in Table 1. The data show that the coefficient Σ is practically independent of the type of cations, and the difference between the maximum 10.6 and the minimum 9.9 values of Σ is around 6%. The elastic modulus E of the gel cross-linked with 0.1 M Fe^{3+} ions exceed that for the gels with 0.1 M Ca^{2+} ions by a factor of 3.5. The type of divalent cations cross-linking the polymer network affects the elastic modulus E of hydrogels. The modulus E decreases in the following order: $\text{Cu}^{2+} > \text{Sr}^{2+} = \text{Ca}^{2+} > \text{Zn}^{2+}$.

Table 1. Material parameters for alginate hydrogels cross-linked with various cations.

| Ion | Σ | E (kPa) |
|--------------------------|----------|-----------|
| Fe^{3+} (0.1 M) | 10.6 | 252.0 |
| Cu^{2+} (1 M) | 10.3 | 187.6 |
| Sr^{2+} (1 M) | 10.5 | 117.4 |
| Ca^{2+} (1 M) | 9.9 | 117.5 |
| Zn^{2+} (1 M) | 9.9 | 73.1 |
| Ca^{2+} (0.1 M) | 10.6 | 71.5 |

3.2. The Equilibrium Degree of Swelling of Alginate Hydrogels

To analyze the influence of cations on the equilibrium degree of swelling, samples of alginate gels were immersed in solutions with $\text{pH} = 7$, and their equilibrium degrees of swelling Q_∞ were measured. The results are presented in Figure 3A where equilibrium degree of swelling Q_∞ was shown for each cation. The equilibrium degree of swelling Q_∞ is affected by the salt used in the preparation procedure, and it grows with a decrease in the elastic modulus E .

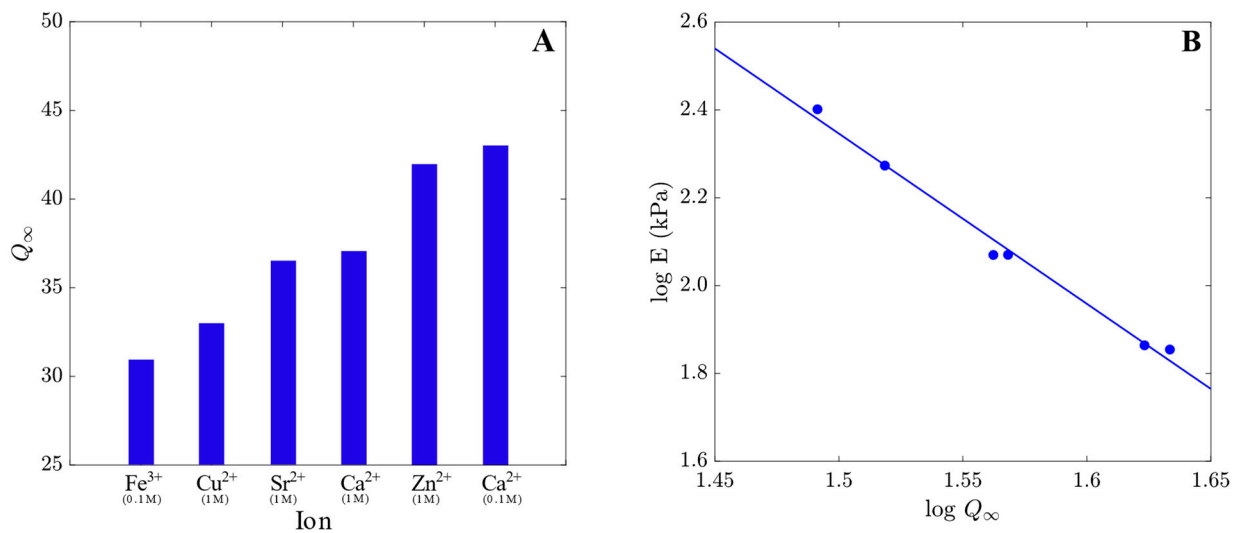


Figure 3. (A) Equilibrium degree of swelling Q_∞ of alginate hydrogels cross-linked with various cations, and (B) The elastic modulus E versus equilibrium degree of swelling Q_∞ . Circles: experimental data. Solid line: their approximation by Equation (7).

The dependence of E on Q_∞ was approximated by Equation [42],

$$E \sim \frac{1}{Q_\infty^B}, \quad (6)$$

which can be presented in the form

$$\log E = A - B \log Q_\infty. \quad (7)$$

The elastic modulus E is plotted in Figure 3B as a function of the equilibrium degree of swelling Q_∞ . The coefficient $B = 3.9$ was determined using the least-square method. This value differs from those predicted by the conventional theories for covalently cross-linked gels (according to these theories, B ranges from 1/3 to 2/3).

4. Discussion

We prepared alginate hydrogels cross-linked with various multivalent cations (Fe^{3+} , Cu^{2+} , Sr^{2+} , Ca^{2+} , Zn^{2+}) and investigated their mechanical properties by means of DMA.

The experimental study involved small-amplitude oscillatory tests in a frequency f range from 0.1 to 60 Hz. It is revealed that the E'' and E' values are affected by cations. A model was used to approximate each set of E'' and E' data in the small-amplitude oscillatory tests. It is found that trivalent ions (Fe^{3+}) have a stronger effect on the elastic modulus E , compared to divalent ions. The elastic modulus E of alginate gels cross-linked with divalent ions decreases in the following order: $\text{Cu}^{2+} > \text{Sr}^{2+} = \text{Ca}^{2+} > \text{Zn}^{2+}$. The divalent ions form two-dimensional egg-box structures with alginate [43], while the trivalent cations are able to form three-dimensional structures [35,44]. Trivalent cations can interact with three carboxylic groups of different alginate chains at the same time. This leads to an increase in the coordination number and formation of a 3D bonding structure [35,44,45].

Molecular modeling and nuclear magnetic resonance (NMR) spectroscopy demonstrated that charge and ion radius of multivalent cations can affect interaction of ions with alginic acid, and the charge may play a more critical role [45,46]. A relationship between the mechanical properties and the ionic radius of divalent ions was introduced in [45], where it was shown that Ba^{2+} cations with a larger ion radius compared to Ca^{2+} can form a tighter structure than Ca^{2+} . This is because Ba^{2+} cations are able to fill a larger space between the blocks of alginate polymers, resulting in a more tightly arranged structure [45]. However, this hypothesis is applicable mostly for cations of the same group. We showed that although Cu^{2+} has a smaller ionic radius than Sr^{2+} , it has a higher elastic modulus. Therefore, factors other than ionic radius affect the mechanical properties of alginate gels.

The mechanical properties of alginate hydrogels depend on the interaction between cations and GG blocks, MM blocks, and MG blocks [45,47]. Fe^{3+} ions can combine with GG, MM, and MG blocks in alginate resulting in enhanced strength of the hydrogel [48]. For the trivalent lanthanide ions, there is a preference for GG blocks over MM blocks, while GG and MM blocks exhibit a stronger binding affinity as the charge density increases [46]. The affinity of alginate toward different divalent ions decreases in the following order: $\text{Pb} > \text{Cu} > \text{Cd} > \text{Ba} > \text{Sr} > \text{Ca} > \text{Co} = \text{Ni} = \text{Zn} > \text{Mn}$ [49–51]. This order agrees with our results and can be explained by the interaction between divalent cations and alginate blocks. According to the “egg-box” model, each Ca^{2+} ion is coordinated by four guluronate units [46], two from each chain. More coordination sites of Sr^{2+} with alginate molecule than Ca^{2+} were reported in [52], which resulted in a stronger binding of Sr^{2+} with alginate [52,53]. However, Sr^{2+} is likely to bind only to GG complex [27], whereas Ca^{2+} binds to both GG and MG blocks, while Zn^{2+} binds to all MM, GG, and MG blocks [54]. However, Zn^{2+} lacks specificity and binds randomly with GG, MM, and MG blocks. In addition, since Zn^{2+} has a low affinity for binding to alginate, it results in a looser network with a higher equilibrium degree of swelling and lower tensile properties [54]. Although Cu^{2+} ions are less selective for binding to alginate [55], their strong binding affinity led to the formation of a rigid structure [56,57]. The lowest release of Cu^{2+} from alginate films compared to Ca^{2+} and Zn^{2+} was reported in [55] and explained by the higher binding affinity of Cu^{2+} .

Moreover, coordination chemistry also plays an important role in the strength of the cation–alginate complexes [58,59]. In [60], the computed bond distances, cation interaction energies, and molecular orbital compositions revealed that the interaction between uronate units and alkaline earth metal ions is purely electrostatic, while transition metals establish strong covalent–coordination bonds. Alkaline earth metal ions have a relatively low charge density and larger ionic radius, making them more likely to form electrostatic interactions rather than strong covalent bonds with the carboxylate groups. The partially

filled d-orbitals of copper facilitate additional interactions, such as d-orbital overlap with carboxylate groups. These additional interactions contribute to the formation of covalent coordination bonds, which enhance the strength of the Cu–alginate complexes. On the other hand, Zn–alginate primarily involves electrostatic interactions. Although zinc can form coordination bonds, the absence of partially filled d-orbitals and a smaller ionic radius result in weaker covalent interactions compared to Cu^{2+} .

The differences in the strength of cations–alginate gels can be attributed to a combination of factors, including the charge density, ionic radius, coordination chemistry, selectivity, and affinity of ions for binding to alginate and the interaction between cations and GG blocks, MM blocks, and MG blocks.

The equilibrium degree of swelling of alginate gels cross-linked with multivalent ions increases in the following order: $\text{Fe}^{3+} < \text{Cu}^{2+} < \text{Sr}^{2+} < \text{Ca}^{2+} < \text{Zn}^{2+}$. The degree of swelling of Ca–alginate hydrogels increases with a decrease in the CaCl_2 concentration in the cross-linking solution as reported in [37]. For practical use, high water content hydrogels should not only show good conductivity but should also be sufficiently strong and have good elastic properties [61]. The mechanical properties of hydrogels are greatly influenced by the fraction of water inside them which is characterized by the equilibrium degree of swelling Q_∞ [61,62]. The elastic modulus E decreases with equilibrium degree of swelling Q_∞ . A similar behavior for alginate hydrogels was observed in [63]. Comparison of hydrogels prepared with 0.1 and 1 M CaCl_2 in Figure 3 shows that at higher concentrations of Ca^{2+} ions, longer GG/GG junctions are formed that are more resistant to elastic deformation and have a higher elastic modulus E .

Alginate gels cross-linked with various ions can be used in such applications as drug delivery, tissues engineering, skin grafting, and biocatalysts. There is an opportunity to select ions based on their known biological effects. Sr^{2+} or Cu^{2+} ions cannot be used to immobilize cells due to their potential toxic effect on cells [64,65], while the Ca^{2+} and Zn^{2+} cations can be used in drug immobilization [65]. Elements closely chemically related to Ca, such as Sr, have pharmacological and metabolic effects on bones in vivo.

For example, Sr^{2+} is beneficial for the bone growth and repair through the activation of osteoblast activity and suppression of osteoclast (bone resorbing) function [32,66]. However, both positive and negative effects of Sr^{2+} on bone growth depend on the concentration of Sr^{2+} ions, availability of calcium in the diet, kidney function, and the animal model [67]. Studies show that Sr (as chloride) is not toxic for bone cells at low doses (lower than 1% or 4 mmol Sr/kg/day) [68,69], whereas higher doses can cause skeletal abnormalities, especially in animals with low-calcium diets [67]. Therefore, it is recommended to use Sr simultaneously with Ca for bone repair.

Fe–alginate can overcome the deficiencies of Ca–alginate, such as poor protein adsorptive capacity. Fe–alginate gels can be used as an effective cell culture substrate [48]. The rich redox chemistry of Fe^{3+} cations can be exploited for a wide range of applications, such as drug delivery, tissue engineering, or environmental remediation [70]. Alginate hydrogels are characterized by a broad chemical modification capacity, which makes them suitable for applications as metal catalysts [71] and biocatalysts [72,73].

5. Conclusions

Alginate gels cross-linked with Fe^{3+} , Cu^{2+} , Sr^{2+} , Ca^{2+} , and Zn^{2+} ions have been prepared, and their mechanical and swelling properties have been studied. Each set of E' and E'' data in small-amplitude compressive oscillatory tests was approximated by a model with two parameters. An acceptable agreement is demonstrated between the data and results of simulation. Cross-linking with Fe^{3+} cations leads to a strong increase in the elastic modulus. The elastic moduli of alginate gels cross-linked with divalent ions decay in the order of Cu–alginate > Sr–alginate = Ca–alginate > Zn–alginate. The divalent ions form a 2D egg-box structure with alginate chains, while the binding extent of trivalent cations with alginate produces a more compact network. In addition to the charge density, the mechanical properties depend on the interaction between cations and GG blocks, MM

blocks, and MG blocks of alginate. The elastic modulus E and the equilibrium degree of swelling Q_{∞} of ionically cross-linked alginate gels are connected by Equation (7) with a coefficient B that differs from those predicted by the conventional theories for covalently cross-linked hydrogels.

Author Contributions: Conceptualization, A.D.D. and J.d.C.; data curation, H.M. and A.D.D.; formal analysis, H.M.; funding acquisition, J.d.C.; investigation, H.M.; methodology, A.D.D.; resources, J.d.C.; writing—original draft, H.M.; writing—review and editing, H.M., A.D.D. and J.d.C. All authors have read and agreed to the published version of the manuscript.

Funding: This research was supported by the Danish Research Infrastructure Program (NUFI) through the ESS SMART (Structure of Materials in Real Time) Lighthouse program, grant number 9091-00010B.

Institutional Review Board Statement: Not applicable.

Data Availability Statement: The data that support the findings of this study are available from the corresponding author, H.M., upon reasonable request.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Sun, J.; Tan, H. Alginate-based biomaterials for regenerative medicine applications. *Materials* **2013**, *6*, 1285–1309. [[CrossRef](#)]
2. Raus, R.A.; Nawawi, W.M.F.W.; Nasaruddin, R.R. Alginate and alginate composites for biomedical applications. *Asian J. Pharm. Sci.* **2021**, *16*, 280–306. [[CrossRef](#)] [[PubMed](#)]
3. Lee, K.Y.; Mooney, D.J. Alginate: Properties and biomedical applications. *Prog. Polym. Sci.* **2012**, *37*, 106–126. [[CrossRef](#)]
4. Hariyadi, D.M.; Islam, N. Current status of alginate in drug delivery. *Adv. Pharmacol. Pharm. Sci.* **2020**, *2020*, 8886095. [[CrossRef](#)]
5. Jana, S.; Kumar Sen, K.; Gandhi, A. Alginate based nanocarriers for drug delivery applications. *Curr. Pharm. Des.* **2016**, *22*, 3399–3410. [[CrossRef](#)] [[PubMed](#)]
6. Kumar Giri, T.; Thakur, D.; Alexander, A.; Badwaik, H.; Krishna Tripathi, D. Alginate based hydrogel as a potential biopolymeric carrier for drug delivery and cell delivery systems: Present status and applications. *Curr. Drug Deliv.* **2012**, *9*, 539–555. [[CrossRef](#)]
7. Xu, S.; Sun, Z.; Sun, C.; Li, F.; Chen, K.; Zhang, Z.; Hou, G.; Cheng, H.M.; Li, F. Homogeneous and fast ion conduction of PEO-based solid-state electrolyte at low temperature. *Adv. Funct. Mater.* **2020**, *30*, 2007172. [[CrossRef](#)]
8. Farokhi, M.; Jonidi Shariatzadeh, F.; Solouk, A.; Mirzadeh, H. Alginate based scaffolds for cartilage tissue engineering: A review. *Int. J. Polym. Mater. Polym. Biomater.* **2020**, *69*, 230–247. [[CrossRef](#)]
9. Aguero, L.; Alpdagtas, S.; Ilhan, E.; Zaldivar-Silva, D.; Gunduz, O. Functional role of crosslinking in alginate scaffold for drug delivery and tissue engineering: A review. *Eur. Polym. J.* **2021**, *160*, 110807. [[CrossRef](#)]
10. Thakur, S.; Sharma, B.; Verma, A.; Chaudhary, J.; Tamulevicius, S.; Thakur, V.K. Recent progress in sodium alginate based sustainable hydrogels for environmental applications. *J. Clean. Prod.* **2018**, *198*, 143–159. [[CrossRef](#)]
11. Wang, B.; Wan, Y.; Zheng, Y.; Lee, X.; Liu, T.; Yu, Z.; Huang, J.; Ok, Y.S.; Chen, J.; Gao, B. Alginate-based composites for environmental applications: A critical review. *Crit. Rev. Environ. Sci. Technol.* **2019**, *49*, 318–356. [[CrossRef](#)]
12. Hu, L.; Chee, P.L.; Sugiarto, S.; Yu, Y.; Shi, C.; Yan, R.; Yao, Z.; Shi, X.; Zhi, J.; Kai, D. Hydrogel-based flexible electronics. *Adv. Mater.* **2023**, *35*, 2205326. [[CrossRef](#)]
13. Teng, K.; An, Q.; Chen, Y.; Zhang, Y.; Zhao, Y. Recent development of alginate-based materials and their versatile functions in biomedicine, flexible electronics, and environmental uses. *ACS Biomater. Sci. Eng.* **2021**, *7*, 1302–1337. [[CrossRef](#)] [[PubMed](#)]
14. Gundewadi, G.; Rudra, S.G.; Sarkar, D.J.; Singh, D. Nanoemulsion based alginate organic coating for shelf life extension of okra. *Food Packag. Shelf Life* **2018**, *18*, 1–12. [[CrossRef](#)]
15. Gheorghita Puscaselu, R.; Lobiuc, A.; Dimian, M.; Covasa, M. Alginate: From food industry to biomedical applications and management of metabolic disorders. *Polymers* **2020**, *12*, 2417. [[CrossRef](#)]
16. Li, D.; Wei, Z.; Xue, C. Alginate-based delivery systems for food bioactive ingredients: An overview of recent advances and future trends. *Compr. Rev. Food Sci. Food Saf.* **2021**, *20*, 5345–5369. [[CrossRef](#)]
17. Skjåk-Bræk, G.; Grasdalen, H.; Smidsrød, O. Inhomogeneous polysaccharide ionic gels. *Carbohydr. Polym.* **1989**, *10*, 31–54. [[CrossRef](#)]
18. Kuo, C.K.; Ma, P.X. Ionically crosslinked alginate hydrogels as scaffolds for tissue engineering: Part 1. Structure, gelation rate and mechanical properties. *Biomaterials* **2001**, *22*, 511–521. [[CrossRef](#)]
19. Kuo, C.K.; Ma, P.X. Maintaining dimensions and mechanical properties of ionically crosslinked alginate hydrogel scaffolds in vitro. *J. Biomed. Mater. Res. Part A Off. J. Soc. Biomater. Jpn. Soc. Biomater. Aust. Soc. Biomater. Korean Soc. Biomater.* **2008**, *84*, 899–907.
20. Liu, G.; Zhou, H.; Wu, H.; Chen, R.; Guo, S. Preparation of alginate hydrogels through solution extrusion and the release behavior of different drugs. *J. Biomater. Sci. Polym. Ed.* **2016**, *27*, 1808–1823. [[CrossRef](#)]

21. Malektaj, H.; Drozdov, A.D.; deClaville Christiansen, J. Swelling of Homogeneous Alginate Gels with Multi-Stimuli Sensitivity. *Int. J. Mol. Sci.* **2023**, *24*, 5064. [[CrossRef](#)] [[PubMed](#)]
22. Hu, C.; Lu, W.; Mata, A.; Nishinari, K.; Fang, Y. Ions-induced gelation of alginate: Mechanisms and applications. *Int. J. Biol. Macromol.* **2021**, *177*, 578–588. [[CrossRef](#)]
23. Haug, A.; Smidsrød, O.; Högdahl, B.; Øye, H.; Rasmussen, S.; Sunde, E.; Sørensen, N.A. Selectivity of some anionic polymers for divalent metal ions. *Acta Chem. Scand* **1970**, *24*, 843–854. [[CrossRef](#)]
24. Zhang, X.; Wang, X.; Fan, W.; Liu, Y.; Wang, Q.; Weng, L. Fabrication, property and application of calcium alginate fiber: A review. *Polymers* **2022**, *14*, 3227. [[CrossRef](#)] [[PubMed](#)]
25. Nützl, M.; Schrottenbaum, M.; Müller, T.; Müller, R. Mechanical properties and chemical stability of alginate-based anisotropic capillary hydrogels. *J. Mech. Behav. Biomed. Mater.* **2022**, *134*, 105397. [[CrossRef](#)]
26. Schütz, K.; Placht, A.M.; Paul, B.; Brüggemeier, S.; Gelinsky, M.; Lode, A. Three-dimensional plotting of a cell-laden alginate/methylcellulose blend: Towards biofabrication of tissue engineering constructs with clinically relevant dimensions. *J. Tissue Eng. Regen. Med.* **2017**, *11*, 1574–1587. [[CrossRef](#)]
27. Mørch, Y.A.; Donati, I.; Strand, B.L.; Skjak-Braek, G. Effect of Ca^{2+} , Ba^{2+} , and Sr^{2+} on alginate microbeads. *Biomacromolecules* **2006**, *7*, 1471–1480. [[CrossRef](#)]
28. Roberge, C.L.; Kingsley, D.M.; Cornely, L.R.; Spain, C.J.; Fortin, A.G.; Corr, D.T. Viscoelastic Properties of Bioprinted Alginate Microbeads Compared to Their Bulk Hydrogel Analogs. *J. Biomech. Eng.* **2023**, *145*, 031002. [[CrossRef](#)]
29. Darrabie, M.D.; Kendall, W.F.; Opara, E.C. Effect of alginate composition and gelling cation on microbead swelling. *J. Microencapsul.* **2006**, *23*, 613–621. [[CrossRef](#)]
30. Sood, N.; Bhardwaj, A.; Mehta, S.; Mehta, A. Stimuli-responsive hydrogels in drug delivery and tissue engineering. *Drug Deliv.* **2016**, *23*, 748–770. [[CrossRef](#)]
31. Reddy, O.S.; Subha, M.; Jithendra, T.; Madhavi, C.; Rao, K.C. Curcumin encapsulated dual cross linked sodium alginate/montmorillonite polymeric composite beads for controlled drug delivery. *J. Pharm. Anal.* **2021**, *11*, 191–199. [[CrossRef](#)] [[PubMed](#)]
32. Catanzano, O.; Soriente, A.; La Gatta, A.; Cammarota, M.; Ricci, G.; Fasolino, I.; Schiraldi, C.; Ambrosio, L.; Malinconico, M.; Laurienzo, P. Macroporous alginate foams crosslinked with strontium for bone tissue engineering. *Carbohydr. Polym.* **2018**, *202*, 72–83. [[CrossRef](#)] [[PubMed](#)]
33. Abi Nassif, L.; Rioual, S.; Trepos, R.; Fauchon, M.; Farah, W.; Hellio, C.; Abboud, M.; Lescop, B. Development of alginate hydrogels active against adhesion of microalgae. *Mater. Lett.* **2019**, *239*, 180–183. [[CrossRef](#)]
34. Wang, Q.; Zhang, L.; Liu, Y.; Zhang, G.; Zhu, P. Characterization and functional assessment of alginate fibers prepared by metal-calcium ion complex coagulation bath. *Carbohydr. Polym.* **2020**, *232*, 115693. [[CrossRef](#)]
35. Shaheen, A.; Maswal, M.; Dar, A.A. Synergistic effect of various metal ions on the mechanical, thixotropic, self-healing, swelling and water retention properties of bimetallic hydrogels of alginate. *Colloids Surf. A Physicochem. Eng. Asp.* **2021**, *627*, 127223. [[CrossRef](#)]
36. LeRoux, M.A.; Guilak, F.; Setton, L.A. Compressive and shear properties of alginate gel: Effects of sodium ions and alginate concentration. *J. Biomed. Mater. Res. Off. J. Soc. Biomater. Jpn. Soc. Biomater. Aust. Soc. Biomater. Korean Soc. Biomater.* **1999**, *47*, 46–53. [[CrossRef](#)]
37. Matyash, M.; Despang, F.; Ikonomidou, C.; Gelinsky, M. Swelling and mechanical properties of alginate hydrogels with respect to promotion of neural growth. *Tissue Eng. Part C Methods* **2014**, *20*, 401–411. [[CrossRef](#)]
38. Mredha, M.T.I.; Pathak, S.K.; Cui, J.; Jeon, I. Hydrogels with superior mechanical properties from the synergistic effect in hydrophobic-hydrophilic copolymers. *Chem. Eng. J.* **2019**, *362*, 325–338. [[CrossRef](#)]
39. Zhang, Z.; Lin, T.; Li, S.; Chen, X.; Que, X.; Sheng, L.; Hu, Y.; Peng, J.; Ma, H.; Li, J. Polyacrylamide/Copper-Alginate Double Network Hydrogel Electrolyte with Excellent Mechanical Properties and Strain-Sensitivity. *Macromol. Biosci.* **2021**, *22*, 2100361. [[CrossRef](#)]
40. Drozdov, A.D.; Christiansen, J.D. Tuning the viscoelastic response of hydrogel scaffolds with covalent and dynamic bonds. *J. Mech. Behav. Biomed. Mater.* **2022**, *130*, 105179. [[CrossRef](#)]
41. Cao, L.; Lu, W.; Mata, A.; Nishinari, K.; Fang, Y. Egg-box model-based gelation of alginate and pectin: A review. *Carbohydr. Polym.* **2020**, *242*, 116389. [[CrossRef](#)]
42. Rubinstein, M.; Colby, R.H.; Dobrynin, A.V.; Joanny, J.-F. Elastic modulus and equilibrium swelling of polyelectrolyte gels. *Macromolecules* **1996**, *29*, 398–406. [[CrossRef](#)]
43. Choi, I.; Lee, Y.; Lyu, J.S.; Lee, J.-S.; Han, J. Characterization of ionically crosslinked alginate films: Effect of different anion-based metal cations on the improvement of water-resistant properties. *Food Hydrocoll.* **2022**, *131*, 107785. [[CrossRef](#)]
44. Menakbi, C.; Quignard, F.; Mineva, T. Complexation of trivalent metal cations to mannuronate type alginate models from a density functional study. *J. Phys. Chem. B* **2016**, *120*, 3615–3623. [[CrossRef](#)] [[PubMed](#)]
45. Yang, C.H.; Wang, M.X.; Haider, H.; Yang, J.H.; Sun, J.-Y.; Chen, Y.M.; Zhou, J.; Suo, Z. Strengthening alginate/polyacrylamide hydrogels using various multivalent cations. *ACS Appl. Mater. Interfaces* **2013**, *5*, 10418–10422. [[CrossRef](#)]
46. DeRamos, C.; Irwin, A.; Nauss, J.; Stout, B. ¹³C NMR and molecular modeling studies of alginic acid binding with alkaline earth and lanthanide metal ions. *Inorg. Chim. Acta* **1997**, *256*, 69–75. [[CrossRef](#)]

47. Montanucci, P.; Terenzi, S.; Santi, C.; Pennoni, I.; Bini, V.; Pescara, T.; Basta, G.; Calafiore, R. Insights in behavior of variably formulated alginate-based microcapsules for cell transplantation. *BioMed Res. Int.* **2015**, *2015*, 965804. [[CrossRef](#)]
48. Machida-Sano, I.; Ogawa, S.; Ueda, H.; Kimura, Y.; Satoh, N.; Namiki, H. Effects of composition of iron-cross-linked alginate hydrogels for cultivation of human dermal fibroblasts. *Int. J. Biomater.* **2012**, *2012*, 820513. [[CrossRef](#)]
49. Güven, K.; Akyüz, K.; Yurdun, T. Selectivity of heavy metal binding by algal polysaccharides. *Toxicol. Environ. Chem.* **1995**, *47*, 65–70. [[CrossRef](#)]
50. Haug, A.; Smidsrød, O. The effect of divalent metals on the properties of alginate solutions. *Acta Chem. Scand* **1965**, *19*, 341–351. [[CrossRef](#)]
51. Wang, J.; Song, T.; Chen, H.; Ming, W.; Cheng, Z.; Liu, J.; Liang, B.; Wang, Y.; Wang, G. Bioinspired High-Strength Montmorillonite-Alginate Hybrid Film: The Effect of Different Divalent Metal Cation Crosslinking. *Polymers* **2022**, *14*, 2433. [[CrossRef](#)]
52. Zhang, X.; Wang, L.; Weng, L.; Deng, B. Strontium ion substituted alginate-based hydrogel fibers and its coordination binding model. *J. Appl. Polym. Sci.* **2020**, *137*, 48571. [[CrossRef](#)]
53. Yamagiwa, K.; Kozawa, T.; Nakamura, A.; Ohkawa, A. Immobilization of denitrifier within a matrix with low oxygen permeability. *Biotechnol. Tech.* **1997**, *11*, 95–98. [[CrossRef](#)]
54. Iskandar, L.; Rojo, L.; Di Silvio, L.; Deb, S. The effect of chelation of sodium alginate with osteogenic ions, calcium, zinc, and strontium. *J. Biomater. Appl.* **2019**, *34*, 573–584. [[CrossRef](#)] [[PubMed](#)]
55. Goh, C.H.; Heng, P.W.S.; Chan, L.W. Cross-linker and non-gelling Na⁺ effects on multi-functional alginate dressings. *Carbohydr. Polym.* **2012**, *87*, 1796–1802. [[CrossRef](#)]
56. Velings, N.M.; Mestdagh, M.M. Physico-chemical properties of alginate gel beads. *Polym. Gels Netw.* **1995**, *3*, 311–330. [[CrossRef](#)]
57. Ouwerx, C.; Velings, N.; Mestdagh, M.; Axelos, M.A. Physico-chemical properties and rheology of alginate gel beads formed with various divalent cations. *Polym. Gels Netw.* **1998**, *6*, 393–408. [[CrossRef](#)]
58. Reig-Vano, B.; Huck-Iriart, C.; de la Flor, S.; Trojanowska, A.; Tylkowski, B.; Giamberini, M. Structural and mechanical analysis on mannuronate-rich alginate gels and xerogels beads based on Calcium, Copper and Zinc as crosslinkers. *Int. J. Biol. Macromol.* **2023**, *246*, 125659. [[CrossRef](#)] [[PubMed](#)]
59. Hari, D.; Kannan, A. A DFT study on Ca-Alginate interactions with divalent transition metals. *Mater. Today: Proc.* **2022**, *62*, 1532–1543. [[CrossRef](#)]
60. Agulhon, P.; Markova, V.; Robitzer, M.; Quignard, F.; Mineva, T. Structure of alginate gels: Interaction of diuronate units with divalent cations from density functional calculations. *Biomacromolecules* **2012**, *13*, 1899–1907. [[CrossRef](#)]
61. Tran, V.T.; Mredha, M.T.I.; Pathak, S.K.; Yoon, H.; Cui, J.; Jeon, I. Conductive tough hydrogels with a staggered ion-coordinating structure for high self-recovery rate. *ACS Appl. Mater. Interfaces* **2019**, *11*, 24598–24608. [[CrossRef](#)]
62. Donati, I.; Mørch, Y.A.; Strand, B.L.; Skjåk-Bræk, G.; Paoletti, S. Effect of elongation of alternating sequences on swelling behavior and large deformation properties of natural alginate gels. *J. Phys. Chem. B* **2009**, *113*, 12916–12922. [[CrossRef](#)]
63. Saarai, A.; Sedlacek, T.; Kasparkova, V.; Kitano, T.; Saha, P. On the characterization of sodium alginate/gelatine-based hydrogels for wound dressing. *J. Appl. Polym. Sci.* **2012**, *126*, E79–E88. [[CrossRef](#)]
64. Simó, G.; Fernández-Fernández, E.; Vila-Crespo, J.; Ruipérez, V.; Rodríguez-Nogales, J.M. Research progress in coating techniques of alginate gel polymer for cell encapsulation. *Carbohydr. Polym.* **2017**, *170*, 1–14. [[CrossRef](#)] [[PubMed](#)]
65. Santos Peretiatko, C.D.; Andreza Hupaló, E.; da Rocha Campos, J.R.; Budziak Parabocz, C.R. Efficiency of Zinc and Calcium Ion Crosslinking in Alginate-coated Nitrogen Fertilizer. *Orbital Electron. J. Chem.* **2018**, *10*, 218–225. [[CrossRef](#)]
66. Place, E.S.; Rojo, L.; Gentleman, E.; Sardinha, J.P.; Stevens, M.M. Strontium-and zinc-alginate hydrogels for bone tissue engineering. *Tissue Eng. Part A* **2011**, *17*, 2713–2722. [[CrossRef](#)] [[PubMed](#)]
67. Marie, P.; Ammann, P.; Boivin, G.; Rey, C. Mechanisms of action and therapeutic potential of strontium in bone. *Calcif. Tissue Int.* **2001**, *69*, 121. [[CrossRef](#)]
68. Grynepas, M.; Hamilton, E.; Cheung, R.; Tsouderos, Y.; Deloffre, P.; Hott, M.; Marie, P. Strontium increases vertebral bone volume in rats at a low dose that does not induce detectable mineralization defect. *Bone* **1996**, *18*, 253–259. [[CrossRef](#)]
69. Grynepas, M.; Marie, P. Effects of low doses of strontium on bone quality and quantity in rats. *Bone* **1990**, *11*, 313–319. [[CrossRef](#)] [[PubMed](#)]
70. Roquero, D.M.; Othman, A.; Melman, A.; Katz, E. Iron (III)-cross-linked alginate hydrogels: A critical review. *Mater. Adv.* **2022**, *3*, 1849–1873. [[CrossRef](#)]
71. Bahsis, L.; Ablouh, E.-H.; Anane, H.; Taourirte, M.; Julve, M.; Stiriba, S.-E. Cu (II)-alginate-based superporous hydrogel catalyst for click chemistry azide–alkyne cycloaddition type reactions in water. *RSC Adv.* **2020**, *10*, 32821–32832. [[CrossRef](#)] [[PubMed](#)]
72. Torres, L.G.; Velasquez, A.; Brito-Arias, M.A. Ca-alginate spheres behavior in presence of some solvents and water-solvent mixtures. *Adv. Biosci. Biotechnol.* **2011**, *2*, 8–12. [[CrossRef](#)]
73. Hassan, R.; Tirkistani, F.; Zaafarany, I.; Fawzy, A.; Khairy, M.; Iqbal, S. Polymeric biomaterial hydrogels. I. Behavior of some ionotropic cross-linked metal-alginate hydrogels especially copper-alginate membranes in some organic solvents and buffer solutions. *Adv. Biosci. Biotechnol.* **2012**, *3*, 845–854. [[CrossRef](#)]

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.