

## Performance and endurance of a high temperature PEM fuel cell operated on methanol reformat

Araya, Samuel Simon; Grigoras, Ionela; Zhou, Fan; Andreasen, Søren Juhl; Kær, Søren Knudsen

*Published in:*  
International Journal of Hydrogen Energy

*DOI (link to publication from Publisher):*  
[10.1016/j.ijhydene.2014.09.007](https://doi.org/10.1016/j.ijhydene.2014.09.007)

*Publication date:*  
2014

*Document Version*  
Early version, also known as pre-print

[Link to publication from Aalborg University](#)

*Citation for published version (APA):*

Araya, S. S., Grigoras, I., Zhou, F., Andreasen, S. J., & Kær, S. K. (2014). Performance and endurance of a high temperature PEM fuel cell operated on methanol reformat. *International Journal of Hydrogen Energy*, 39(32), 18343–18350. <https://doi.org/10.1016/j.ijhydene.2014.09.007>

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -


### Take down policy

If you believe that this document breaches copyright please contact us at [vbn@aub.aau.dk](mailto:vbn@aub.aau.dk) providing details, and we will remove access to the work immediately and investigate your claim.



Available online at [www.sciencedirect.com](http://www.sciencedirect.com)

ScienceDirect

journal homepage: [www.elsevier.com/locate/he](http://www.elsevier.com/locate/he)

# Performance and endurance of a high temperature PEM fuel cell operated on methanol reformat

Samuel Simon Araya<sup>\*</sup>, Ionela Florentina Grigoras, Fan Zhou,  
Søren Juhl Andreassen, Søren Knudsen Kær

Department of Energy Technology, Aalborg University, Pontoppidanstræde 101, 9220 Aalborg East, Denmark

## ARTICLE INFO

### Article history:

Received 12 June 2014

Received in revised form

28 August 2014

Accepted 2 September 2014

Available online xxx

### Keywords:

High temperature PEM

Fuel cell

Methanol

Impedance spectroscopy

## ABSTRACT

This paper analyzes the effects of methanol and water vapor on the performance of a high temperature proton exchange membrane fuel cell (HT-PEMFC) at varying temperatures, ranging from 140 °C to 180 °C. For the study, a H<sub>3</sub>PO<sub>4</sub> – doped polybenzimidazole (PBI) – based membrane electrode assembly (MEA) of 45 cm<sup>2</sup> active surface area from BASF was employed. The study showed overall negligible effects of methanol-water vapor mixture slips on performance, even at relatively low simulated steam methanol reforming conversion of 90%, which corresponds to 3% methanol vapor by volume in the anode gas feed. Temperature on the other hand has significant impact on the performance of an HT-PEMFC. To assess the effects of methanol-water vapor mixture alone, CO<sub>2</sub> and CO are not considered in these tests. The analysis is based on polarization curves and impedance spectra registered for all the test points. After the performance tests, endurance test was performed for 100 h at 90% methanol conversion and an overall degradation rate of –55 μV/h was recorded.

Copyright © 2014, Hydrogen Energy Publications, LLC. Published by Elsevier Ltd. All rights reserved.

## Introduction

Some of the main advantages of fuel cells compared to traditional energy conversion devices are their superior efficiency, fuel flexibility and possibility for renewable power generation. These advantages together with their modular nature are making them increasingly attractive as power sources of the future.

According to the fuel cell industry review by Fuel Cell Today, fuel cells are now commercial and profitable for various applications, with overall fuel cell system shipments (excluding toys and education kits) in 2012 of 45,700, growing

by 86% compared to 2011 [1]. The report forecasts even more success for fuel cells in the near future.

Proton exchange membrane (PEM) fuel cells are the most developed and most commercialized among fuel cell types to date [2]. They have the advantage of working at a relatively low temperature and hence with faster startup and easier manageability they are attractive for several applications, such as automotive, microCHP, uninterrupted power supply (UPS) and auxiliary power units (APUs).

Some of the main drawbacks of fuel cells that are hindering their widespread commercialization are cost, durability and infrastructure. Hydrogen infrastructure can be costly as the initial investment costs are high, even though, production

<sup>\*</sup> Corresponding author. Tel.: +45 2137 1172.

E-mail address: [ssa@et.aau.dk](mailto:ssa@et.aau.dk) (S. Simon Araya).

<http://dx.doi.org/10.1016/j.ijhydene.2014.09.007>

0360-3199/Copyright © 2014, Hydrogen Energy Publications, LLC. Published by Elsevier Ltd. All rights reserved.

Methanol steam reforming produces impurities like  $\text{CO}_2$ , CO and unconverted methanol-water vapor mixture. However, the study of the poisoning effects of reformat mixtures is usually limited to  $\text{CO}_2$  and CO, perhaps due the fact that they are common to most reforming processes, especially the reforming of alcohols and hydrocarbons. The effects of CO are usually associated to preferential surface adsorption of its molecules on the catalyst, thereby reducing the electro-active area [14]. The effects of  $\text{CO}_2$  on the other hand are limited to dilution of the anode feed, with the possibility of chemical or electrochemical reduction into CO [15]. There are also several mitigation techniques suggested for CO and  $\text{CO}_2$  poisoning, which include increasing the operating temperature and performing partial oxidation of CO by oxygen bleeding on the anode [12,16]. However, the effects of wet methanol reformat are not well documented and thus the phenomena is not clearly understood. Consequently, there are not many suggestions on how to mitigate the effects.


In our previous works, preliminary performance and durability studies of an HT-PEMFC at relatively high methanol-water vapor mixture have been presented [19,20]. High methanol concentrations were tested in order to accelerate tests and they revealed that the vapor mixture has degrading effects if present at concentrations of above 3%. The current study focuses on methanol contents between 0 and 3%, which is what can be expected from methanol steam reformers of different efficiencies and different operating temperatures [8,21].

## Experimental

The experimental setup incorporates a methanol vaporizer, which is used to supply a controlled amount of methanol to the anode feed. It also has the capabilities for humidifying and preheating the anode feed gases.

### Test procedures

First, break-in conditioning of the fuel cell was performed according to the BASF's recommendations before the start of characterization tests. The conditioning was performed for 100 h at 160 °C, at current density of 0.2 A/cm<sup>2</sup>, and stoichiometric ratios of 1.2 and 4, on the anode and the cathode respectively. Then, Methanol reforming conversions from 90%

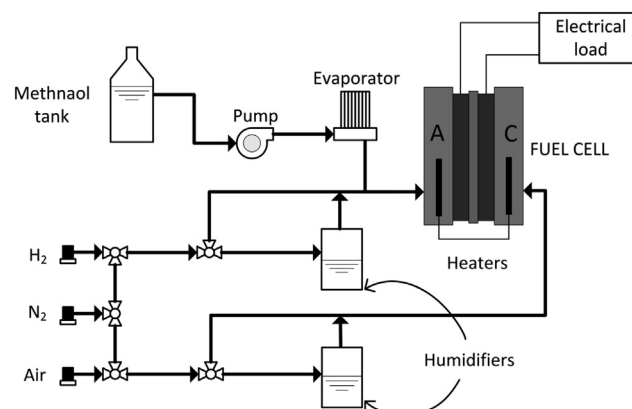


**Fig. 1 – Schematic of the experimental setup.**

to 100% were tested, starting from pure and dry hydrogen towards higher concentration of unconverted methanol in reformat mixture. Tests with dry hydrogen were carried out as reference for the tests in the presence of vapor mixture in the anode feed. Preheating of anode gases is also tested to see whether this affects the performance of a fuel cell.

Finally, after the performance characterization tests, an endurance test was conducted for 100 h at 160 °C. This was done to see if the effects exacerbate when the fuel cell is exposed to the methanol slip for prolonged period of time. A methanol conversion of 90%, which corresponds to 3% of methanol slip in anode feed gas, was chosen for the endurance test.

### Test conditions

The following reaction was considered for the steam methanol reforming process;



where a steam to carbon (S/C) ratio of 1.5 is considered for the steam methanol reforming prior to feeding to the anode. This is an overall reaction excluding methanol decomposition and reverse water gas shift reaction, both of which give rise to CO formation. The methanol and water contents of the different conversion rates were calculated based on this overall reaction. To isolate the effects of methanol-water vapor mixture on the performance of the HT-PEMFC at varying temperatures, CO and CO<sub>2</sub> are not considered in the simulation of the reformat mixture in the current work.

The methanol concentrations and water vapor content of the anode feed are given in tab.1. These test points are repeated for temperatures between 140 °C and 180 °C at a temperature step of 10 °C.

Methanol was provided by means of an integrated methanol vaporizer in the test stand, and water vapor was provided as humidification by controlling the dew point of the anode gases. The dew point temperature of gaseous reactants is calculated using Magnus formula for every relative humidity corresponding to each reformer conversion ratio as follows [23];

$$\text{RH} = \frac{e}{e_s} \cdot 100 \quad (2)$$

$$e_s(T_d) = e(T) \quad (3)$$

$$e_s = C_1 \exp \left( \frac{A_1 T}{B_1 + T} \right) \quad (4)$$

where RH is the relative humidity, T is the anode feed temperature, T<sub>d</sub> is the dew point temperature, e is the vapor pressure and e<sub>s</sub> is the saturation vapor pressure. The coefficients' values are; A<sub>1</sub> = 17.625, B<sub>1</sub> = 243.04 °C, and C<sub>1</sub> = 610.94 Pa. Substituting Eq. (4) in Eq. (3) and combining with Eq. (2) gives the conversion from RH to T<sub>d</sub> for a given temperature of gases, T.

$$T_d = \frac{B_1 \left[ \ln \frac{\text{RH}}{100} + \left( \frac{A_1 T}{B_1 + T} \right) \right]}{A_1 - \ln \frac{\text{RH}}{100} - \left( \frac{A_1 T}{B_1 + T} \right)} \quad (5)$$

### Data analysis

To characterize the fuel cell comprehensively, polarization curves and EIS measurements were analyzed in complementarity to each other for every test point. The polarization curves were taken between 0 and 60 A at a current ramp rate of 1 A/sec in ascending current direction.

EIS was performed between 10 kHz and 0.1 Hz in a galvanostatic mode, in which AC current was applied and voltage response was registered. The interpretation of EIS data usually requires a model, whether physical or empirical, to be fitted to the measurements. In the current work an equivalent circuit (EC) model was used to translate the trends of impedance spectra and extract physical meaning from the data. The model used is shown in Fig. 2.

## Results and discussion

### Performance characterization

The performance of a H<sub>3</sub>PO<sub>4</sub>/PBI-based HT-PEMFC is mapped against operating temperature and methanol content of the anode feed. Temperature was varied, not only to test the effects of temperature on the fuel cell performance, but also to investigate whether the effects of methanol slip vary with temperature. Temperature is known to enhance the kinetics of the reactions that take place in a fuel cell [24,13,8]. Fig. 3 shows the effects of varying the operating temperature and preheating the anode gases. It can be seen that the performance of the fuel cell increases with increase in temperature. This is intuitive and in agreement with literature, as the reaction kinetics improve with increase in temperature, giving rise to better performances [25,13].

The effects of preheating the anode feed gas on the fuel cell performance is also tested. As shown in Fig. 3 the effects are negligible. Given the fact that CO is the main impurity whose effects are highly dependent on temperature [13], it is expected that preheating of the anode feed gas would have effects in the presence of CO. However, in the current study no CO is present in the anode feed, and therefore, the performance remains unaltered when anode gases are preheated. It could also be that even in the case where the anode feed gas is not preheated, the gases heat up immediately as they come into contact with the hot end plates.

With increase in temperature the impedance spectra in Fig. 4 shrink as a sign of decreasing impedance and therefore, increasing performance. This shrinking happens throughout the measured frequency range. This means that there is enhancement in all the fuel cell activities, electrode kinetics (the high frequency region), membrane conductivity (the real-


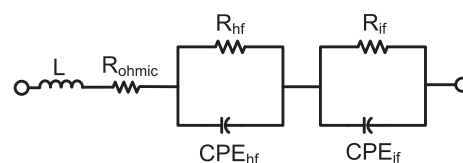


Fig. 2 – The equivalent circuit model used to fit the measured impedance spectra.

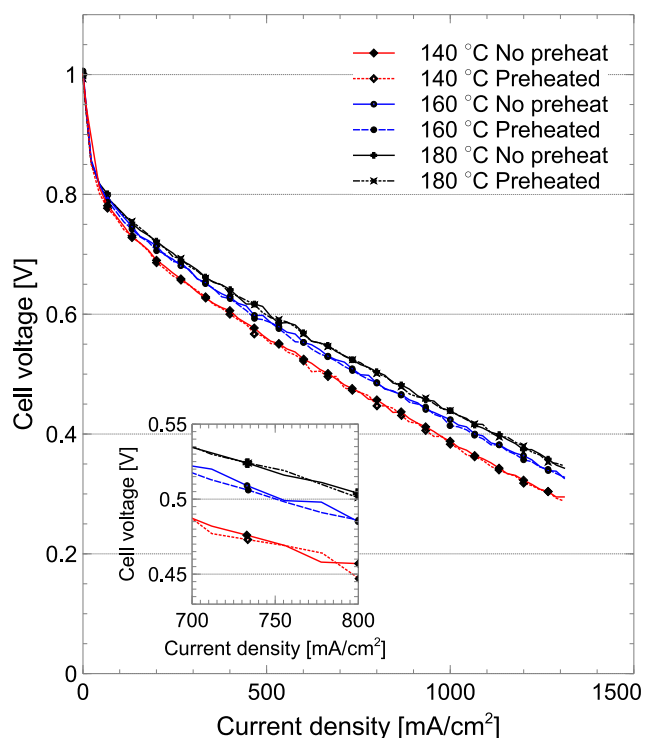


**Fig. 3 – I–V curves showing the effect of varying the operating temperature and preheating the anode feed gas on the fuel cell performance.**

axis intercept of the spectra) and mass transport (the low frequency region).

The increase in membrane conductivity with temperature is not linear, and there seems to be an optimal conductivity at around 160 °C. Above this temperature proton conductivity decreases for operation in dry hydrogen and remains unaltered or slightly decreases in the presence of vapor mixture of water and methanol. This is seen from the position of the real-axis intercept of the impedance spectra in Fig. 4 and the ohmic resistances in Fig. 5(a).

Fig. 5 shows both the effects of methanol slip and temperature. As already seen from the impedance spectra in Fig. 4, temperature enhances the performance at most ranges of frequency and for all concentrations of methanol. The only exceptions are the ohmic resistances above 160 °C and high frequency resistances above 170 °C for operation at 90% conversion, which increase with temperature. These suggest that temperature improves the electrode reaction kinetics and mass transport in the GDL. Xiao et al. [26] found that the conductivity of a typical phosphoric acid-doped PBI membrane made by the sol–gel process with approximately 32 mol of PA per PBI repeat unit increases with increasing temperature up to 200 °C. This is not entirely confirmed in the current work as the decrease in ohmic resistance, which is indicative of the increase in membrane conductivity, is clear only until 160 °C. Afterwards it either slightly increases or remains unaltered. It is not clear if this slight increase in ohmic resistance above 160 °C is related to phosphoric acid leaching, but it is known that the free nature of the phosphoric acid makes it volatile at higher operating temperatures, especially above 200 °C [26]. This can cause the fuel cell performance to

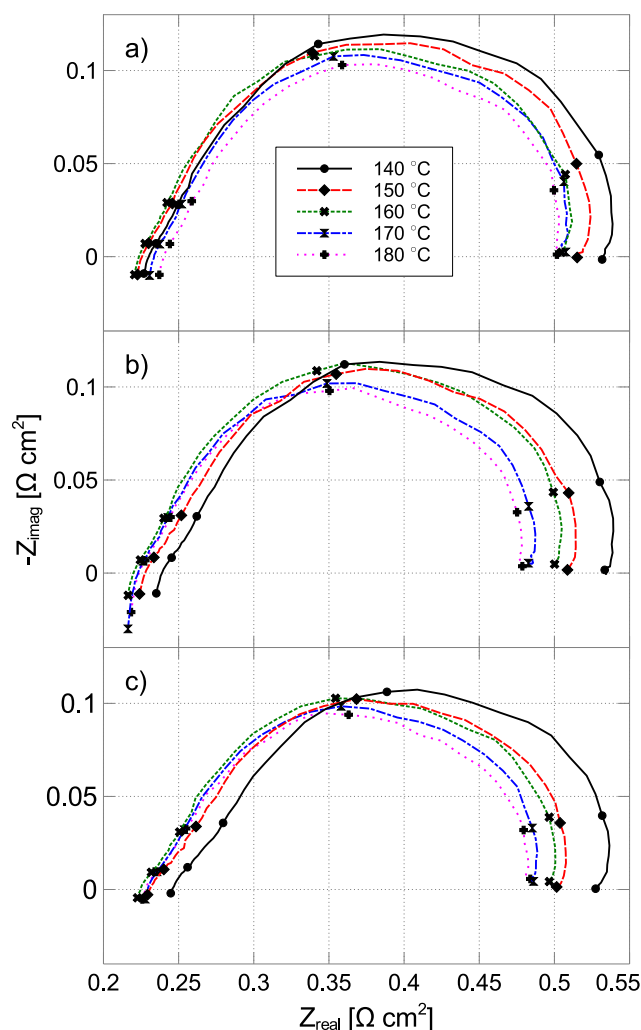


**Fig. 4 – Impedance spectra showing the effects of temperature for different anode compositions a) dry and pure hydrogen b) wet hydrogen with water alone c) wet hydrogen with water and methanol with the assumption of 90% conversion of methanol.**

decrease, due to the evaporation of phosphoric acid, which can lower the membrane conductivity.

To investigate the effects of methanol slip the performance mapping has been done by varying the concentration between 100% reformer conversion ratio and 90% conversion. These test points were chosen due to the trade-off in a methanol reformer between methanol conversion rate and CO formation, i.e., as reformer temperature increases, methanol conversion rate increases, and at the same time the rate of reverse water gas shift reaction increases producing more CO [27]. Kim [21] achieved a methanol conversion higher than 90% at temperature higher than 250 °C and at feed rate of methanol of 2 ml/h. At higher temperatures the conversion rate can go close to 100% [28]. Therefore, a methanol conversion range between 90% and 100% was chosen in order to investigate the effects of high concentrations of methanol slip, since the trade-off suggests that higher methanol slip corresponds to lower CO concentration, which is a known poison to PEM fuel cells.




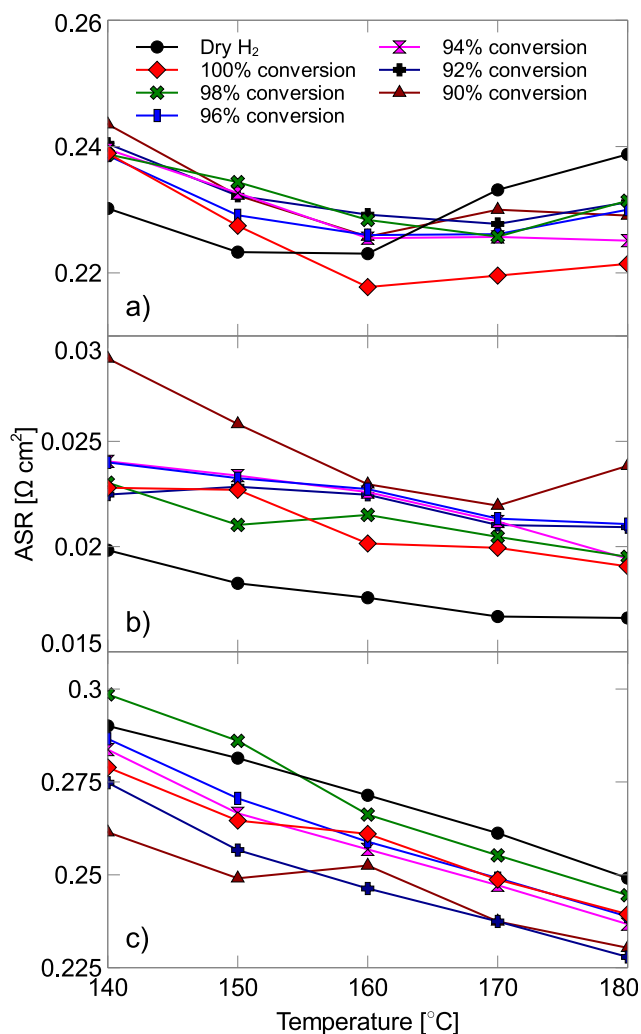

**Fig. 5 – Fitted resistances for varying temperatures and anode compositions a) ohmic resistances b) high frequency resistances c) intermediate-low frequency resistances.**

The results reveal that the effects of methanol on the overall performance of the fuel cell are negligible at all the tested concentrations. This can be noticed in the polarization curves in Fig. 6, where the different methanol concentrations are shown at 160 °C. The effects remain unaltered for the entire range of methanol conversion rates tested. A slight decrease in performance is seen when water vapor is added with respect to dry hydrogen operation. This decrease in performance corresponds to the decrease in hydrogen flow rate with decrease in conversion rate given in Table 1, especially from test point 1 to 2. Other studies state that the proton conductivity of PBI increases with increase in relative humidity, which suggests that if water vapor was added without decreasing the hydrogen flow rate, the performance would increase due to enhanced proton conductivity [29,12,30]. However, it is also stated that water produced from the electrochemical reaction at the cathode is capable of hydrating the polymeric material and promoting the cell performance, without the need for humidification [30].

The generally little or no effects of methanol-water vapor mixture are also confirmed from the impedance spectra in

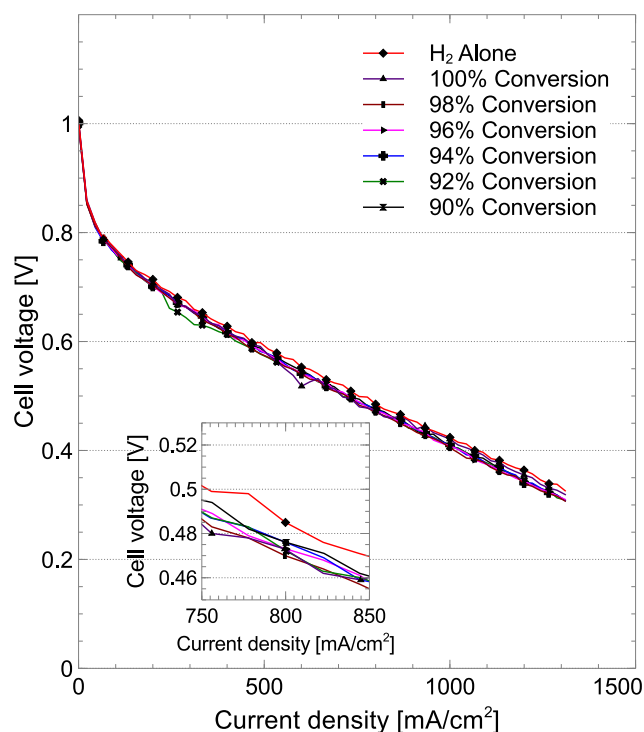

**Fig. 6 – I–V curves showing the effects of methanol slip at different simulated reforming conversion rates at 160 °C. The percentage values represent the conversion of methanol considered.**

Fig. 7. They show similar spectra for all measurements in the presence of methanol, from 98% to 90% methanol conversion, and similar spectra for the ones without methanol slip. These impedance spectra were recorded at 160 °C. The real-axis intercepts of the spectra, which denote the ohmic resistance of the fuel cell, move to the left in the case of 100% conversion. In this case the anode feed is composed of hydrogen and water vapor, and the shift towards left of the intercept may be attributed to the humidification of the membrane.

A closer look into the spectra by means of equivalent circuit fitting reveals more details and small changes due to methanol slip. The first observable change happens when water alone is added to the anode feed gas, as a simulation of 100% conversion ratio of a reformer running at S/C of 1.5. This corresponds to the addition of 14.29% by volume of water vapor and the decrease of hydrogen concentration by the same percentage by volume in the anode feed. There is an increase in ohmic resistance from dry hydrogen to 100% conversion at 140 °C and 150 °C, which can be attributed to decrease in hydrogen flow rate. Above 160 °C the ohmic resistances increase slightly for reformat operating conditions, but it does so more significantly for dry hydrogen operation. This could be due to the drying of the membrane in the case of dry hydrogen operation. In reformat operation on the other hand the presence of water vapor in the mixture keeps the membrane hydrated. The lowest ohmic resistances are achieved for 100% conversion at 160 °C, i.e., humidified hydrogen feed. Here the negative effect of reduced hydrogen concentration is overwhelmed by the positive effect of membrane humidification. At temperatures above 170 °C, the presence of

**Table 1 – Operating parameters for tests between 140 °C and 180 °C at a temperature step of 10 °C.**

Exp. id	Conversion	H <sub>2</sub>	H <sub>2</sub>	CH <sub>3</sub> OH	H <sub>2</sub> O
	[%]	[NLPM]	[% Volume]	[% Volume]	[% Volume]
1	H <sub>2</sub> (20 °C)	0.124	100	0	0
2	H <sub>2</sub> (140 °C)	0.124	100	0	0
3	100	0.106	85.71	0	14.29
4	98	0.105	84.48	0.57	14.94
5	96	0.103	83.24	1.16	15.61
6	94	0.102	81.98	1.74	16.28
7	92	0.100	80.70	2.34	17.65
8	90	0.098	79.41	2.94	19.96

methanol-water vapor mixture seems to prevent the membrane from drying out. However, the slightly higher resistances in the presence of methanol compared to water alone suggest that methanol vapor has slight negative effect on the ohmic resistances, and therefore, the membrane conductivity.

The high frequency resistances increase with increase in methanol slip, Fig. 5(b). This could be due to dehydrogenation process that methanol undergoes on platinum surface that can also lead to CO formation and therefore, can affect the electrode kinetics negatively [18]. In Fig. 5(b) it can be noticed that there is a significant increase in the resistances between dry H<sub>2</sub> and 100% conversion and then the increase slows with the addition of methanol. It can be said that the vapor mixture of methanol and water has generally negative effect on this frequency range. However, further isolation of the effects of methanol is required to have a more conclusive remarks on its effects. This frequency range is representative of the anodic processes, and therefore, the negative effect could be due to the dilution of the anode feed with the addition of the vapor mixture and the decrease of hydrogen flow rate. The complex reactions methanol is said to undergo on Pt surface could also play a role in these losses [18,31].

Low frequency resistances have decreasing trend both with increase in temperature and methanol slip. The resistances at this frequency range are the highest at 98% conversion ratio. Contrary to the general trend, this conversion ratio also shows higher resistance compared to 100% conversion ratio. This could suggest that methanol has a slightly negative effect on the phenomena represented in this frequency range, the cathodic activities and the diffusion limitations. However, these negative effects are masked for the rest of the conversions by the positive effects of humidification as both methanol and water contents in the anode feed increase.


Overall, the effect of methanol-water vapor mixture on performance is negligible for the measured concentrations. This is mainly because the dilution and degrading effects seen at high frequency range for anodic activities are balanced out by the enhanced mass transport due to the vapor mixture.

Furthermore, the generally parallel resistance lines in Fig. 5 with few exceptions at high temperature show that the effects of methanol do not depend on the operating temperature. An exception is seen in Fig. 5(b) at 90% conversion ratio, in both ends of the temperature range. This shows that at such low reformer conversion rates, it is best to operate the fuel cell at the typical operating temperatures of 160 °C and 170 °C. This also suggests that at low fuel cell operating temperature, low reformer conversion can have negative effects on the anode kinetics.

### Endurance test


After the performance characterization tests, an endurance test was conducted in the presence of methanol in the anode feed. The fuel cell was operated at constant current density of 0.33 A/cm<sup>2</sup> at constant temperature of 160 °C and hydrogen and air stoichiometry of 1.2 and 4, respectively. A simulated reformat of 90% conversion, was used for the anode feed composition.

The voltage profile in Fig. 8 shows how the cell potential changes during the 100 h of endurance test. For the chosen operating conditions the overall degradation rate is –55 μV/h. This is ten times the reported degradation rate of a Celtec MEA, at constant current density of 0.2 A/cm<sup>2</sup> at 160 °C and using dry gases over 18,000 h of operation [22]. On the other hand Hu et al. [32] found a higher degradation rate of –150 μV/h over 400 h of operation following 100 h of conditioning at constant load of 0.64 A/cm<sup>2</sup> at 150 °C for their home-made unit

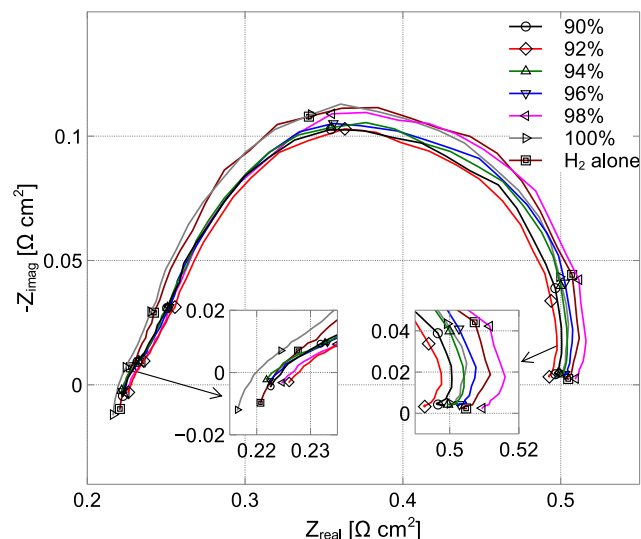

**Fig. 7 – Impedance spectra showing the effects of methanol slip at different simulated reforming conversion rates at 160 °C. The percentage values represent the conversion of methanol considered.**



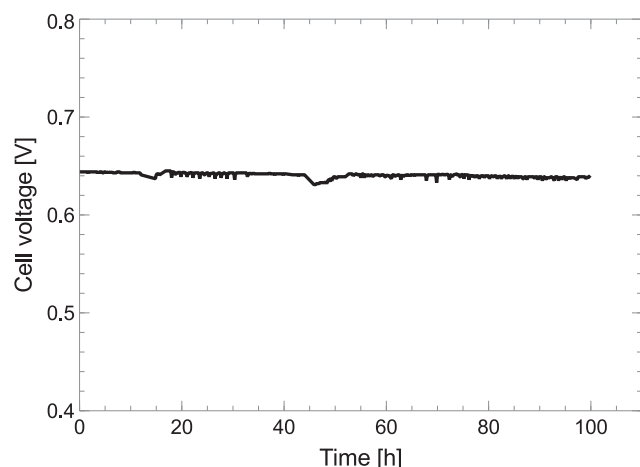

**Fig. 8 – Durability tests in the presence of methanol at 160 °C.**

cell assembly. Other degradation rates at similar conditions as the current work but pure hydrogen operation include, Modestov et al. [33] and Galbiati et al. [34] at 0.2 A/cm<sup>2</sup> at 160 °C, with degradation rates of  $-25 \mu\text{V/h}$  and  $-10 \mu\text{V/h}$ , respectively. The difference in degradation rates may be attributed, other than the different operating conditions, also to the different MEA manufacturing and doping processes. Some test bench specific factors, such as the techniques used to assemble the fuel cell and the balance of plant of the fuel cell system may also affect the operation of the fuel cell, and therefore, the degradation rate. In general, it can be said that the degradation rates in this work are above the average of pure hydrogen operations in literature, implying that part of the degradation may be caused by the presence of the reformate vapor.

However, negligible effect on performance and not significant degradation on endurance tests mean simpler fuel cell and reformer design, and overall simpler system integration. There is increasing interest in using renewable methanol as a viable hydrogen carrier as it offers higher energy density, and is more economical compared to pure hydrogen. This has led some to consider internal reforming of methanol in fuel cells or coupling methanol reformers and fuel cells in compact systems [11,8]. The results of the current work suggest that such a reformer can be run at conversion rates as low as 90%, with negligible effects on the performance of the fuel cell and no significant degradation up to 100 h. This means it can be run at temperatures comparable to that of the fuel cell and produce lower CO concentrations.

## Conclusions

The effects of methanol-water vapor mixture at different concentrations and varying operating temperatures on the performance of PBI-based HT-PEMFC were studied. Endurance test was also performed for 100 h at 90% conversion.

The overall effects of methanol-water vapor mixture on the performance are negligible at all the measured vapor concentrations. However, from the impedance measurements it is

found that the vapor mixture has negative effects on the high frequency region and positive effects on the low frequency region. Therefore, the membrane conductivity and the electrode activities are slightly degraded, whereas the mass transport losses are slightly reduced. This results in an overall balancing of positive and negative effects on the fuel cell performance.

An overall degradation of  $-55 \mu\text{V/h}$  over a 100 h of endurance tests at 90% conversion was registered. This is above the average degradation rate for pure hydrogen operations in literature, implying that part of the degradation may be caused by the presence of the reformate vapor.

## Acknowledgment

The work that led to these results has been funded by the Danish Energy Technology Development and Demonstration Program (EUDP) through the project – Commercial Breakthrough of Advanced Fuel Cells (COBRA) 64010-0033 and 64012-0257. The authors would also like to thank SerEnergy A/S for providing MEAs.

## REFERENCES

- [1] Fuel Cell Today. The fuel cell industry review. 2013. Tech. Rep.; Fuel Cell Today; 2013.
- [2] Fuel Cell Today. The fuel cell today industry review. 2012. Tech. Rep.; 2012.
- [3] Lasher S, Unnasch S, Chan M, Marion III M. 7 Fuel choice for fuel cell vehicles: hydrogen infrastructure costs. Tech. Rep. U.S. Department of Energy; 2005
- [4] Crabtree GW, Dresselhaus MS, Buchanan MV. The hydrogen economy. *Phys Today* 2004;57(12):39–44. <http://dx.doi.org/10.1063/1.1878333>.
- [5] Olah GA, Goeppert A, Prakash GKS. Beyond oil and gas: the methanol economy. Wiley; 2009.
- [6] Methanex Corporation. Technical information and safe handling guide for methanol. 2006.
- [7] Wee JH. Which type of fuel cell is more competitive for portable application: direct methanol fuel cells or direct borohydride fuel cells? *J Power Sources* 2006;161(1):1–10. <http://dx.doi.org/10.1016/j.jpowsour.2006.07.032>.
- [8] Pan C, He R, Li Q, Jensen JO, Bjerrum NJ, Hjulmand HA, et al. Integration of high temperature PEM fuel cells with a methanol reformer. *J Power Sources* 2005;145(2):392–8. <http://dx.doi.org/10.1016/j.jpowsour.2005.02.056>.
- [9] Icardi U, Specchia S, Fontana G, Saracco G, Specchia V. Compact direct methanol fuel cells for portable application. *J Power Sources* 2008;176(2):460–7. <http://dx.doi.org/10.1016/j.jpowsour.2007.08.048>.
- [10] Iulianelli A, Ribeiro P, Mendes A, Basile A. Methanol steam reforming for hydrogen generation via conventional and membrane reactors: a review. *Renew Sustain Energy Rev* 2014;29:355–68. <http://dx.doi.org/10.1016/j.rser.2013.08.032>.
- [11] Avgouropoulos G, Paxinou A, Neophytides S. In situ hydrogen utilization in an internal reforming methanol fuel cell. *Int J Hydrogen Energy* 2014. <http://dx.doi.org/10.1016/j.ijhydene.2014.03.101>.
- [12] Li Q, He R, Jensen J, Bjerrum N. PBI-based polymer membranes for high temperature fuel cells – preparation, characterization and fuel cell demonstration. *Fuel Cells* 2004;4(3):147–59. <http://dx.doi.org/10.1002/fuce.200400020>.

- [13] Zhang J, Xie Z, Zhang J, Tang Y, Song C, Navessin T, et al. High temperature PEM fuel cells. *J Power Sources* 2006;160(2):872–91. <http://dx.doi.org/10.1016/j.jpowsour.2006.05.034>.
- [14] Tang Y, Zhang H, Zhong H, Xu Z. In-situ investigation on the CO tolerance of carbon supported PdPt electrocatalysts with low Pt content by electrochemical impedance spectroscopy. *Int J Hydrogen Energy* 2012;37(3):2129–36. <http://dx.doi.org/10.1016/j.ijhydene.2011.10.104>.
- [15] Du B, Pollard R, Elter JF, Ramani M. Performance and durability of a polymer electrolyte fuel cell operating with reformate: effects of CO, CO<sub>2</sub>, and other trace impurities. In: Buchi FN, Inaba M, Schmidt TJ, editors. *Polym. electrolyte fuel cell durab*; 2009. p. 341–66.
- [16] Sapountzi F, Tsampas M, Vayenas C. Methanol reformate treatment in a PEM fuel cell-reactor. *Catal Today* 2007;127(1–4):295–303. <http://dx.doi.org/10.1016/j.cattod.2007.03.016>.
- [17] Ji X, Yan L, Zhu S, Zhang L, Lu W. Methanol distribution and electroosmotic drag in hydrated poly (perfluorosulfonic) acid membrane. *J Phys Chem B* 2008;112(49):15616–27. <http://dx.doi.org/10.1021/jp8066469>.
- [18] Cao D, Lu GQ, Wieckowski A, Wasileski SA, Neurock M. Mechanisms of methanol decomposition on platinum: a combined experimental and ab initio approach. *J Phys Chem B* 2005;109(23):11622–33. <http://dx.doi.org/10.1021/jp0501188>.
- [19] Simon Araya S, Andreasen SJ, Kær SK. Experimental characterization of the poisoning effects of methanol-based reformate impurities on a PBI-based high temperature PEM fuel cell. *Energies* 2012;5(12):4251–67. <http://dx.doi.org/10.3390/en5114251>.
- [20] Simon Araya S, Juhl Andreasen SR, Venstrup Nielsen H, Knudsen Kær SR. Investigating the effects of methanol-water vapor mixture on a PBI-based high temperature PEM fuel cell. *Int J Hydrogen Energy* 2012b;37(23):18231–42. <http://dx.doi.org/10.1016/j.ijhydene.2012.09.009>.
- [21] Kim T. Micro methanol reformer combined with a catalytic combustor for a PEM Fuel Cell. *Int J Hydrogen Energy* 2009;34(16):6790–8. <http://dx.doi.org/10.1016/j.ijhydene.2009.06.024>.
- [22] Schmidt TJ. Durability and degradation in high-temperature polymer electrolyte fuel cells. *ECS Trans*, vol. 1; 2006. p. 19–31. <http://dx.doi.org/10.1149/1.2214541>. ECS.
- [23] Lawrence MG. The relationship between relative humidity and the dewpoint temperature in moist air: a simple conversion and applications. *Bull Am Meteorol Soc* 2005;86(2):225–33. <http://dx.doi.org/10.1175/BAMS-86-2-225>.
- [24] Juhl Andreasen S, Rabjerg Vang J, Knudsen Kær S. High temperature PEM fuel cell performance characterisation with CO and CO<sub>2</sub> using electrochemical impedance spectroscopy. *Int J Hydrogen Energy* 2011;36(16):9815–30. <http://dx.doi.org/10.1016/j.ijhydene.2011.04.076>.
- [25] Lebak Jesper. Experimental characterization and modeling of PEM fuel cells. Ph.D. thesis. 2010.
- [26] Xiao L, Zhang H, Scanlon E. High-temperature polybenzimidazole fuel cell membranes via a sol-gel process. *Chem Mater* 2005;16(7):5328–33.
- [27] Nagano S, Miyagawa H, Azegami O, Ohsawa K. Heat transfer enhancement in methanol steam reforming for a fuel cell. *Energy Convers Manag* 2001;42(15–17):1817–29. [http://dx.doi.org/10.1016/S0196-8904\(01\)00043-7](http://dx.doi.org/10.1016/S0196-8904(01)00043-7).
- [28] Agrell J, Birgersson H, Boutonnet M. Steam reforming of methanol over a Cu/ZnO/Al<sub>2</sub>O<sub>3</sub> catalyst: a kinetic analysis and strategies for suppression of CO formation. *Chem Mater* 2002;14(1):249–57.
- [29] Wainright J, Wang J, Weng D, Savinell R, Litt M. Acid-doped polybenzimidazoles: a new polymer electrolyte. *J Electrochem Soc* 1995;142(7):1121–3. <http://dx.doi.org/10.1149/1.2044337>.
- [30] Daletou MK, Kallitsis JK, Voyiatzis G, Neophytides SG. The interaction of water vapors with H<sub>3</sub>PO<sub>4</sub> imbibed electrolyte based on pbi/polysulfone copolymer blends. *J Memb Sci* 2009;326(1):76–83. <http://dx.doi.org/10.1016/j.memsci.2008.09.040>.
- [31] Sriramulu S, Jarvi TD, Stuve EM. Reaction mechanism and dynamics of methanol electrooxidation on platinum (111). *J Electroanal Chem* 1999;467(1–2):132–42. [http://dx.doi.org/10.1016/S0022-0728\(99\)00036-4](http://dx.doi.org/10.1016/S0022-0728(99)00036-4).
- [32] Hu J, Zhang H, Zhai Y, Liu G, Yi B. 500 h continuous aging life test on PBI/H<sub>3</sub>PO<sub>4</sub> high-temperature PEMFC. *Int J Hydrogen Energy* 2006;31(13):1855–62. <http://dx.doi.org/10.1016/j.ijhydene.2006.05.001>.
- [33] Modestov A, Tarasevich M, Filimonov V, Zagudaeva N. Degradation of high temperature MEA with PBI-H<sub>3</sub>PO<sub>4</sub> membrane in a life test. *Electrochim Acta* 2009;54(27):7121–7. <http://dx.doi.org/10.1016/j.electacta.2009.07.031>.
- [34] Galbiati S, Baricci A, Casalegno A, Marchesi R. Degradation in phosphoric acid doped polymer fuel cells: a 6000 h parametric investigation. *Int J Hydrogen Energy* 2013;38(15):6469–80. <http://dx.doi.org/10.1016/j.ijhydene.2013.03.012>.