

Characterization of clay-modified thermoset polymers under various environmental conditions for the use in high-voltage power pylons

Kliem, Mathias; Høgsberg, Jan; Wang, Qian; Dannemann, Martin

Published in:
Advances in Mechanical Engineering

DOI (link to publication from Publisher):
[10.1177/1687814017698890](https://doi.org/10.1177/1687814017698890)

Creative Commons License
CC BY 4.0

Publication date:
2017

Document Version
Publisher's PDF, also known as Version of record

[Link to publication from Aalborg University](#)

Citation for published version (APA):
Kliem, M., Høgsberg, J., Wang, Q., & Dannemann, M. (2017). Characterization of clay-modified thermoset polymers under various environmental conditions for the use in high-voltage power pylons. *Advances in Mechanical Engineering*, 9(5), 1-16. <https://doi.org/10.1177/1687814017698890>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

Take down policy

If you believe that this document breaches copyright please contact us at vbn@aub.aau.dk providing details, and we will remove access to the work immediately and investigate your claim.

Characterization of clay-modified thermoset polymers under various environmental conditions for the use in high-voltage power pylons

Mathias Kliem¹, Jan Høgsberg¹, Qian Wang² and Martin Dannemann³

Abstract

The effect of nanoclay on various material properties like damping and strength of typical thermoset polymers, such as epoxy and vinyl ester, was investigated. Different environmental conditions typical for high-voltage transmission pylons made of composite materials were taken into account. Resin samples were prepared with various clay weight fractions ranging from 0% to 3%. Scanning electron microscopy, transmission electron microscopy, X-ray diffraction and rheological analysis were used to study the morphology and the structure of the nanocomposites. For all nanoclay-modified thermoset polymers, the morphology was found to be of exfoliated structure mainly. Static, uniaxial tensile tests showed that the addition of nanoclay to thermoset polymers led to a beneficial effect on the stiffness, whereas the tensile strength and ductility significantly decreased. When exposed to different environmental conditions, nanoclay was found to have a positive influence on the dynamic properties, analysed by a dynamic mechanical thermal analysis. The addition of nanoclay to the thermoset resin led to an increase of the damping properties by up to 28% for vinyl ester and up to 6% for epoxy at -20°C . The dielectric properties were evaluated by electrical breakdown strength tests resulting in 11% better insulating behaviour for nanoclay-modified vinyl ester.

Keywords

Nanoclay, thermoset polymers, material testing, environmental ageing

Date received: 14 October 2016; accepted: 13 February 2017

Academic Editor: Mohammad Talha

Introduction

Glass fibre-reinforced plastic (GFRP) materials are of non-conductive nature and well suited for use in high-voltage applications, such as insulators and power transmission pylons.¹ Thus, overhead transmission lines can be attached directly to the cross arms of each composite pylon because of the inherent non-conductivity of the raw material. Due to a rigid connection of the transmission lines to the pylon, any wind-induced vibration and motion will be directly transferred to the slender composite mast structure. As a consequence, the severe cable vibration phenomenon known as ‘galloping’ can lead to catastrophic failure of

the entire structure due to excessive vibration amplitudes at resonance.^{2,3} Therefore, galloping is

¹Department of Mechanical Engineering, Technical University of Denmark, Kongens Lyngby, Denmark

²Department of Energy Technology, Aalborg University, Aalborg, Denmark

³Institute of Lightweight Engineering and Polymer Technology, Technische Universität Dresden, Dresden, Germany

Corresponding author:

Mathias Kliem, Department of Mechanical Engineering, Technical University of Denmark, Anker Engelds Vej 1, 2800 Kongens Lyngby, Denmark.

Email: mkliem@mek.dtu.dk



Creative Commons CC-BY: This article is distributed under the terms of the Creative Commons Attribution 3.0 License

(<http://www.creativecommons.org/licenses/by/3.0/>) which permits any use, reproduction and distribution of the work without

further permission provided the original work is attributed as specified on the SAGE and Open Access pages (<https://us.sagepub.com/en-us/nam/open-access-at-sage>).

considered as a major design parameter for the overall transmission line system.⁴ Galloping occurs at temperatures around or below 0°C, as non-symmetrical ice aggregations along the transmission lines are usually initiating this low frequent vibration phenomenon associated with large vibration amplitudes (0.1–1 Hz).^{5,6} The increase of structural damping is an effective way to raise the critical wind speed for the onset of galloping.⁷ Nanoparticles, such as nanoclay (NC) and nanotubes (NT) within composite materials, have been found to enhance the static and dynamic material properties, specifically with regard to damping.^{8–13} Kibir and colleagues^{14,15} have been investigating the damping behaviour of GFRP beams with different laminate configurations by a free decay test and a dynamic mechanical thermal analysis (DMTA) at room temperature and have observed an increase in damping for a quasi-isotropic laminate by up to 36% in combination with a stiffness enhancement of 10% when reinforced by 2 wt% NC.

Another central issue of this article is a sensibility analysis of an NC modification of thermoset polymers to various environmental conditions and the resulting change in material properties, although this has been partially addressed in Singh et al.¹⁶ and Tcherbi-Narteh et al.¹⁷ Composite structures designed for an external application are being exposed to different environmental conditions like ultraviolet (UV) radiation, moisture and pollution, inducing material degradation. Although coatings are widely used for protection against environmental degradation,^{18,19} the structural material to be used is required to be resistant against the weathering conditions mentioned above, especially as power transmission pylons are designed for life times of ≥ 50 years. NC has been found to enhance the barrier properties within the polymer, such as the resistance to moisture transport, and has been leading to a reduction of material degradation by UV exposure. These material properties play an important role for the design of high-voltage power pylons exposed to harsh environmental conditions, such as moisture, UV irritation and strong electromagnetic fields. Furthermore, an easy and inexpensive availability, processability and non-toxicity of NC is of high importance among other things, as it has been reported in Dasan²⁰ and Bensadoun et al.,²¹ resulting in commercial attention towards these materials. Nowadays, NC is increasingly used in various industries, for example, in automotive, packaging, coating and paints, electronics and aerospace,^{22–24} to enhance cost-effective, specific material properties, such as stiffness,²⁵ strength,²⁶ limited flammability and thermal stability,²⁷ fracture toughness²⁸ and viscosity.²⁹ Furthermore, NC is also of electrical non-conductive nature.³⁰ The overall dielectric material property of NC-modified Epoxy (EP) has been observed to be 20% higher compared to neat EP.³¹ The use of NTs, for

example, carbon NTs, is not conducive, as the material properties like non-conductivity and inexpensive availability are required for the design of the power transmission pylons. In summary, NC is a suitable and promising additive for the enhancement of static and dynamic material properties to be used in connection with high-voltage power pylons.

It has been reported in Velmurugan and Mohan¹¹ that NC modified with an organic modifier results in improved performance in terms of dispersion, thermal stability, stiffness and hardness compared to non-modified NC. This modification, for example, by an organic quaternary ammonium salt, has led to an enhanced interaction between the clay surface and the matrix.³² Therefore, the organomodified NC Garamite 1958 has been chosen in the following investigations due to its potential to enhance the relevant material properties of the neat polymer.^{33,34}

Already small amounts of NC (of a few wt%) can lead to considerable improvements due to the high aspect ratio of layered silicate, resulting in a huge network of interfacial surface area.^{13,14} Clay nanocomposites can be grouped into three different morphologies (see Figure 1) depending on the remaining agglomerate sizes of NC particles and the related interplanar distances (d-spacing) between clay platelets representing the crystal lattice planes (see Figure 3). The exfoliated clay-polymer morphology is the most desirable for improved material properties,^{12,34,35} whereas in practice the final dispersion consists probably of all three morphologies with different percentage proportions.¹²

A number of investigations have dealt with various dispersion techniques to maximize the dispersion quality in terms of amount of exfoliated clay particles within the polymer.^{36,37} It has been found that the mixing speed is one of the driving parameters for achieving an

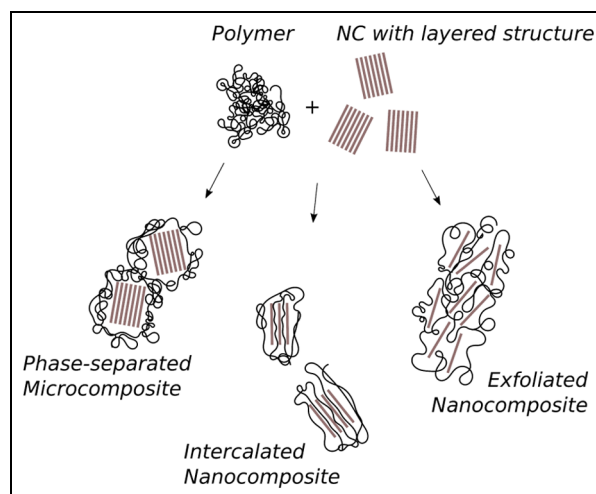


Figure 1. Scheme of different clay-polymer morphologies.

exfoliated clay–polymer morphology realizable with the high-speed homogenization technique used for this investigation.³⁸ The just mentioned dispersion quality, the type of polymer and clay as well as its pretreatment may all have a significant influence on the final material properties of the NC-modified polymer.³⁹ Therefore, the aim of this study is to present an evaluation on the effect of NC on the static and dynamic material properties by keeping those parameters constant. Thus, the investigation focuses on the NC modification of the polymer resin material only, instead of considering the whole fibre–polymer composite. Therefore, the conclusion of this study is only valid for matrix-dominated material properties, such as the transverse stiffness and transverse damping capability of a unidirectional (UD) laminate.^{14,33} The effect of NC on the static material properties of vinyl ester (VE) and epoxy (EP) is investigated specifically for different environmental conditions, such as moisture, UV irradiation and the presence of a high electrical field, representative of a composite power transmission pylon in its realistic environment. However, the major subject of this investigation is the damping analysis of different NC-modified polymer configurations at low temperatures (between -20°C and 0°C), low frequencies ($\leq 1\text{ Hz}$) and under the influence of various environmental conditions, representing an aged composite power transmission pylon being affected by galloping-induced vibrations of the attached overhead transmission lines. These material properties have not been investigated so far in relation to the specific environmental conditions mentioned above in combination with the materials used for the analysis.

Experimental methods

This section provides a detailed description about the materials, methods and procedures used to analyse the effect of NC on the static and dynamic material properties of EP and VE. Besides a comprehensive analysis of the dispersion quality in terms of clay–polymer morphology, different mechanical and electrical testing procedures are explained. The experimental setup used for environmental ageing is described at the end of the section.

Materials

The thermoset matrices investigated were a bisphenol-epoxy vinyl ester resin DION IMPACT 9102-683 (VE) and an epoxy infusion system PRIME 20LV (EP). These resin materials are both well suited for use in electrical insulation devices due to their high dielectric properties.^{1,40,41} An alkyl ammonium–based NC, commercially available as Garamite 1958 by Byk Additives and Instruments, was used in four weight concentrations (0, 1, 2 and 3 wt%) within the polymer to

gradually demonstrate a change in the mechanical properties. This organically modified mixed clay system is a mixture of platelets and ribbon-like clay particles and has been chosen due to its specified usability within EP and VE.⁴²

Sample preparation

The NC was added in four different weight concentrations to the thermoset resins relative to the final polymer weight: 0, 1, 2 and 3 wt%. In accordance with Keyoonwong et al.³⁷ and Ngo et al.,³⁸ a high-speed homogeniser Ultra-Turrax T25 was chosen to increase the probability of an entirely exfoliated clay–polymer morphology. A maximum of 500 mL resin was mixed during each run with 20,000 rpm for 40 min. The mixing temperature never exceeded 80°C . The final mixing viscosity was dependent on the type of thermoset resin, due to different resin–hardener mixing ratios (VE – 2:100/EP – 26:100). Whereas 98 wt% of the VE resin relative to the final matrix material weight was used for mixing, only 80 wt% of the EP resin was mixed with NC. All dispersions were evacuated for about 90 min under vacuum at 35°C to remove air trapped during mixing. Only for the mixture EP-2 (epoxy with 2 wt% NC), it appeared to be difficult to achieve an air-bubble free dispersion. Additional degassing of the dispersion under vacuum at temperatures of around 50°C for more than 12 h was to little avail. Furthermore, it was observed that VE resin exhibited a loss of mass of about 3% after evacuation, which might be explained by the outgassing of styrene. The resin temperature was raised to 35°C before mixing with the hardener to reduce viscosity. As illustrated in Figure 2, the nanocomposite dispersion was then poured into a vertically orientated mould consisting of two parallel plates to minimize the surface shrinkage pattern. In total, eight

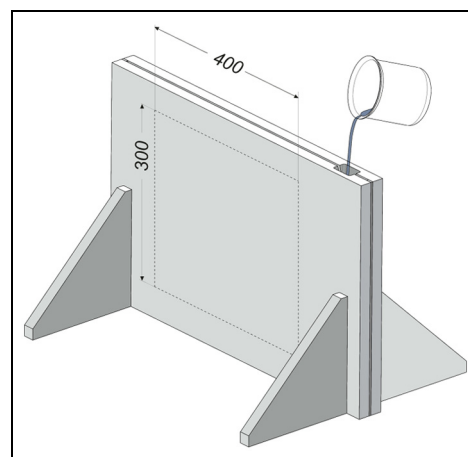


Figure 2. Filling process of the NC-modified resin into the vertically orientated mould.

nanocomposite panels with $300\text{ mm} \times 400\text{ mm} \times 2\text{ mm}$ were manufactured to test EP and VE with four NC concentrations. After curing and post-curing, the panels rested for at least 24 h at 40°C and 10 h at 70°C and were then cut by computerized numerical controlled (CNC) milling to samples used for tensile tests and DMTA in test-specific dimensions (see sections ‘Mechanical properties’ and ‘Breakdown strength analysis’).

Morphology analysis of nanocomposites

There are several complementary methods typically used for the evaluation of the NC distribution within a polymer, such as scanning electron microscopy (SEM), transmission electron microscopy (TEM), X-ray diffraction (XRD) and rheology analysis.⁴³ All methods were used in this present investigation.

The SEM analysis was conducted under high vacuum using a Quanta 200 F electron microscope by FEI, while a FEI Tecnai G2 transmission electron microscope was used to generate the TEM images. The required surface treatment of all SEM samples as well as the cutting of 100 nm slices for the TEM analysis was carried out using a Leica Ultracut UCT microtome. To monitor the time-dependent NC distribution within the polymer over a mixing period of 40 min, dispersion samples extracted after every 10 min were cured and then optically analysed.

The XRD method can be used to determine the clay–polymer morphology (see Figure 1) of neat NC and NC-modified polymer materials.⁴⁴ Based on the diffraction angle 2θ of the incident and the diffracted X-rays, the interplanar distance d (d-spacing) of two atomic-scale crystal lattice planes can be calculated according to Bragg’s law (see Figure 3)

$$n\lambda = 2d \sin \theta \quad (1)$$

The X-ray diffraction investigations on both neat NC and NC composites were performed using a Philips PW 1830 X-ray Generator with Cu $K\alpha$ radiation ($\lambda_{Cu} = 1.5405\text{ \AA}$). The specimens were scanned at 45 kV and 40 mA with the diffraction angle of 2θ ranging

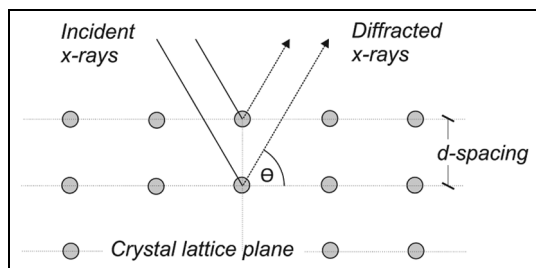


Figure 3. Bragg’s diffraction by a crystal lattice plane with the incident and diffracted wave vectors.

from 2° to 30° with equidistant increments of 0.1° and a retention time of 3 s.

A supplementary rheological analysis was carried out using a Rheometer AR 2000 by TA, as this technique is widely used for the evaluation of the dispersion state. While SEM, TEM and XRD methods usually require solid samples, non-cured NC–resin dispersions were used for this rheological investigation. The rheological investigation of all NC–resin dispersions was carried out at 25°C . A parallel plate setup with a gap distance of around 1 mm was used to perform shear rate sweeps for different NC contents in the range from 1 to 100 s^{-1} .

Mechanical properties

The influence of the NC modification on the mechanical properties of the polymer was evaluated based on static tensile tests at room temperature as well as a DMTA at environmental conditions similar to those experienced during transmission line galloping. The static and dynamic results obtained by the tests described below are specifically used to assess the use of NC-modified matrix for high-voltage power pylons.

Tensile test. Uniaxial tensile tests were used to evaluate the effects of NC and various ageing conditions on the static mechanical properties of different thermoset polymers. The tensile test was conducted at room temperature according to the ISO 527-2 Standard.⁴⁵ All dog-bone samples with the standardized dimensions of type 1 BA⁴⁵ were quasi-statically tested on an MTS Acumen Electrodynamic Test System with a 3 kN load cell at a crosshead speed of 1 mm/min. The displacement was measured by an MTS extensometer with 25 mm gauge length. At least six specimens were used for each configuration.

DMTA. The Dynamic Mechanical Thermal Analyser (DMTA) used for the damping characterization of the nanocomposite samples was a Q800 from TA as shown in Figure 4. The specimens with the dimensions of $60\text{ mm} \times 5\text{ mm} \times 2\text{ mm}$ were tested in galloping close environmental conditions according to Liu et al.,⁴⁶ at a frequency of 0.5 Hz for the two temperatures of -20°C and 0°C . A three-point bending fixture was used for the analysis.

Breakdown strength analysis

The electrical strength is an important property of an insulating material, as it indicates the maximum electrical field the material can withstand before it fails to work due to the breakdown channel through the material. Thus, electric strength is used to investigate the

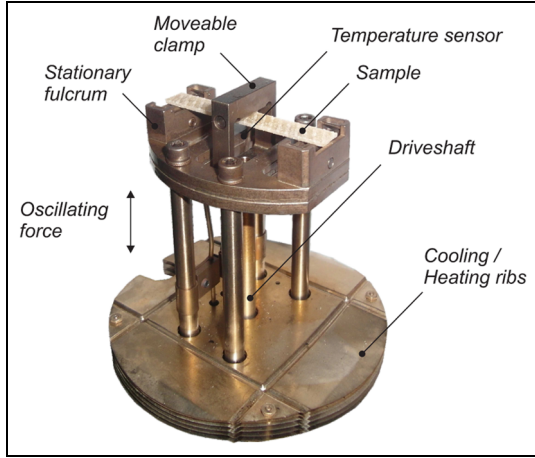


Figure 4. Sample placed in the three-point bending fixture of the DMTA Q800.

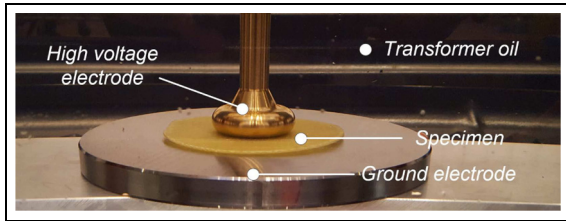


Figure 5. Electric strength test configuration.

effects of different weight percentages of NC particles on the dielectric properties of VE and EP materials. Electric strength tests are performed according to the IEC 60243 Standard⁴⁷ to investigate the influence of the NC modification on the dielectric properties of the polymer. Round-plate specimens with the dimensions of 100 mm × 2 mm were tested at ambient atmosphere conditions at 21°C and 50% relative humidity.⁴⁸ A cylinder-plate electrode configuration was adopted. Tests were conducted at a grid frequency of 50 Hz in transformer oil. Figure 5 shows the electric strength test configuration.

Environmental ageing test

Artificial weathering tests, such as water immersion and UV exposure, were conducted to investigate the changes in mechanical properties. To shorten the environmental ageing process, high-intensity test conditions were chosen: (a) the samples were placed in a water bath instead of applying realistic condensation conditions and (b) the intensity of UV radiation was about 17 times higher than stated in the ASTM D4329-13 Standard.⁴⁹

Water immersion. The oven-dried nanocomposite samples were immersed in distilled water at room

temperature and periodically weight in accordance with the ASTM D570-98 Standard,⁵⁰ in order to evaluate the water uptake W_t by

$$W_t(\%) = \frac{(S_t - S_{t_0})}{S_{t_0}} \cdot 100 \quad (2)$$

where S_t and S_{t_0} are the sample weight at time t_0 and t .

UV exposure. The photoageing process was carried out in a UV exposure chamber as described in Christiansen et al.⁵¹ using UV-lamps from both sides with a relatively broad spectrum centered around 365 nm at 14 mW/cm³. After measuring the weight, the specimens were randomly redistributed within the chamber. The temperature during UV exposure never exceeded 40°C.

Results and discussion

In this section, the results of the morphological study in terms of dispersion quality are presented first. The sample weight as a result of the sensibility to artificial weathering is then evaluated based on the morphological analysis. Furthermore, the static and dynamic material properties are discussed together with the results of the environmental ageing procedure, leading to an assessment of the applicability of NC-modified thermoset polymers with respect to the use in high-voltage transmission pylons. Finally, the effect of NC on the breakthrough strength, as an indicator for enhanced dielectric properties, is discussed.

Morphology and dispersion quality

The clay-polymer morphology was evaluated by SEM images in Figure 6 for different NC-modified VE configurations. The average agglomerate size was found to depend on the different mixing durations and NC contents (1–3 wt%).

The mixing duration denoted as 0 min corresponds to a brief manual mixing to ensure that all NC particles are bound by resin, and that no loose NC is left on the resin surface. In Figure 6, the bright areas on the back-scattered micrographs represent agglomerated NC particles. The clay portions are continuously being broken up during increased mixing, although a few and small NC agglomerated particles are still present after 40 min of mixing, as shown in Figure 6 for the 3 wt% mixture. The maximal remaining aggregate size is about 5 μm for all three NC concentrations, whereas the density of those max-sized aggregates clearly increases with increasing NC concentration. However, the NC is well dispersed within the polymer after 40 min mixing for all three NC configurations (VE-1, VE-2 and VE-3), although the remaining few clay agglomerates are large and therefore may have a negative influence on the

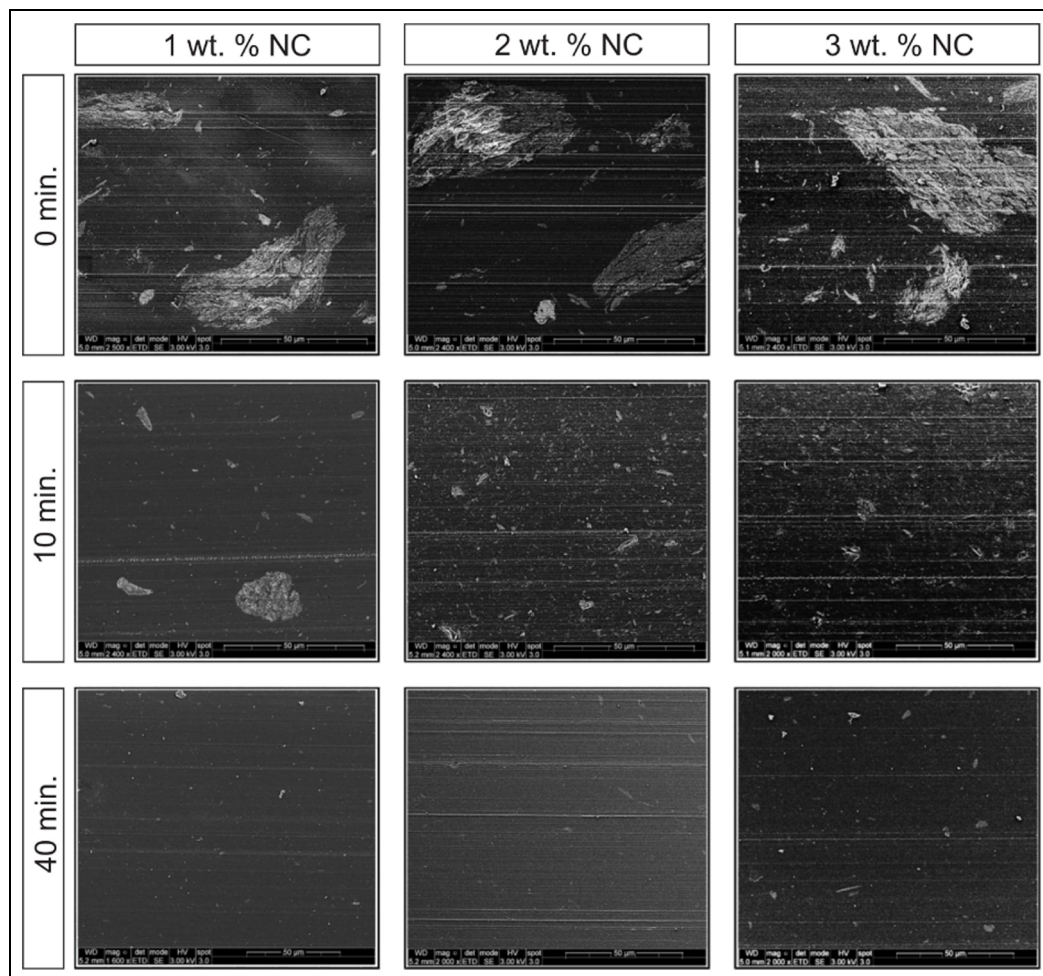


Figure 6. SEM images of VE with respect to different NC contents and mixing durations.

mechanical behaviour of the nanocomposite, due to appearing stress concentrations in these areas.^{52,53}

The layered, ribbon-like structure typical for Garamite³⁷ is shown in Figure 7(a) and (b) obtained by TEM image for VE-2 with 0 and 40 min mixing duration, respectively. Figure 7(a) shows a multi-stack agglomerate consisting of a large number of evenly aligned, tightly packed platelets with small interplanar d-spacing. This phase-separated microcomposite (see Figure 1) with a low d-spacing is typical for an unmixed state and agrees well with the SEM images for 0 min of mixing in Figure 6. In contrast, a well dispersed NC agglomerate with increased d-spacing is seen in Figure 7(b). The remaining average particle size of about four platelets with an increased d-spacing is in good agreement with the observations in Ngo et al.³⁸ based on an applied high shear mixing method. To support the microscopical results for VE, the broadly used XRD method was performed to evaluate the clay dispersal within the polymer. The results for the neat NC ‘Garamite 1958’ are in good agreement with Ingram

et al.³² and Huynh et al.⁵⁴ and present a mix of minerals dominated by sepiolite (see Figure 8). According to Bragg’s law (see equation (1)), the d-spacing of the clay platelets results in $d = 1.194$ nm from the distinct basal peak in Figure 8 at the diffraction angle 2θ of $\sim 7.4^\circ$.

Cured VE- and NC-VE samples were also analysed to determine the clay–polymer morphology, indicating the level of exfoliation. In Figure 8, the broad curve of neat VE with its maximum at around 2θ of $\sim 20.0^\circ$ represents the amorphous structure and it is in good agreement with Pal.⁵⁵ The XRD patterns of neat VE with its clay-modified derivatives (VE-1, VE-2 and VE-3) are of similar shape containing no sharp peaks and indicating a complete exfoliation state for all NC-VE dispersions (VE-x). Only for VE-2 and VE-3, an insignificant peak at 2θ of $\sim 7.1^\circ$ can be observed. It may indicate an almost insignificant portion of intercalated NC particles within the exfoliated nanocomposite (see Figure 1). The resulting d-spacing of $d = 1.244$ nm is 4% larger compared to neat Garamite 1958, indicating a

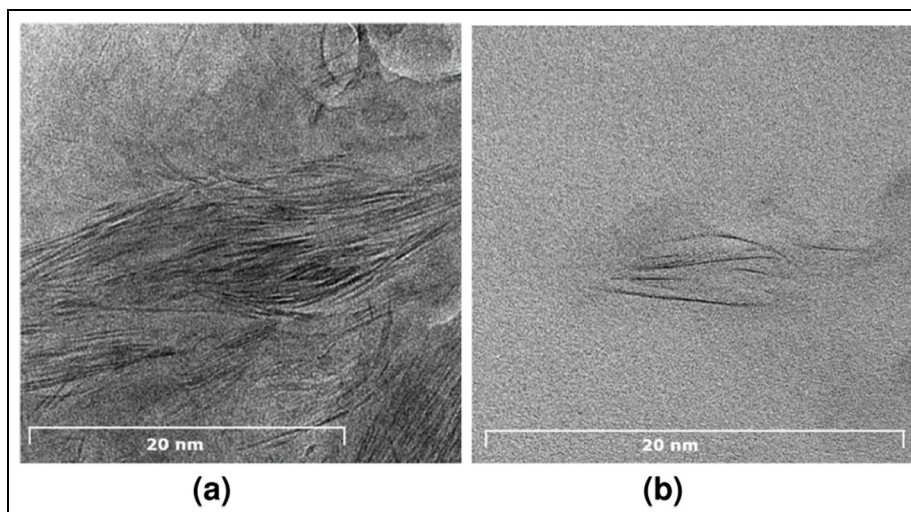


Figure 7. TEM images of VE-2 with different mixing durations: (a) 0 min mixing and (b) 40 min mixing.

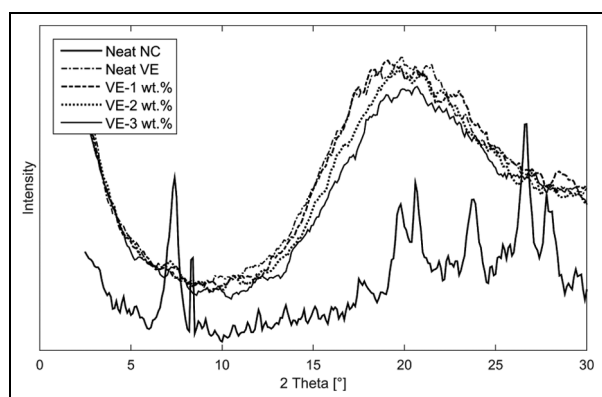


Figure 8. XRD curves of neat Garamite, neat VE and VE-Garamite dispersions.

negligible increase of polymer molecules between the clay platelets and therefore a higher clay-matrix interaction.

Rheological measurements were carried out for neat and NC-modified EP to evaluate its morphological structure of the nanocomposite. The results for EP are shown in Figure 9. As expected, the initial viscosity increases with increasing NC content due to an enhanced interaction of clay particles within the polymer matrix.¹² At the same time, a viscosity decrease with increasing shear rate is observed, indicating the non-Newtonian behaviour called ‘shear thinning’.⁵⁶ These phenomena are in agreement with Ingram et al.³² and Huynh et al.⁵⁴ and are found to be directly related to a high grade of exfoliation within the clay-polymer network due to a strong interaction between clay particles and the EP matrix. Consequently, a high level of exfoliated NC particles within the EP is being assumed.

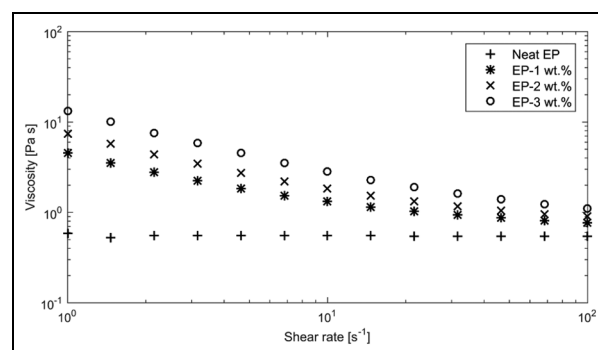


Figure 9. Shear viscosities for neat and NC-modified EP.

Sample weight as function of ageing duration

The effect of NC on the sample weight related to the ageing duration of polymer matrices, such as moisture and UV irritation, was investigated using water immersion and UV exposure tests. Three different ageing scenarios were developed: (a) UV exposure for 250 h, (b) water immersion for 400 h and (c) combined ageing with 250 h UV exposure and 400 h water immersion. All specimens were regularly weighed to track the sample weight as function of the duration of ageing. The presented curves in Figure 10 comprise an average of six different samples per configuration.

Organoclay, such as Garamite 1958, are capable of water absorption in humid environments⁵⁷ and may influence the water uptake characteristics of the nanocomposite when embedded within the polymer. In Figure 10(b), the normalized, time-dependent increase in weight is seen for all material combinations immersed in distilled water for up to 400 h. After a rapid water uptake within the first 100 h, the increase

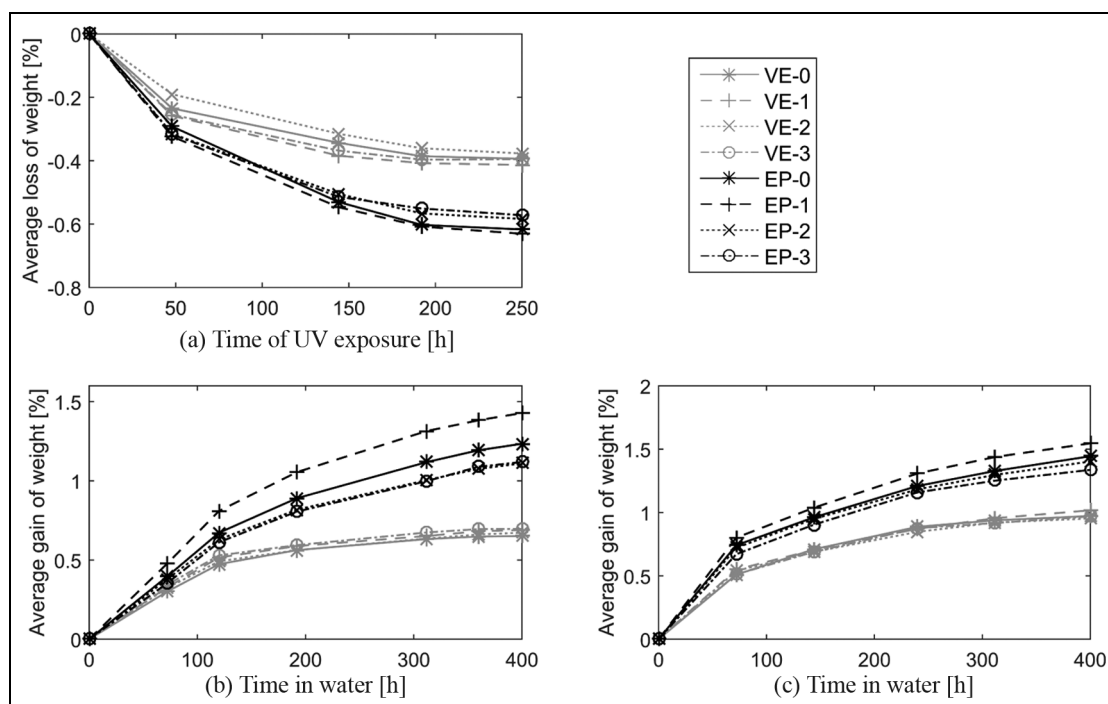


Figure 10. Average weight changes of non-modified and NC-modified VE and EP due to (a) UV exposure for 250 h, (b) water immersion for 400 h and (c) combined ageing condition with UV exposure for 250 h followed by 400 h water immersion.

in weight almost stabilizes for VE at around 0.7% due to saturation. An equilibrium is not reached for EP after 400 h, as the weight steadily increases towards the end of water immersion at 1.2%. No remarkable variation in weight gain for VE and its NC-modified derivatives ($\pm 0.02\%$) is observed, whereas a significant clay dependency is detected for EP ($\pm 0.2\%$). By modifying EP with 1 wt% NC, the water uptake is increased by 14% compared to neat EP. A decrease in weight by 9% can be observed for EP-2 and EP-3 compared to the reference EP-0. The results for EP-1 are partly contradictory to the results in Kusmono et al.²² and Khanbabaie et al.,⁵⁸ as the water uptake should have been reduced with increasing amounts of exfoliated clay structures acting as efficient barriers against the water transport through the polymer. It is assumed that either a few of the larger clay particles remained non-dispersed within the polymer or a higher dispersion porosity of EP-1 due to mixing and manufacturing lead to the increased water uptake.

A similar type of water uptake is observed for samples that had previously been subjected to UV exposure for 250 h (Figure 10(c)). The water uptake for EP-1 is again 7% higher and for EP-2 and EP-3 in average 5% lower compared to EP-0. However, the water uptake capability is significantly increased for both – for VE by 30% and for EP by about 14% compared to the configurations subjected to water immersion only. This phenomenon is caused by micro-cracks as a result of

UV exposure, providing pathways for a rapid water ingress.^{16,59}

The average weight loss of all analysed VE and EP configurations (VE-x and EP-x) by UV exposure only is shown in Figure 10(a). The mass reduction as a result of UV exposure is caused by the expulsion of volatiles and residual moisture as well as by a physico-chemical degradation.^{16,59} After a rapid drop of specimen weight within the first 50 h, the change in weight stabilized after 250 h of photoageing. This trend is apparent for both EP and VE, whereas EP in general is more prone to weight loss with 0.6% than VE with 0.4%. The weight changing characteristics of each polymer configuration due to UV light is inversely proportional to the water uptake behaviour, as shown in Figure 10(a) and (b). EP modified with 1 wt% experiences the highest water uptake, and consequently the highest gain in weight, but also the highest weight loss by UV exposure. The same relation occurs for EP-2 and EP-3. This correlation is not observed for VE, as the water uptake characteristics are found to be similar for all analysed VE configurations. In fact, the NC seems to have a neglectable influence on VE exposed to different environmental ageing conditions. The influence of NC on the mechanical behaviour of VE under environmental conditions will be analysed in the following sections.

It should finally be mentioned that all specimens suffer from discoloration. This phenomena is a result of oxidation reactions due to, for example, photoageing or

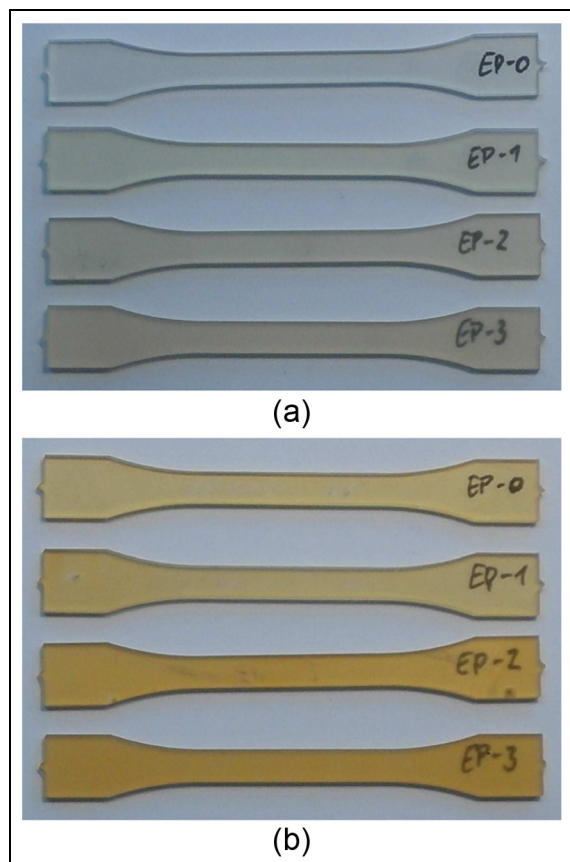


Figure 11. Non-modified and NC-modified EP tensile specimens before and after 250 h of UV exposure: (a) no UV exposure and (b) 250 h of UV exposure.

hydrothermal ageing^{59,60,61} and is a nonreversible process based on chemical interactions within the network. The colour changes of the semi-transparent ageing specimens are illustrated by the photos in Figure 11.

Effect on the static mechanical properties

The effect of different ageing conditions, such as moisture and UV light, on the static mechanical properties like stiffness, strength and elongation at break of VE-x and EP-x was evaluated by uniaxial tensile tests according to the ISO 527-2 Standard.⁴⁵ It is well established that the environmental ageing conditions, considered in the previous section, may lead to decreased mechanical properties of thermoset polymers, whereas moisture may result in less adverse effects on a polymeric matrix compared to the degradation by UV radiation.⁵⁹ Both chain scission and chain cross-linking can take place because of UV irradiation. This may result in reduced strength and enhanced brittleness due to a lower molecular weight and the presence of micro-cracks. On the other hand, an ingress of water has been observed to change the thermo-physical, mechanical and chemical characteristics of the polymer, leading to swelling,

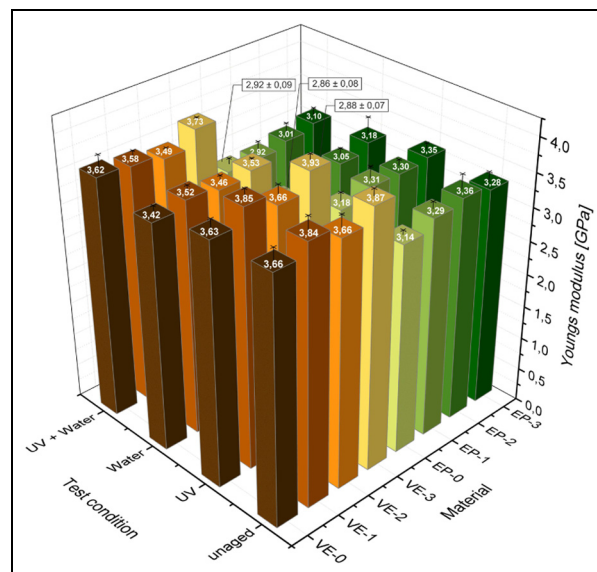


Figure 12. Tensile modulus for NC-modified EP and VE before and after ageing.

plasticization and hydrolysis and thereby resulting in an apparent decrease in the tensile (Young's) modulus.^{62,63} A combined ageing of UV exposure and water immersion will couple these effects and may lead to either lower mechanical properties or unchanged stiffness properties due to synergistic effects.⁵⁹


The stiffness of VE-x and EP-x is shown in Figure 12 with respect to different ageing conditions. Supported by a fairly uniform stiffness distribution, the stiffness of VE-x is found to be in average 15% higher compared to the EP-x configurations. A matrix modification by Garamite 1958 leads to a slight increase in stiffness of max. 5% for both VE and EP, although the highest amount of NC not necessarily results in the maximal stiffness.¹¹ This stiffening effect is found to be consistent for all environmental conditions and is caused by exfoliated or intercalated clay particles restricting the mobility of polymer chains during loading. The highest stiffness is observed for VE-3 and EP-2.

As mentioned above, water immersion of 400 h has a weakening effect on the stiffness of EP-x and VE-x, as shown in Figure 12. The reduction in stiffness is observed to be between 5.5% and 8.7% for VE and 3%–12% for EP.

Surprisingly, a stiffness reduction is not being observed for VE-x and EP-x after combined ageing, although a higher water uptake has been determined after prior UV radiation (see Figure 10(c)). Instead, a constant or slight decrease in stiffness compared to the unaged samples is observed, independent of the NC modification. This indicates the presence of synergistic effects, which seem to positively influence the material properties of specimens exposed to both UV light and moisture. The effect is found to be more pronounced

Table 1. Comparison of the material properties for neat EP and VE based on experiments and datasheet specifications.

Material		Tensile modulus (GPa)	Tensile strength (MPa)	Tensile elongation (%)
VE	Spec.	3.4	79	4.5
	Exp.	3.7 ± 0.2	84.5 ± 3.2	5.07 ± 1.3
EP	Spec.	3.5	73	3.5
	Exp.	3.0 ± 0.1	66.0 ± 0.3	6.4 ± 0.5

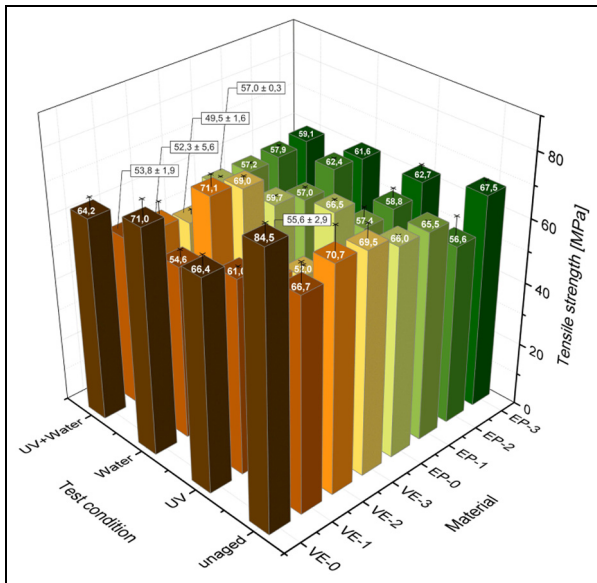**Figure 13.** Tensile strength for NC-modified EP and VE before and after ageing.

for VE-x than for EP-x, while UV exposure seems to have no effect on the stiffness, which is in agreement with Thiagarajan et al.⁶⁴

It can be concluded that the stiffness of VE-x and EP-x can be slightly improved by a matrix modification with NC. However, this stiffening effect is found to be independent of any environmental ageing conditions.

The tensile strength results for VE and EP are shown in Figure 13 with respect to varying NC contents and environmental conditions. For any material configuration investigated, the matrix modification by NC leads to a lower strength compared to the neat resin. Only EP-3 demonstrates a negligible increase in strength compared to its non-modified reference (EP-0). These results are in conflict with Chandradass et al.,²⁶ Ho et al.⁶⁵ and Rashmi et al.,⁶⁶ reporting an increase in or constant strength by a matrix modification with Garamite 1958. A decrease in strength for NC-modified EP up to a certain threshold concentration of 2 wt% has also been reported in Velmurugan and Mohan.¹¹ In contrast, a reduction in tensile strength of NC-modified polymers has been claimed in previous studies.^{26,39,67,68} The presence of microvoids—proportional to the clay content due to an increased dispersion viscosity—and

agglomerated NC particles have been reported to be the main reasons for a reduction in strength. The manufacturing process itself might be another causal factor for the differences, as the specified material properties for neat VE and EP are not properly matching either as indicated by the materials properties in Table 1. As mentioned previously, it is also conceivable that a small amount of NC remained agglomerated after mixing, leading to a reduced final strength of the nanocomposite. However, the dispersion control technologies, such as SEM, TEM, viscosity analysis and XRD used in the analysis, were not detecting any conspicuity in the respective dispersion morphology.

The effect of environmental ageing on the tensile strength varies significantly between VE-x and EP-x. Furthermore, UV exposure leads to considerable strength degradation for VE-x, whereas just a slight reduction in strength is observed for EP-x. On the other hand, water immersion results in slight decreased strength properties for EP-x and VE-x, while the tensile strength of VE-2 and VE-3 is very close to the strength of corresponding unaged samples. The diminishing effect of environmental ageing on the tensile strength of EP-x is plausible and in agreement with the matrix-dominated, transverse tensile properties of UD carbon fibre-reinforced EP samples after ageing.⁵⁹ The tensile strength is however found to be less affected by UV light compared to water immersion. Only EP-2 represents an uncommon case, as the reference tensile strength is lower compared to all related specimens exposed to environmental ageing.

It can be concluded that the addition of NC leads to a reduction in tensile strength for almost all analysed polymer configurations. The effect is more pronounced for VE-x than for EP-x. Furthermore, an NC modification seems to have no significant influence on the tensile strength of specimens when exposed to different environmental ageing conditions.

The effect of NC on the ductility of VE-x and EP-x is represented in Figure 14 with respect to the three different environmental ageing conditions. Similar to the strength analysis, the addition of NC to the thermoset polymers leads to a significant reduction in ductility. This NC related loss of ductility by up to 65% can be observed for both VE and EP and is in agreement with Rashmi et al.,⁶⁶ reporting an increase in brittleness with

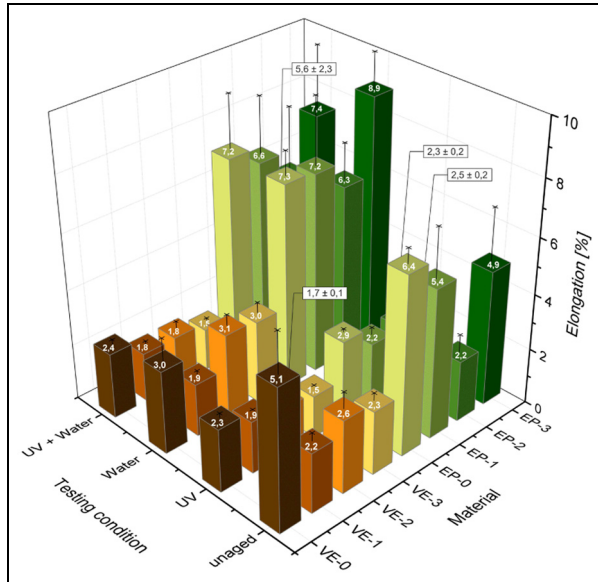


Figure 14. Elongation at break for NC-modified EP and VE before and after ageing.

NC content. Again, two mechanisms are believed to be responsible for this partial dramatic drop in ductility: a limitation in mobility of polymer chains under loading and the presence of voids.

When analysing the material-dependent ductility with respect to different ageing scenarios, an opposite tendency of the material-dependent water sensibility is observed for VE and EP. Water immersion only leads to either reduced or slightly increased ductility for VE, depending on the amount of NC. In contrast, a strong increase of ductility independent on the NC content is observed for EP compared to the related non-aged configurations. This individual behaviour has been reported in Zhao and Li⁶⁹ for VE and⁷⁰ for EP and can be explained by changes on the molecular level of each resin type. The embrittlement of VE and EP by about 55% due to UV exposure is due to the formation of micro-cracks as mentioned before.

Effect on the dynamic mechanical properties

The effect of NC modification and environmental conditioning on the damping behaviour of VE and EP was investigated using the DMTA with a three-point bending fixture (see Figure 4). The specimen to be analysed was sinusoidally loaded and the response signal was analysed in terms of phase shift between load and response signal. The related phase angle δ is representing the dissipated energy for one load cycle and is used to calculate the damping in the form of the loss factor $\tan \delta$.⁷¹ In Figures 15 and 16, the damping of VE and EP is shown as function of NC content, ageing conditions and temperature. The testing frequency is chosen

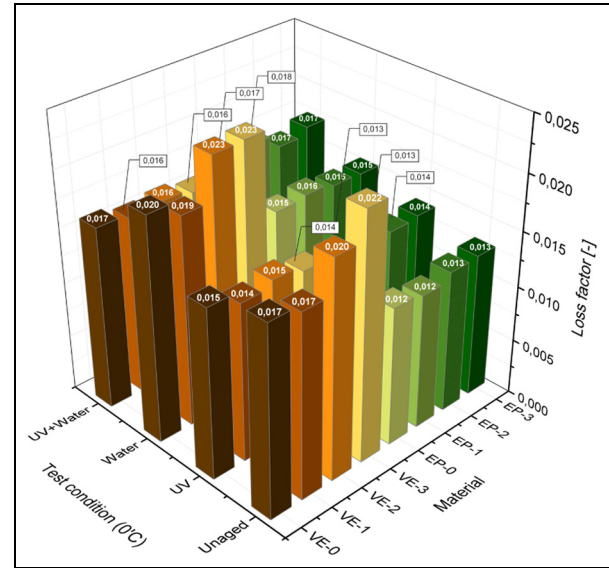


Figure 15. Damping at 0°C for NC-modified EP and VE before and after ageing.

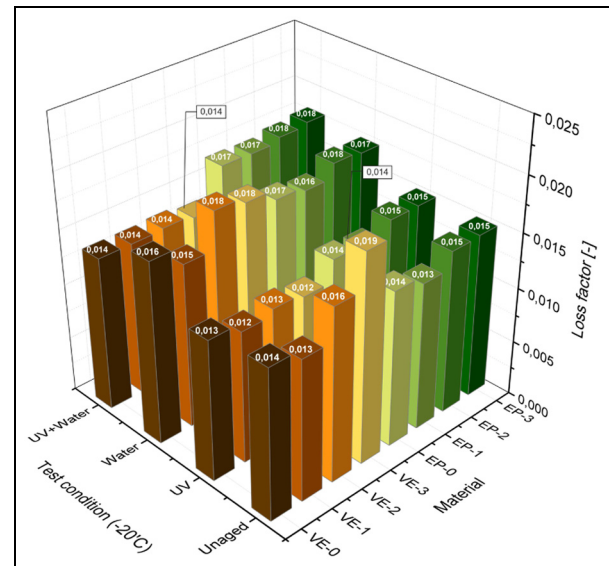


Figure 16. Damping at -20°C for NC-modified EP and VE before and after ageing.

as a typical galloping frequency of 0.5 Hz. It is observed that the damping characteristics change considerably by varying the NC content and the weathering condition.

The damping capability in general is being reduced for VE by decreasing the temperature of 20°C from 0°C to -20°C, whereas the damping increases for all EP configurations for the same drop in temperature. This effect has been described in Zhang et al.⁷¹ for neat EP and can be explained by the polymer crystallization and its high ordered microstructure at lower

temperatures. This leads to higher damping for VE at 0°C and for EP at −20°C. By modifying VE and EP with up to 3 wt% NC, an increase in the damping characteristics can be achieved at both temperatures. However, the damping enhancement for unaged VE-3 is with 23% at 0°C and with 28% at −20°C much larger compared to unconditioned EP-3 with 4% at 0°C and 6% at −20°C. The reason for this difference in damping increase is assumed to be related to changes in the interaction between clay particles and polymer molecules.

The sensibility of the damping property to different environmental conditions differs to some extent significantly between VE, EP and their NC-modified derivatives. The conditioning of all VE-x samples by UV light results in a decrease to more or less the same loss factor $\tan \delta$ of about 0.0147 at 0°C and 0.0123 at −20°C. Thus, an NC modification of VE specimens remains without influence on the damping behaviour, when exposed to UV light. This implies the dominating damping effect of UV light-induced micro-cracks, instead of NC-introduced material damping. The same effect is observed by the damping results after combined environmental ageing for all VE-x. The damping of all VE-x is reduced to similar values for the loss factor $\tan \delta$ of about 0.0162 at 0°C and 0.0140 at −20°C – independent of any NC modification. When considering water immersion only, a slight increase in damping of max. 15% is observed for VE-x compared to the related unaged specimens. This effect is due to the softening and swelling characteristics of the polymer and the absorbed water molecules.^{62,63}

Compared to VE-x, the damping behaviour of EP is found to be less sensitive to any NC addition and at the same time much more stable when exposed to different environmental ageing conditions. The increased damping caused by water immersion and UV irradiation accumulates to the maximum damping $\tan \delta = 0.018$ after combined ageing. The results are valid for both investigated temperatures 0°C and −20°C.

To summarize, the damping behaviour can be increased for VE by up 28% and for EP by 6% due to a modification with NC. The overall damping capability of unaged VE is about 30% higher compared to EP at 0°C, whereas the damping behaviour of the two materials is very similar at −20°C. Compared to VE, it is found that EP is less sensitive to any matrix modification by NC as well as more stable when exposed to different environmental conditions. For example, the beneficial effect on the damping for NC-modified VE is lost when exposed to UV light.

Breakdown strength

Eight groups of specimens, VE-0, VE-1, VE-2, VE-3, EP-0, EP-1, EP-2 and EP-3 in four weight

Table 2. Test results of the electric strength of VE and EP specimens.

Materials	No. of specimen	Electric strength (kV/mm)
VE-0	# 1	14.4
	# 2	14.7
VE-1	# 1	16.2
	# 2	8.7
VE-2	# 1	16.2
	# 2	16.0
	# 3	16.7
VE-3	# 1	14.9
	# 2	15.4
EP		no results

concentrations, 0, 1, 2 and 3 wt% in NC composites, were tested in the electric strength test. Each group contains two or three specimens numbered in sequence. Breakdown voltage was obtained for each specimen and electric strength was calculated by dividing the breakdown voltage (kV) with the specimen thickness (mm). The electric strength of the specimens is presented in Table 2.

It is indicated in Table 2 that the electric strength of VE specimens modified by the NC is slightly increased compared with that of the neat VE specimens. For instance, # 2 in group VE-2 has a larger electric strength of 16 kV/mm compared to group VE-0 with strength values of 14.4 and 14.7 kV/mm. This observation agrees with results in the literature.^{31,73–76}

The increase in electric strength can be explained by a redistribution of space charge from a modification of NC in the material, resulting in an electrical field uniformity within the nanocomposite. Also, the small distance between NC particles leads to a zigzagging of the electrical tree, that is, it hinders the propagation of the electrical tree in the material. Thus, the specimen can withstand a higher electrical field. However, # 2 in group VE-1 has an unusual low electric strength, even compared with the neat specimens, which may be attributed to weak points (voids, particle agglomeration, etc.) in the material. Thus, this unusual value should be discarded when determining the inherent electrical strength of the VE material. It is also demonstrated based on the limited number of specimens that the electric strength promotion is not proportional to the weight percentage of the NC particles. Specimens with 1 and 2 wt% of NC have similar electric strength of around 16 kV/mm, while the value decreases when the NC concentration increases to 3 wt%. The decrease in electric strength may be the result of clay agglomerates in specimens in VE-3.

In the test, since the distance between the high-voltage electrode and the ground electrode was not

long enough, surface flashover always happened on EP specimens at an electrical field of 19 kV/mm. Therefore, all the EP specimens have a higher electric strength than 19 kV/mm and no effective data about the electric strength were obtained for the EP specimens.

Conclusion

The scope of this investigation was to prove the feasibility and performance of the NC-modified thermoset resin materials VE and EP with respect to high-voltage applications designed for life times of ≥ 50 years. Therefore, various mechanical and electrical material properties have been analysed under harsh environmental conditions such as water immersion, UV exposure and of these combinations. In particular, the effect of NC on the damping behaviour was studied at low temperatures and low frequencies, at which the dangerous cable vibration phenomena galloping typically occurs. In order to eliminate errors during mixing that could negatively affect the material properties at an early stage, various morphology analysis techniques such as SEM, TEM, XRD and rheological measurements were used. It was found that the NC was well dispersed within the polymer mainly consisting of exfoliated clay particles. Results from the experimental study demonstrate the effect of NC on the static, dynamic and electrical material behaviour. The main conclusions are drawn as follows:

- VE has a lower water absorption capacity as well as a lower weight loss due to UV exposure compared to EP. In contrast, VE is more sensitive to environmental ageing. For example, the strength of VE decreased by 22%, when exposed to UV light.
- The sensitivity of VE to the addition of NC is larger compared to EP. For example, an NC modification by 3 wt% led to a strength reduction of 18%, but also resulted in increased damping of up to 26%. This tendency is valid for all investigated environmental conditions.
- The dielectrical properties of VE increased by up to 11%, when modified with 2 wt% NC.
- By adding NC to EP, the tensile strength, stiffness and damping behaviour slightly increased for almost every configuration at all tested environmental conditions.
- The presence of NC led to a significant embrittlement of all investigated VE and EP matrix materials. The brittle behaviour of EP-x slightly changed under the influence of water immersion compared to EP-0.
- The material properties of neat EP were more stable under environmental ageing conditions, but less sensitive to NC compared to VE.

The last point inevitably leads to a design flexibility with respect to the material selection and material properties. Ensuring that all structural components are adequately protected during the life time from environmental impacts, for example, by coatings, the use of NC-modified VE (e.g. VE-3) can significantly enhance the vibrational behaviour – although it also results in some deficiencies in terms of strength and ductility. If special emphasis is on robust design with respect to environmental ageing, the use of NC-modified EP (e.g. EP-3) is preferred and may also result in slightly increased material properties like stiffness, strength and damping compared to neat EP. An embrittlement phenomena is only observed for the unaged and UV exposure test conditions.

The economic feasibility in terms of technical implementation of NC must also be considered and assessed. The long mixing times and the deteriorated flow characteristics during infusion processes due to increased dispersion viscosity are therefore important aspects to consider. Alternative manufacturing methods like filament winding may provide a solution to these drawbacks. Despite the above-mentioned limitations, NC is a promising and suitable additive for the enhancement of mainly dynamic, but also of specific static, material properties to be used in connection with high-voltage power pylons. However, a precise design evaluation and feasibility study has to be done prior to the application of NC-modified thermoset resin materials in composite structures.

Acknowledgements

Thanks are to the Institute of Lightweight Engineering and Polymer Technology of TU Dresden for their kind cooperation in carrying out the experimental dynamic study of this work.

Declaration of conflicting interests

The author(s) declared no potential conflicts of interest with respect to the research, authorship and/or publication of this article.

Funding

The author(s) disclosed receipt of the following financial support for the research, authorship and/or publication of this article: This research is supported by Innovationsfonden Denmark via the project Power Pylons of the Future (PoPyFu) in collaboration with Bystrup and Tuco Marine ApS, which are gratefully acknowledged.

References

1. Arora R and Mosch W. *High voltage and electrical insulation engineering*. New York: Wiley, 2011.

2. Ibrahimbegovic A and Kozar I. *Extreme man-made and natural hazards in dynamics of structures* (NATO security through science series). Rotterdam: Springer, 2007.
3. Li SY and Chen ZQ. Experimental investigation concerning aerodynamic stability of a stay cable incorporated with lamps. In: *Proceedings of the seventh Asia-Pacific conference on wind engineering*, Taipei, 8–12 November 2009, http://www.iawe.org/Proceedings/7APCWE/T3B_4.pdf
4. Boddy D and Rice J. Impact of alternative galloping criteria on transmission line design. In: *Proceedings of the electrical transmission and substation structures*, Fort Worth, TX, 8–12 November 2009, pp.1–12. Virginia: American Society of Civil Engineers.
5. Hu J, Yan B, Zhou S, et al. Parameter study on galloping of iced bundled conductors. In: *Proceedings of the 2010 Asia-Pacific power and energy engineering conference (APPEEC)*, Chengdu, China, 28–31 March 2010. New York: IEEE.
6. Lilien JL. State of the art of conductor galloping (Electra technical brochure 322), 2007, https://orbi.ulg.ac.be/bitstream/2268/17595/1/ELT_232_3.pdf
7. Chen WF and Lui EM. *Handbook of structural engineering*. 2nd ed. Boca Raton, FL: CRC Press, 2005.
8. Mohan TP, Velmurugan R and Kanny K. Damping characteristics of nanoclay filled hybrid laminates during medium velocity impact. *Compos Part B* 2015; 82: 178–189.
9. Kireitseu M, Hui D and Tomlinson G. Advanced shock-resistant and vibration damping of nanoparticle-reinforced composite material. *Compos Part B* 2008; 39: 128–138.
10. Sarathi R, Sahu R and Danikas MG. Understanding the mechanical properties of epoxy nanocomposite insulating materials. *J Electr Eng* 2009; 60: 358–361.
11. Velmurugan R and Mohan TP. Room temperature processing of epoxy-clay nanocomposites. *J Mater Sci* 2004; 39: 7333–7339.
12. Bensadoun F, Kchit N, Billotte C, et al. A comparative study of dispersion techniques for nanocomposite made with nanoclays and an unsaturated polyester resin. *J Nanomater* 2011; 2011: 406087-1–406087-12.
13. Karippal JJ, Murthy HNN, Rai KS, et al. Study of mechanical properties of epoxy/glass/nanoclay hybrid composites. *J Compos Mater* 2011; 45: 1893–1899.
14. Kabir A and Hoa SV. Improvement of vibration damping and flexural fatigue property incorporating nanoclay into glass/epoxy composite. In: *Proceedings of the 26th ICAF symposium*, Montreal, 1–3 June 2011. Berlin: Springer.
15. Kabir A. *Vibration damping property and flexural fatigue behavior of glass/epoxy/nanoclay composites*. PhD Thesis, Concordia University, Montreal, QC, Canada, 2010.
16. Singh RP, Khait M, Zunjarrao SC, et al. Environmental degradation and durability of epoxy-clay nanocomposites. *J Nanomater* 2010; 2010: 352746-1–352746-13.
17. Tcherbi-Narteh A, Hosur M and Jeelani S. Mechanical and thermal properties of carbon/epoxy nanoclay composites exposed to synergistic effect of UV radiation and condensation. In: *Proceedings of the 18th international conference on composite materials*, Jeju Island, Korea, 21–26 August 2011. International Committee on Composite Materials.
18. Hua J, Li X, Gao J, et al. UV aging characterization of epoxy varnish coated steel upon exposure to artificial weathering environment. *Mater Design* 2008; 30: 1542–1547.
19. Signor AW and Chin AW. Effects of ultraviolet radiation exposure on vinyl ester matrix resins: chemical and mechanical characterization. In: *Proceedings of the 16th technical conference on American society for composites*, Blacksburg, VA, 9–12 September 2001.
20. Dasan KP. Nanoclay/polymer composites: recent developments and future prospects. *Adv Struct Mater* 2015; 75: 561–579.
21. Bensadoun F, Kchit N, Billotte C, et al. A study of nanoclay reinforcement of biocomposites made by liquid composite molding. *Int J Polym Sci* 2011; 2011: 964193.
22. Kusmono M, Wildan MW and Ishak ZAM. Preparation and properties of clay-reinforced epoxy nanocomposites. *Int J Polym Sci* 2013; 2013: 690675.
23. Deepak K, Reddy NS and Naidu TV. Thermosetting polymer and nano clay based natural fiber bio-composites. *Proced Mater Sci* 2015; 10: 626–631.
24. Majeeda K, Jawaide M, Hassana A, et al. Potential materials for food packaging from nanoclay/natural fibres filled hybrid composites. *Mater Design* 2013; 46: 391–410.
25. Wang K, Chen L, Wu J, et al. Epoxy nanocomposites with highly exfoliated clay: mechanical properties and fracture mechanisms. *Macromolecules* 2005; 38: 788–800.
26. Chandradass J, Kumar MR and Velmurugan R. Effect of clay dispersion on mechanical, thermal and vibration properties of glass fiber-reinforced vinyl ester composites. *J Reinf Plast Comp*. Epub ahead of print 4 June 2008. DOI: 10.1177/0731684407081368.
27. Gilman JW. Flammability and thermal stability studies of polymer layered-silicate (clay) nanocomposites. *Appl Clay Sci* 1999; 15: 34–49.
28. Ozbenli E. Mechanical properties of exfoliated nanoclay/epoxy nanocomposites (University of Oklahoma), <http://www.ou.edu/> (2011, accessed 19 September 2016).
29. Kumar M, Kumar V, Muthuraja A, et al. Influence of nanoclay on the rheological properties of PMMA/organo-clay nanocomposites prepared by solvent blending technique. *Macromol Sy* 2016; 365: 104–111.
30. Karapappas P, Tsotra P and Scobbie K. Effect of nanofillers on the properties of a state of the art epoxy gelcoat. *eXPRESS Polym Lett* 2011; 5: 218–227.
31. Guevara-Morales A and Taylor AC. Mechanical and dielectric properties of epoxy-clay nanocomposites. *J Mater Sci* 2014; 49: 1574–1584.
32. Ingram S, Dennis H, Hunter I, et al. Influence of clay type on exfoliation, cure and physical properties of in situ polymerised poly(methyl methacrylate) nanocomposites. *Polym Int* 2008; 57: 1118–1127.
33. Chandradass J, Kumar MR and Velmurugan R. Effect of nanoclay addition on vibration properties of glass fibre reinforced vinyl ester composites. *Mater Lett* 2007; 61: 4385–4388.
34. Ho MW. *The mechanical thermal and microstructural behaviors of the strip silicates reinforced epoxy-based*

- nanocomposites. PhD Thesis, University of New Orleans, New Orleans, LA, 2006.
35. Lam CK, Lau KT, Cheung HY, et al. Effect of ultrasound sonication in nanoclay clusters of nanoclay/epoxy composites. *Mater Lett* 2005; 59: 1369–1372.
 36. Agubra VA, Owuor PS and Hosur MV. Influence of nanoclay dispersion methods on the mechanical behavior of E-glass/epoxy nanocomposites. *Nanomaterials* 2013; 3: 550–563.
 37. Keyoonwong W, Guo Y, Kubouchi M, et al. Corrosion behavior of three nanoclay dispersion methods of epoxy/organoclay nanocomposites. *Int J Corros* 2012; 2012: 924283.
 38. Ngo TD, Ton-That MT, Hoa SV, et al. Effect of temperature, duration and speed of pre-mixing on the dispersion of clay/epoxy nanocomposites. *Compos Sci Technol* 2009; 69: 1831–1840.
 39. Alateyah AI, Dhakal HN, Zhang ZY, et al. Nanoindentation and characterisations of vinyl ester matrix nanocomposites based on layered silicate: effect of voids content. *Int J Mater Eng* 2014; 4: 97–102.
 40. Imai T, Sawa F, Nakano T, et al. Effects of nano- and micro-filler mixture on electrical insulation properties of epoxy based composites. *IEEE T Dielect El In* 2006; 13: 319–326.
 41. Kandelbauer A, Tondi G and Goodman S. *Handbook of thermoset plastics: 6. Unsaturated polyesters and vinyl esters*. 3rd ed. London: William Andrew, 2013.
 42. Datasheet of GARAMITE 1958 by BYK: Additives and Instruments. GARAMITE 1958-rheological additive for epoxy, vinyl ester and unsaturated polyester resins, datasheet (Issue 10), 2013, www.byk.com
 43. Bhat G, Hegde RR, Kamath MG, et al. Nanoclay reinforced fibers and nonwovens. *J Eng Fiber Fabr* 2008; 3: 22–34.
 44. Chen J and Yan N. Crystallization behavior of organo-nanoclay treated and untreated kraft fiber – HDPE composites. *Compos Part B* 2013; 54: 180–187.
 45. ISO 527-2:2012. Plastics: determination of tensile properties: part 2: test conditions for moulding and extrusion plastics.
 46. Liu B, Zhu KJ, Sun XQ, et al. A contrast on conductor galloping amplitude calculated by three mathematical models with different DOFs. *Shock Vib* 2014; 2014: 781304.
 47. IEC 60243-1:2013. Electrical strength of insulating materials-test methods – part 1: tests at power frequencies.
 48. IEC 60212:2011. Standard conditions for use prior to and during the testing of solid electrical insulating materials.
 49. ASTM D4329-13:2013. Standard practice for fluorescent ultraviolet (UV) lamp apparatus exposure of plastics.
 50. ASTM D570-98:2010. Standard test method for water absorption of plastics.
 51. Christiansen MB, Lopacinska JM, Jakobsen MH, et al. Polymer photonic crystal dye lasers as Optofluidic Cell Sensors. *Opt Express* 2009; 4: 2722–2730.
 52. Ferreira JAM, Borrego LP, Costa JDM, et al. Fatigue behaviour of nanoclay reinforced epoxy resin composites. *Compos Part B* 2013; 52: 286–291.
 53. Khan SU. *Multiscale carbon fiber-reinforced epoxy composites containing nanofillers*. PhD Thesis, The Hong Kong University of Science and Technology, Hong Kong, 2011.
 54. Huynh HT, Benzarti K and Duc M. Role of interfacial chemistry on the rheology and thermo-mechanical properties of clay-polymer nanocomposites for building applications. *Chem Pap* 2012; 66: 519–531.
 55. Pal R. *Moisture diffusion through organomodified montmorillonite polymer nanocomposites and resulting property degradations*. PhD Thesis, University of Mysore, Mysore, India, 2014.
 56. Vijayan PP, Puglia D, Kennyb JM, et al. Effect of organically modified nanoclay on the miscibility, rheology, morphology and properties of epoxy/carboxyl-terminated (butadiene-co-acrylonitrile) blend. *Soft Matter* 2013; 9: 2899–2912.
 57. Vosters PJC. *Dual action adhesive composition*. Patent WO 2014033273 A2, 2014, <https://patentscope.wipo.int/search/en/detail.jsf?docId=WO2014033273>
 58. Khanbabaie G, Aalaie J, Rahmatpour A, et al. Preparation and properties of epoxy-clay nanocomposites. *J Macromol Sci B* 2007; 46: 975–986.
 59. Kumar BG, Singh RP and Nakamura T. Degradation of carbon fiber-reinforced epoxy composites by ultraviolet radiation and condensation. *J Compos Mater* 2002; 24: 2713–2733.
 60. Tcherbi-Narteh A, Hosur M, Triggs E, et al. Viscoelastic and thermal properties of full and partially cured DGEBA epoxy resin composites modified with montmorillonite nanoclay exposed to UV radiation. *Polym Degrad Stabil* 2014; 101: 81–91.
 61. Simar A, Gigliotii M, Grandidier JC, et al. Evidence of thermo-oxidation phenomena occurring during hygro-thermal aging of thermosetting resins for RTM composite applications. *Composites: Part A* 2014; 66: 175–182.
 62. Zai BA, Park MK, Choi HS, et al. Effect of moisture absorption on damping and dynamic stiffness of carbon fiber/epoxy composites. *J Mech Sci Technol* 2009; 23: 2998–3004.
 63. Dutta SS. *Water absorption and dielectric properties of epoxy insulation*. Master Thesis, Department of Electrical Power Engineering, Norwegian University of Science and Technology, Trondheim, 2008.
 64. Monneya L, Dubois C, Perreux D, et al. Mechanical behaviour of an epoxy-glass composite under photo-oxidation. *Polym Degrad Stabil* 1999; 63: 219–224.
 65. Thiagarajan A, Kaviarasan K, Vigneshwaran R, et al. The nano clay influence on mechanical properties of mixed glass fibre polymer composites. *Int J ChemTech Res* 2014; 6: 1840–1843.
 66. Ho MW, Lam CK, Lau KT, et al. Mechanical properties of epoxy-based composites using nanoclays. *Compos Struct* 2014; 75: 415–421.
 67. Rashmi, Renukappa NM, Chikkakuntappa R, et al. Montmorillonite nanoclay filler effects on electrical conductivity, thermal and mechanical properties of epoxy-based nanocomposites. *Polym Eng Sci* 2011; 51: 1827–1836.
 68. Zunjarrao SC, Sriraman R and Singh RP. Effect of processing parameters and clay volume fraction on the

- mechanical properties of epoxy-clay nanocomposites. *J Mater Sci* 2006; 41: 2219–2228.
69. Sobrinho LL, Ferreira M and Bastian FL. The effects of water absorption on an ester vinyl resin system. *Mater Res* 2009; 12: 353–361.
70. Zhao H and Li RKY. Effect of water absorption on the mechanical and dielectric properties of nano-alumina filled epoxy nanocomposites. *Key Eng Mat* 2007; 334: 617–620.
71. Ehrenstein GW, Riedel G and Trawiel P. *Praxis der Thermischen Analyse von Kunststoffen*. Vienna: Hanser Verlag, 1998.
72. Zhang PQ, Ruan JH and Li WZ. Influence of some factors on the damping property of fiber-reinforced epoxy composites at low temperature. *Cryogenics* 2001; 41: 245–251.
73. Ma D, Hugener TA and Siegel RW. Influence of nanoparticle surface modification on the electrical behaviour of polyethylene nanocomposites. *Nanotechnology* 2005; 6: 724–731.
74. Hai-bing H, Hong-Yan L and Bin L. Effect of nanometric fillers on electrical properties of polymers. *Insul Mater* 2006; 5: 36–39.
75. Junguo G, Jinmei Z and Quanquan J. Study on breakdown and partial discharge of polyethylene montmorillonite nanocomposites. In: *Proceedings of the international symposium on electrical insulating materials (ISEIM)*, Yokkaichi, Japan, 7–11 September 2008. New York: IEEE.
76. Zazoum B, David E and Ngo AD. Correlation between structure and dielectric breakdown in LDPE/HDPE/clay nanocomposites. *ISRN Nanomater* 2014; 2014: 612154-1–612154-9.