

'Shadow' Glass Transition in Glass

Yue, Yuanzheng

Published in:
National Science Review

DOI (link to publication from Publisher):
[10.1093/nsr/nwab160](https://doi.org/10.1093/nsr/nwab160)

Creative Commons License
CC BY 4.0

Publication date:
2021

Document Version
Publisher's PDF, also known as Version of record

[Link to publication from Aalborg University](#)

Citation for published version (APA):
Yue, Y. (2021). 'Shadow' Glass Transition in Glass. *National Science Review*, 8(12), Article nwab160.
<https://doi.org/10.1093/nsr/nwab160>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

Take down policy

If you believe that this document breaches copyright please contact us at vbn@aub.aau.dk providing details, and we will remove access to the work immediately and investigate your claim.

MATERIALS SCIENCE

'Shadow' glass transition in glass

Yuanzheng Yue

The glass transition is the most striking dynamic feature of glass-forming liquids and rigid glass, manifest in the following two scenarios [1]. First, a viscous glass-forming liquid is transformed into a rigid glass state during cooling if the cooling rate is high enough to prevent the liquid from crystallizing—this process is called the 'liquid–glass transition'. Second, a rigid glass state is transformed into a viscous liquid on heating—this process is called the 'glass–liquid transition' or simply the 'glass transition'. Substantial progress has been made in understanding of the glass transition through atomistic simulations and advanced structure probing tools [1]. However, despite such progress, there is much we do not know about the glass transition, largely because of difficulties in probing the structural response of liquid or glass to the glass transition at different length and time scales. Thus, the nature of glassy state was selected as one of the 125 big scientific questions of our time by *Science* in 2005,

where it was asked 'Where and why does liquid end and glass begin?'. This question continues to attract considerable interest of scientists.

As a crucial contribution to understanding of the calorimetric glass transition, several groups of scientists independently observed a striking pre-endothermic event, that is an endothermic pre-peak before the real glass transition starts. This phenomenon occurs in annealed hyperquenched (HQ) (cooled at $>10^5$ K/s) glasses including metallic [2], organic [3] and inorganic systems [4], respectively, during dynamic reheating (or upscan) in a differential scanning calorimeter (DSC). The pre-peak is followed by an exothermic sub- T_g peak in HQ glass that has undergone a certain duration of annealing below T_g . The reheating and the subsequent cooling are conducted at the standard rate of 20 K/min. The glass cooled at this rate is usually defined as the 'standard' glass. The cooling rate

for a HQ glass is more than six orders of magnitude higher than the standard rate. The magnitude of the SGT peak is quantified by the difference in isobaric heat capacity (C_p) between the annealed HQ glass and the standard glass in the temperature range of the SGT peak, and it is expressed as $\Delta C_{p@T_g, shadow}$. To distinguish from the real reversible glass transition peak, the endothermic pre-peak was expressed as the shadow glass transition (SGT) by Yue and Angell [4]. Both the magnitude and temperature of the SGT peak continuously increase with increasing annealing temperature and time.

As a significant step towards understanding of SGT, Yang *et al.* recently detected SGT peaks in HQ metallic glasses (MGs) using the chip-based fast scanning calorimetry (FSC) without performing annealing [5]. In doing so, they verified that SGT is a universal feature of HQ metallic glasses. They elegantly revealed the quantitative correlation of SGT with β relaxation by

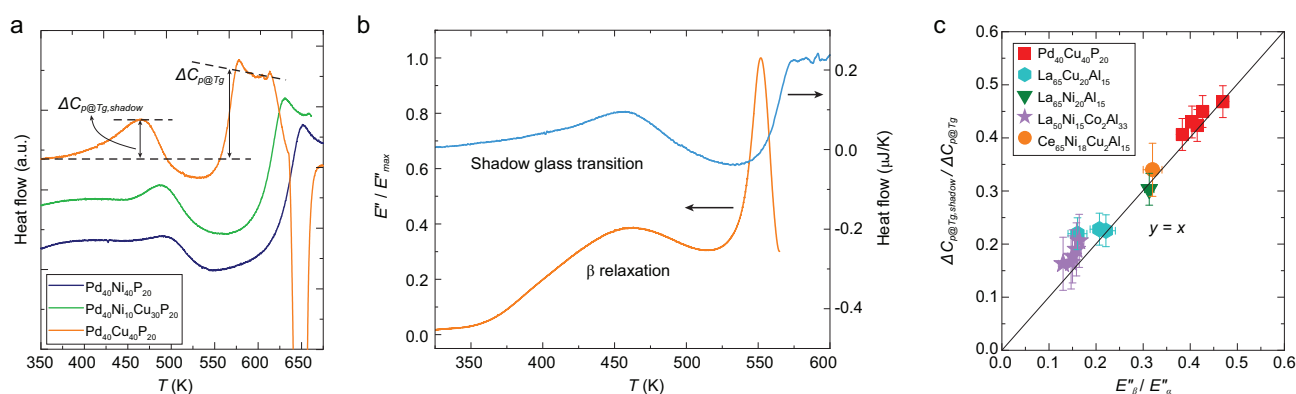


Figure 1. Coupling between shadow glass transition and β relaxation [5]. (a) FSC heat flow curves for Pd₄₀Ni_{40-x}Cu_xP₂₀ ($x = 0, 30$ and 40) MGs at an upscan rate of 500 K/s, showing quantification of the extents of both SGT ($\Delta C_{p@T_g, shadow}$) and real glass transition ($\Delta C_{p@T_g}$). (b) FSC heat flow (200 K/s) versus DMS loss modulus (2 Hz). (c) Relationship between the normalized extent of SGT ($\Delta C_{p@T_g, shadow} / \Delta C_{p@T_g}$) and that of β relaxation ($E''_{\beta} / E''_{\alpha}$).

comparing the calorimetric traces with dynamic mechanical spectra (DMS). Figure 1a shows the pronounced endothermic SGT peaks for three HQ metallic glass systems, which are followed by the exothermic enthalpy relaxation peaks, and then by the real glass transition peaks. For the $\text{Pd}_{40}\text{Ni}_{40-x}\text{Cu}_x\text{P}_{20}$ glass, a crystallization peak appears subsequent to the glass transition. As illustrated in Fig. 1a, the magnitudes of both SGT and real glass transition are determined by the heights of their corresponding peaks, that is $\Delta C_p@T_{g,shadow}$ and $\Delta C_p@T_g$, respectively. Figure 1b displays the direct correspondence between SGT and β relaxation in the same temperature range through the FSC and DMS measurements, while Fig. 1c shows the proportionality between SGT and β relaxation. These results thus become the first direct evidence for the dynamic origin of SGT. The evidence is supported by the heating rate dependences of both SGT and β relaxation overlapping with

each other, and merging with those of the real glass transition and α relaxation at sufficiently high temperature, that is well above the standard T_g . This implies a bridge between the dynamics and the thermodynamics of β relaxation. Interestingly, Yang *et al.* also discovered that the SGT temperature ($T_{g,shadow}$) first decreases with quenching rate, and then remains unchanged when the quenching rate exceeds 10^6 K/s. This indicates that a critical $T_{g,shadow}$ value exists, below which the glass structural domains with the lowest potential energy cannot be rejuvenated to the average energy level of the standard glass.

In summary, the work by Yang *et al.* provides a great advancement in revealing the nature of the shadow glass transition. Their findings have implications for the connection between the shadow and real glass transitions, as well as for correlation of the shadow glass transition with both β relaxation and physical properties of hyperquenched glasses [6]. Their

work is anticipated to stimulate research into the microscopic origin of the shadow glass transition.

Conflict of interest statement. None declared.

Yuanzheng Yue

Department of Chemistry and Bioscience, Aalborg University, Denmark

E-mail: yy@bio.aau.dk

REFERENCES

1. Debenedetti PG and Stillinger FH. *Nature* 2001; **410**: 259–67.
2. Chen HS and Inoue A. *J Non-Cryst Solids* 1984; **61&62**: 805–10.
3. Berens AR and Hodge IM. *Macromolecules* 1982; **15**: 756–61.
4. Yue YZ and Angell CA. *Nature* 2004; **427**: 717–20.
5. Yang Q, Peng SX and Wang Z *et al.* *Natl Sci Rev* 2020; **7**: 1896–905.
6. Yang Q, Pei CQ and Yu HB *et al.* *Nano Lett* 2021; **21**: 6051–6.