



**AALBORG UNIVERSITY**  
DENMARK

**Aalborg Universitet**

## **Advanced Solid-State Lithium Battery and Its Safety**

Zhao, Zhaoyang; Hu, Haitao; He, Zhengyou; Zhu, Hongyi; Davari, Pooya; Blaabjerg, Frede

*Published in:*

CPSS Transactions on Power Electronics and Applications (CPSS TPEA)

*DOI (link to publication from Publisher):*

[10.24295/CPSSSTPEA.2023.00027](https://doi.org/10.24295/CPSSSTPEA.2023.00027)

*Publication date:*

2023

*Document Version*

Publisher's PDF, also known as Version of record

[Link to publication from Aalborg University](#)

*Citation for published version (APA):*

Zhao, Z., Hu, H., He, Z., Zhu, H., Davari, P., & Blaabjerg, F. (2023). Advanced Solid-State Lithium Battery and Its Safety. *CPSS Transactions on Power Electronics and Applications (CPSS TPEA)*, 8(4), 348 - 362. Article 10122805. <https://doi.org/10.24295/CPSSSTPEA.2023.00027>

### **General rights**

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

### **Take down policy**

If you believe that this document breaches copyright please contact us at [vbn@aub.aau.dk](mailto:vbn@aub.aau.dk) providing details, and we will remove access to the work immediately and investigate your claim.

# Advanced Solid-State Lithium Battery and Its Safety

Zhaoyang ZHAO, Haitao HU, Zhengyou HE, Hongyi ZHU, Pooya DAVARI, and Frede BLAABJERG

**Abstract**—Solid-state lithium battery (SSLB) is considered as the most potential energy storage device in the next generation energy system due to its excellent safety performance. However, there are still intimidating safety issues for the SSLB, due to it being still in the development stage. This paper gives an overview of the safety of SSLBs. First, advanced solid-state battery techniques are introduced. Second, the safety issues of SSLBs are discussed. Then, the safety enhancement techniques are provided. Finally, future research opportunities are presented. This paper aims to provide a reference for researchers in the fields of electronic and electrical engineering who want to make some efforts in SSLB safety.

**Index Terms**—Failure, safety enhancement techniques, safety issues, solid-state lithium battery (SSLB).

## NOMENCLATURE

SSLB	Solid-state lithium battery.
ANN	Artificial neural network.
ARC	Accelerating rate calorimeter.
ASD	Adjustable speed drive.
ASSB	All-solid-state battery.
BSEE	Battery energy storage system.
CB	Cell balancing.
CC-CV	Constant current-constant voltage.
EIS	Electrochemical impedance spectroscopy.
EKF	Extended Kalman filtering.
EL	Ensemble learning.
EVs	Electric vehicles.
FFT	Fast Fourier transform.
HEVs	Hybrid EVs.
KF	Kalman filtering.
K-NN	K-nearest neighbor regression.
LE	Liquid electrolyte.

LEBs	Liquid electrolyte batteries.
LIBs	Lithium-ion batteries.
LLZO	Lithium lanthanum zirconium niobium oxide.
LR	Linear regression.
NDP	Neutron depth profiling.
PC	Pulse current.
PE	Power electronic.
PI	Proportional integral.
QSSB	Quasi-solid-state battery.
RF	Random forest.
RLS	Recursive least square.
RMS	Root mean square.
SEM	Scanning electron microscopy.
SE	Solid electrolyte.
SOE	State of energy.
SOH	State of health.
SOP	State of power.
SOS	State of safety.
SOT	State of temperature.
SRC	Sinusoidal ripple current.
SSB	Solid-state battery.
SVM	Support vector machine.
sXAS	Soft X-ray absorption spectroscopy.
UKF	Unscented KF.

## I. INTRODUCTION

NOWDAYS, lithium-ion batteries (LIBs) have been widely used in grid energy storage, electric vehicles, portable devices, etc. [1], [2]. Fig. 1(a) and Fig. 1(b) show the typical applications of LIBs in power systems [3] and electric vehicles (EVs)/hybrid EVs (HEVs) [4]. However, conventional LIB is composed of flammable liquid electrolytes and carbon anodes, its energy density and safety are relatively low. Some safety accidents caused by fires and explosions of LIBs have been widely reported [5], [6]. Typical cases are shown in Fig. 1(c) [7], [8].

Recently, many efforts have been made to improve the safety of LIBs, from the designing phase to the application phase of batteries. Some state-of-the-art techniques are systematically summarized in [9]–[15]. From the perspective of the application phase, some state-of-the-art thermal management techniques [9], [10], state estimation techniques [11], fault diagnosis techniques [12], [13], etc., have been reviewed in [9]–[13]. From the perspective of the designing phase, the critical progress in materials design has been summarized in [14], [15].

Although the above-mentioned methods can improve the safety of LIBs, their intrinsic safety has not been addressed.

Manuscript received January 3, 2023; revised March 10, 2023; accepted March 20, 2023. Date of publication December 30, 2023; date of current version May 10, 2023. This work was supported in part by the National Natural Science Foundation of China under Grant 52207225, in part by Sichuan Science and Technology Program under Grant 2022NSFSC0001, in part by the Natural Science Foundation of Sichuan Province under Grant 2023NSFSC0814, and in part by Central University Science and Technology Innovation Project under Grants 2682022ZTPY070, 2682022KJ029, and 2682023CX004. (Corresponding author: Haitao Hu.)

Z. Zhao, H. Hu, and Z. He are with the Institute of Smart City and Intelligent Transportation, Southwest Jiaotong University, Chengdu 610031, China (e-mail: zhaoyang.zhao@swjtu.edu.cn; hht@swjtu.edu.cn; hezy@swjtu.edu.cn).

H. Zhu is with the School of Electrical Engineering, Southwest Jiaotong University, Chengdu 610031, China (e-mail: dextero@my.swjtu.edu.cn).

P. Davari and F. Blaabjerg are with the AAU Energy, Aalborg University, 9220 Aalborg, Denmark (email: pda@energy.aau.dk; fbl@energy.aau.dk).

Digital Object Identifier 10.24295/CPSS TPEA.2023.00027

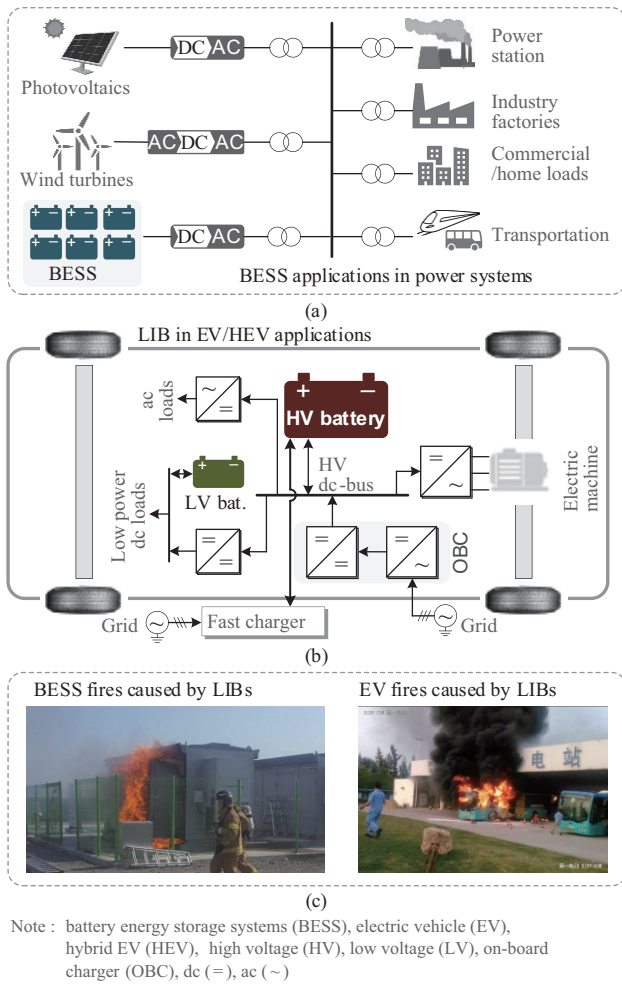


Fig. 1. Typical applications of LIBs and accidents caused by LIBs. (a) Battery energy storage system (BESS) applications in power systems [3]. (b) LIBs in electric vehicle (EV)/hybrid EV (HEV) applications [4]. (c) Typical accidents caused by LIBs [5]–[8].

Nowadays, solid-state lithium batteries (SSLBs) have caused broad attention due to the potential of achieving higher safety compared with conventional LIBs [16], [17]. However, there are still intimidating safety issues for the SSLB, due to it being still in the development stage and the design and fabrication are not entirely satisfactory. In [18], [19], the failure mechanisms of SSLBs have been summarized. Furthermore, the stability issues and safety issues of SSLBs have been thoroughly reviewed in [20], [21]. Typical failure mechanisms and safety issues are summarized in Table I.

These overviews provide summaries of SSLBs' safety issues. However, they mainly focus on the fields of materials analysis and design. In order to provide a reference for researchers in the fields of electronic and electrical engineering, this paper review the state-of-the-art solid-state lithium battery and its safety. The main contributions are given in the following.

- 1) Summarizes the state-of-the-art solid-state battery techniques and analyzes the safety of solid-state lithium batteries (SSLBs).
- 2) Discusses the safety enhancement techniques of battery, which can be used for SSLBs.

TABLE I  
TYPICAL FAILURE MECHANISMS AND SAFETY ISSUES OF SSLBs [18]–[21]

Safety issue	Critical failure mechanisms
Electrochemical/chemical issue	Electrochemical reaction
	Electrode and electrolyte loss
	External mechanical stresses (e.g., nail penetration and severe impact crushing)
Mechanical issue	Internal mechanical damage (e.g., lithium dendrite, short circuit, materials volume change, internal contact problems)
	External thermal stresses (e.g., high temperature, and combustion)
Thermal issue	Internal heat generation (e.g., electrochemical reaction, overcharge, short circuit)

The rest of this paper is organized as follows: Section II reviews the advanced solid-state battery techniques. The safety issues of SSLBs are discussed in Section III. Section IV is dedicated to safety enhancement techniques. Finally, the conclusion and outlook are put forward in Section V.

## II. ADVANCED SOLID-STATE BATTERY TECHNIQUES

In this section, the development of battery techniques is discussed. Then, the state-of-the-art solid-state battery (SSB) techniques are analyzed.

### A. Development of Battery Techniques

According to the amount of liquid in the assembled batteries, batteries can be divided into three categories, i.e., liquid electrolyte battery, all-solid-state battery, and quasi-solid-state battery, as shown in Fig. 2.

Nowadays, the widely used LIBs are liquid electrolyte batteries (LEBs), which contain electrodes, separators, and liquid electrolytes, such as nonaqueous and aqueous electrolytes. Besides, gel electrolyte battery is also considered as liquid battery. Generally, LEBs have mature manufacturing techniques and have been widely used in various applications requiring energy storage. However, the safety issue of LEBs is considered as the main challenge. Fig. 2(a) shows the typical thermal runaway process of LEBs [22], [23].

As next-generation batteries, all-solid-state batteries (ASSBs) have been attracting wide attention. Generally, ASSBs include inorganic solid electrolyte batteries, polymer solid electrolyte batteries, composite polymer/ceramic solid electrolyte batteries, etc. However, there are still intimidating challenges in the designing and manufacturing of ASSBs. The maximum challenge of ASSBs is the interface issue, which results in the capacity, cycling, and rate performances of ASSBs being far below that of traditional LIBs. Generally, the interface issue is very complex, detail discussion can be found in [24]. Fig. 2(b) shows the typical interface issue of ASSBs [25]. Generally, the space charge layer and the interfacial layer will cause a large interfacial impedance, which reduces reaction kinetics and limits the performance of batteries. Moreover, the charging and discharging will further exacerbate the interface issue. Taking the interface between

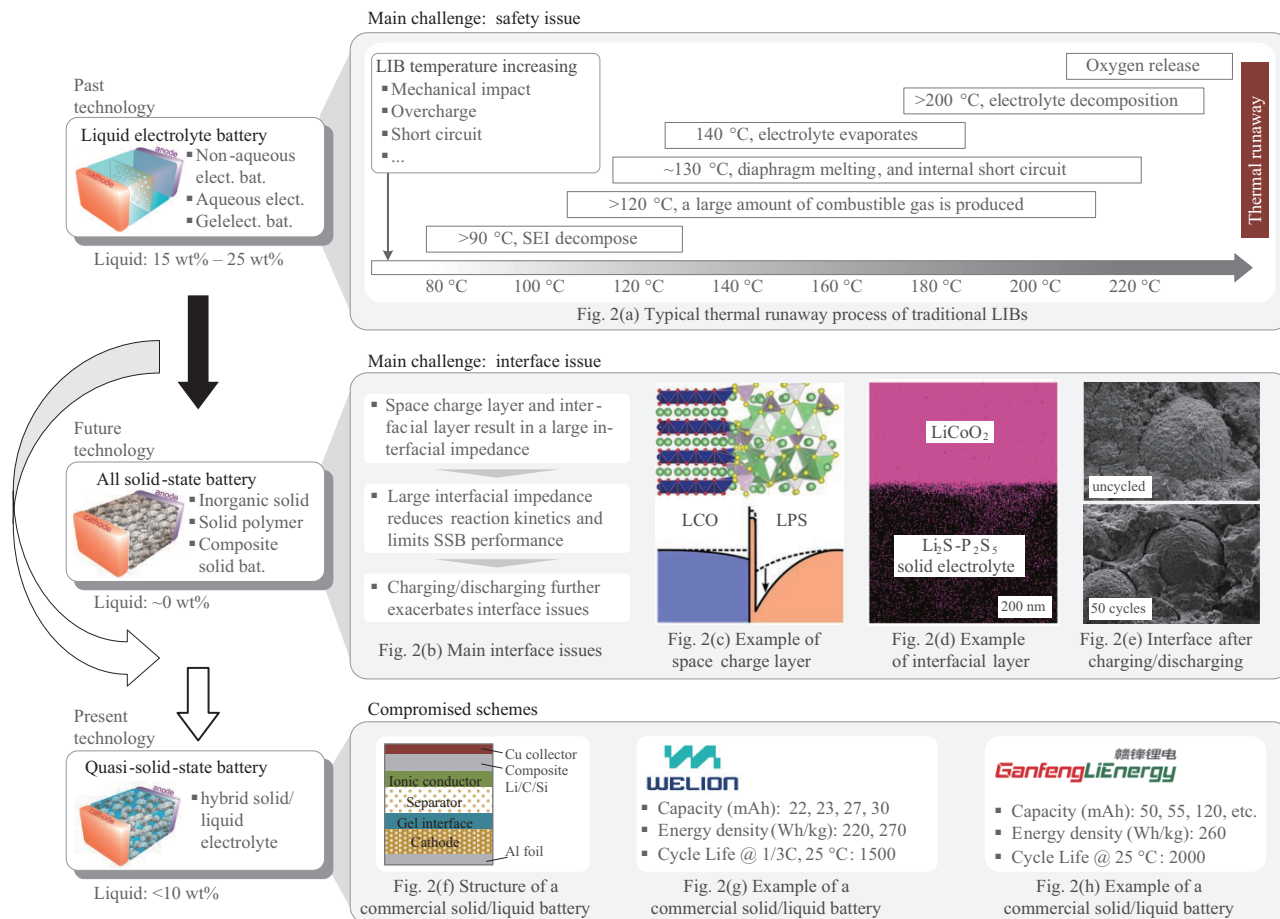


Fig. 2. Development of battery techniques [22]–[31].

$\text{LiCoO}_2$  cathode and  $\beta\text{-Li}_3\text{PS}_4$  solid electrolyte (LCO/LPS) as an example, Fig. 2(c) shows the interface issue caused by space charge layer [26], [27]. Moreover, Fig. 2(d) shows the example of interfacial layer, where the electrodes are  $\text{LiCoO}_2$  and  $\text{Li}_2\text{S-P}_2\text{S}_5$  [28]. Furthermore, Fig. 2(e) shows the picture of SSB's interfacial layer before and after charging/discharging [29]. It can be seen that there exist obvious gaps on the interface after charging/discharging, which results in the increasing of interfacial impedance.

In order to overcome the limitations of conventional liquid electrolyte batteries and all-solid-state batteries, hybrid solid/liquid batteries have been developed. They are also known as quasi-solid-state batteries (QSSBs). Usually, a little amount of liquid phase is added on the cathode side to obtain sufficient contact between cathode particles and the solid-state electrolyte, in order to balance the performance and safety. Nowadays, the commercial “solid-state battery” all belong to quasi-solid-state batteries. Fig. 2(f) shows the structure of a commercial quasi-solid-state battery, and some commercial products are shown in Fig. 2(g) and Fig. 2(h) [30], [31].

### B. State-of-the-Art SSB Techniques

Recently, the majority of studies have focused on the material development of SSBs, including the cathode, anode,

and solid electrolyte.

Generally, the available anode materials include lithium metal electrodes, graphene electrodes, silicon-based electrodes, tin-based electrodes, and metallic oxide/nitride electrodes. The composite sulfur electrodes, metallic oxide electrodes, metal sulfide electrodes, and metal fluoride electrodes can be used for the cathode of SSBs. Furthermore, polymer electrolytes, inorganic electrolytes, and composite electrolytes are widely used for solid electrolytes. Fig. 3(a) shows the classification of SSB materials. Detailed discussions of the state-of-the-art SSB materials can be found in [32]–[38].

Fig. 3(b) shows the typical assembly technologies of SSBs [20], which include heat treatment technique, cold-press technique, film technique, and roll-to-roll stack techniques. Generally, the SSB assembled using heat treatment has relatively poor interfacial and mechanical properties, and it is difficult to manufacture batteries with large capacities. The cold-press technique requires additional mechanical devices to generate presses on SSB, which has a high cost. Similarly, the film technique and roll-to-roll stack technique are also limited by battery capacity.

In summary, the materials and assembly technologies of SSBs are not mature at present. Quasi-solid batteries are feasible solutions in years to come. However, the safety of QSSBs should be considered due to the existence of liquid



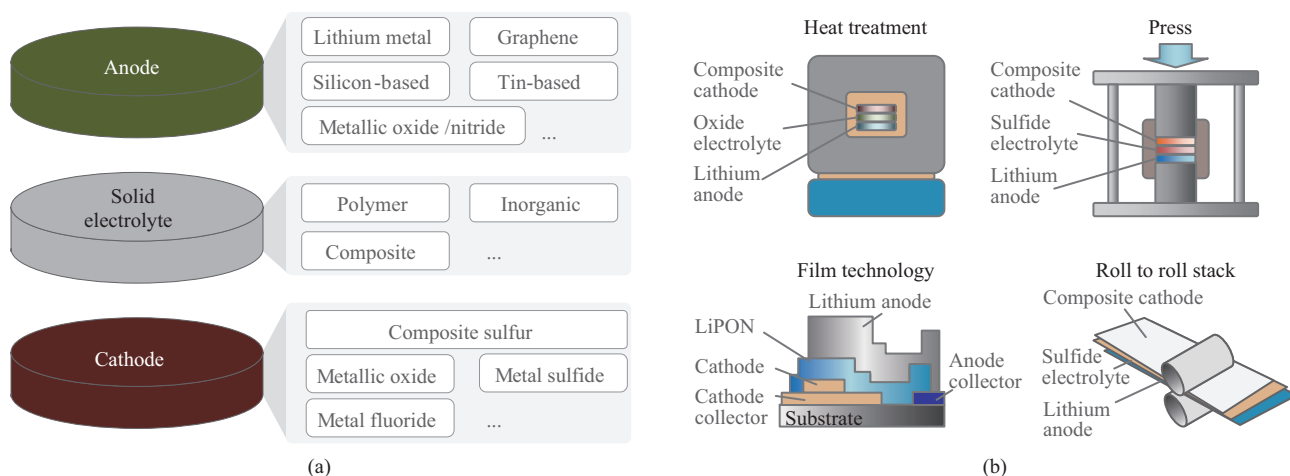


Fig. 3. State-of-the-art SSB techniques. (a) Advanced SSB materials [32]–[38]. (b) Typical assembly technologies of SSBs [20].

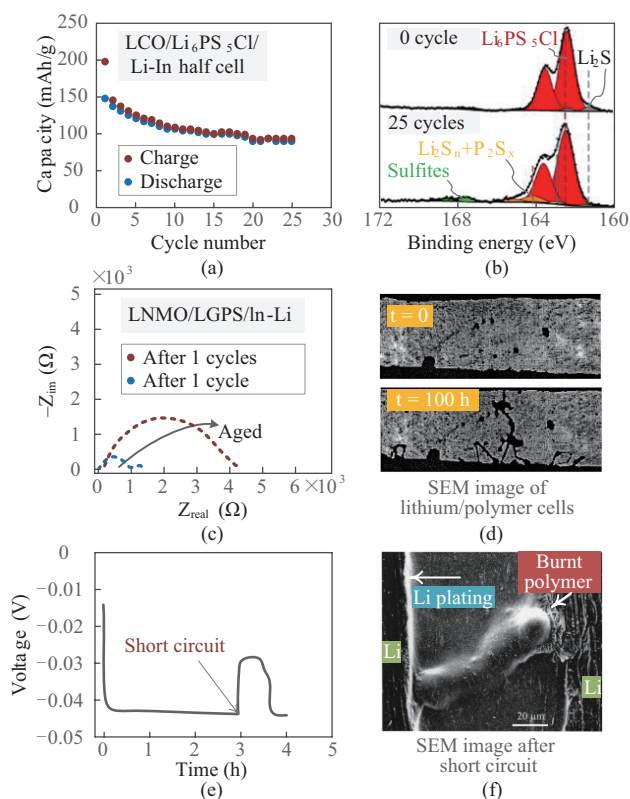


Fig. 4. Examples of failure behaviors of SSLBs. (a) Example of capacity degradation [43]. (b) X-ray photoelectron spectroscopy of the electrode surface before and after battery aging [43]. (c) Example of impedance variation [47]. (d) Example of dendritic growth [49]. (e) Example of voltage profile before and after short circuit [50]. (f) Example of short circuit [50].

electrolytes in batteries.

### III. SAFETY ISSUES OF SOLID-STATE LITHIUM BATTERIES

Similar to conventional LIBs, emerging solid-state lithium batteries (SSLBs) also exists some failure behaviors caused by electric, chemical, electrochemical, mechanical, and thermal effects. In this section, the typical safety issues of SSLBs are discussed.

#### A. Failure Behaviors and Failure Mechanisms

Generally, it is considered that cracks caused by mechanical stresses (e.g., nail penetration and severe impact crushing) would result in short-circuiting and thermal runaway of SSLBs [21]. However, some experimental results from battery manufacturers illustrate that an SSLB can continue operating after nail penetration tests [39], [40]. At this stage, there is no clear failure analysis for SSLBs under external mechanical stresses, which is not considered in this paper. Typical failure behaviors of SSLBs include electrical parameters drift [41]–[48], internal structure change [49]–[55], and thermal runaway [56]–[58] are discussed in this part.

##### 1) Electrical Parameters Drift

Generally, the electrical parameters, such as capacity, and impedance, will drift with the degradation of SSLBs [41], [42]. Taking LCO/Li<sub>6</sub>PS<sub>5</sub>Cl/Li-In half cell as an example, Fig. 4(a) shows the relationship between capacity and cycle number. It can be seen that the capacity of SSLBs decreases with the cycle number increases [43]. Generally, the electrical parameters drift is caused by the interface reaction of batteries. Fig. 4(b) shows the X-ray photoelectron spectroscopy of the electrode surface before and after battery aging. It is found that the intensity of the S2p signal of Li<sub>2</sub>S decreases, whereas the intensity of the signal of sulfites increases [43], which demonstrates the interfacial reaction occurred.

Taking LNMO/LGPS/In-Li symmetric cells as an example, Fig. 4(c) shows the variation of electrochemical impedance spectroscopy (EIS) with the aged of SSLBs [47]. Generally, the impedance drift depends on the reaction on the solid electrolyte/electrode interface, such as space charge layer formation, element interdiffusion, and material/electrolyte interface reaction.

##### 2) Internal Structure Change

Although solid-state electrolyte is considered can reduce the penetration of Li dendrites across electrolytes, lithium dendrite in SSBs is still a potential safety issue [49]–[52]. Taking solid

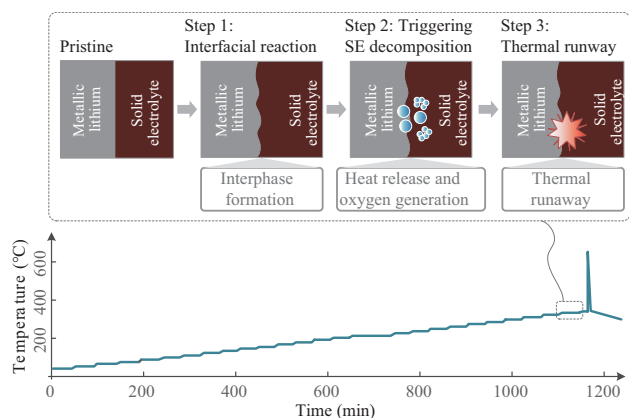


Fig. 5. Example of thermal runaway of SSLBs [57].

polymer batteries as an example, Fig. 4(d) shows its scanning electron microscopy (SEM) image, which demonstrates the growth of lithium dendrite [49]. The continuous growth of lithium dendrite may result in the internal circuit of SSBs. Taking a lithium/polymer cell as an example, Fig. 4(e) shows the voltage profile before and after an internal short occurs. Furthermore, Fig. 4(f) shows SEM image of this cell, which demonstrates the presence of a dendrite that went through the polymer.

Moreover, the volume of electrode materials will change after frequent charging and discharging. Repeated expansion and contraction will cause internal mechanically damage and contact problems, which results in the performance degradation of SSLBs [53]–[55].

### 3) Thermal Runaway

Similar to conventional LIBs, there exists a thermal runaway of SSBs [56]–[58]. Taking oxide solid electrolytes (SEs) with Li metal as an example, Fig. 5 shows the typical thermal runaway procedure of SSBs [57]. It can be seen that there exist three steps of this type of SE. First, the interface has formed after the contact between SEs and metallic Li. With the increase of temperature, metallic Li starts melting, and the contact of SEs and metallic Li is closer. The speed of interface reaction is accelerated. The increase of temperature and heat generated by thermal reaction further promotes the thermal decomposition of SE, which results in oxygen generation. Furthermore, the thermal runaway occurs due to the further heat generation by Li-oxygen reactions. As a result, the reactions of Li and SEs are the origin of the thermal runaway of these types of SEs. This example demonstrates that SSBs are not absolutely safe when compared with conventional LIBs.

### B. Safety Performance Benchmarking With Conventional LIBs

In order to conduct the safety performance benchmarking of SSBs with conventional liquid-electrolyte LIBs, Charbonnel *et al.* [59] evaluated the safety of SSLBs with lithium lanthanum zirconium niobium oxide (LLZO) electrolytes. Fig. 6(a) and Fig. 6(b) show the characteristic curves of liquid-electrolyte LIB and LLZO-electrolyte SSB, respectively. The temperature

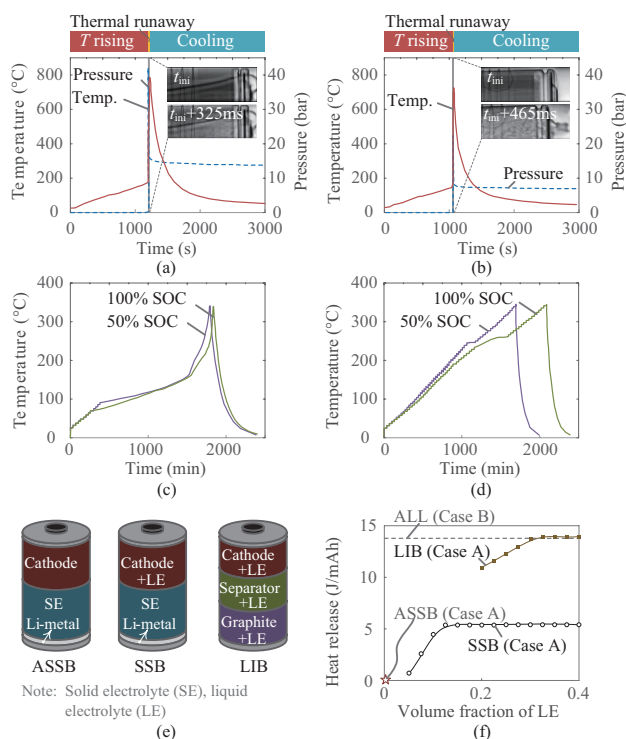


Fig. 6. Comparison of SSLBs and conventional liquid LIBs. (a) Thermal runaway procedure of a conventional LIB [59]. (b) Thermal runaway procedure of an SSB with LLZO electrolytes [59]. (c) Temperature versus time for thermal decomposition of Li/LiFePO<sub>4</sub> half-cells with liquid electrolytes [60]. (d) Temperature versus time for thermal decomposition of Li/LiFePO<sub>4</sub> half-cells with solid electrolytes [60]. (e) Typical configurations of all-solid-state batteries (ASSBs), SSBs, and LIBs [61]. (f) Heat-release results of different cells [61].

and pressure represent the surface temperature and gas pressure of battery cells during thermal runaway. There exist 3 stages in the safety test experiment. In the first stage, the batteries are heated and their temperature ( $T$ ) increases. Here, the pressures have almost no change. In the second stage, a thermal runaway occurs. The temperature increases rapidly. A large amount of gas is released and the pressure increases remarkably. The upper-right portions of Fig. 6(a) and Fig. 6(b) show the X-ray images of cells, where  $t_{mi}$  indicates the initial instant of thermal runaway. It can be seen that the internal of cells have changed after the thermal runaway. In the third stage, the temperature and pressure start to decrease, which indicates the end of the thermal runaway procedure.

Based on the thermal runaway experiment, Table II summarizes the critical parameters of battery cells. Here,  $T_{ini}$ ,  $T_{max}$  represent the initial temperature and maximum temperature during thermal runaway.  $Q$ ,  $n_{gas}$ , and  $t_{TR}$  denote the heat release, gas quantity, and duration of thermal runaway. Referring to Fig. 6(a), Fig. 6(b) and Table II, it can be seen that  $T_{ini}$ ,  $T_{max}$ ,  $Q$ ,  $n_{gas}$ , and  $t_{TR}$  of liquid-electrolyte LIB are slightly larger than that of SSLB.

For different types of SSLB, similar conclusions can be found. In [60], the heat release of Li/LiFePO<sub>4</sub> half-cell with solid polymer electrolyte and liquid electrolyte are analyzed. Fig. 6(c) and Fig. 6(d) show the experimental results of these two half cells using an accelerating rate calorimeter (ARC). It

TABLE II  
TYPICAL TEST DATA OF SSB CELLS AND LIB CELLS REPORTED IN [50]

Type	$T_{ini}/^{\circ}\text{C}$	$T_{max}/^{\circ}\text{C}$	$Q/\text{kJ}$	$n_{\text{gas}}/\text{mmol}$	$t_{\text{TR}}/\text{ms}$
LIB	159	821	78.5	262	329
SSB	148	813	69.8	156	191

TABLE III  
EXAMPLE OF SAFETY TEST STANDARD FOR BATTERIES [54]

Type	Test subject	Description
Cell	Over discharge	Discharge for 90 min
	Over charge	Constant-current charge to 115% SOC
	External short circuit	Connect the positive and negative terminals for 10 minutes
	Heating	Increase the temperature to $130 \pm 2^{\circ}\text{C}$ with a rate of $5^{\circ}\text{C}/\text{min}$ , then hold the temperature for 30 minutes
	Temperature cycling	Set the temperature like Fig. 7(a) for 5 times
	Crush	Hold a pressure (e.g., 100 kN) for 10 minutes
Pack	Vibration	Set the random vibration parameters like Fig. 7(b) for 12 h
	Mechanical shock	Half-sine wave in $\pm z$ direction for 6 times, the accelerated speed is 7g and the pulse time is 6 ms
	Crash	Crash simulation, the accelerated speed is like Fig. 7(c)
	Crush	Similar to that for cells
	Hygrothermal cycle	Set the humidity and temperature like Fig. 7(d) and 7(e) for 5 times
	Immersion	Immerse in water for 30 minutes
	External fire	Directly exposed to flame for 70 s, then indirectly exposed for 60 s using a fire-resistant partition
	Thermal runaway	External heating or using nail penetration test
	Thermal shock	Set temperature variation between $-40 \pm 2^{\circ}\text{C}$ and $60 \pm 2^{\circ}\text{C}$ for 5 times
	Salt spray	Salt spray test for 8 h, then stewing 16 h for 6 times
High altitude	Set atmospheric pressure as 61.2 kPa for 5 h	

is found that the time to reach the maximum temperature of the solid-electrolyte cell is longer than that for liquid-electrolyte cells.

Notice that the thermal runaway results in Fig. 6(a)–(d) are caused by an external heat source, short-circuit failure also needs to be considered. In [61], thermodynamic models of all-solid-state batteries (ASSBs), SSBs, and LIBs are built to analyze their safety performance. Here, SSB refers to batteries that use a solid electrolyte with some amount of liquid electrolyte (LE), while ASSB refers to cells with no liquid electrolyte, as shown in Fig. 6(e). Considering two typical failure conditions, Fig. 6(f) shows the calculation results of heat release, where the horizontal axis represents the volume fraction of LE in batteries. Case A and Case B represent the thermal runaway resulting from an external heat source and short-circuit failure due to dendrite penetration of the electrolyte, respectively. It can be seen that the heat release of LIBs is larger than that of SSBs for Case A, and there is no heat release of ASSBs. These theoretical results are consistent with the experimental results in Fig. 6(a)–(d). For Case B, it is found that the results of these three types of cells are the same, which demonstrates the short circuit failures procedure the same heat release.

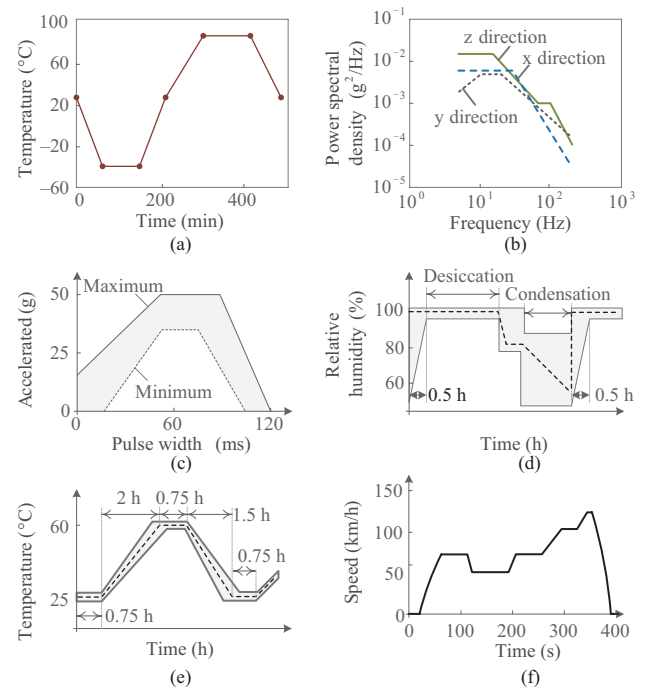


Fig. 7. Example of safety test standards and mission-profile-based methods for batteries. (a) Temperature cycling curve for cells [63]. (b) Vibration test curve [63]. (c) Schematic diagram of tolerance range of simulated collision pulse [63]. (d) Humidity cycle curve [63]. (e) Temperature cycling curve for packs [63]. (f) Example of mission profile in EVs [4].

These above-mentioned analyses demonstrate that the heat release of solid-electrolyte cells is slightly lower than that of liquid-electrolyte cells with an external heat source. However, it is not rigorous to draw a conclusion that solid-electrolyte batteries are safer than liquid-electrolyte batteries. Solid-electrolyte batteries need to be further developed.

#### IV. SAFETY ENHANCEMENT TECHNIQUES FOR BATTERIES

Nowadays, various safety enhancement techniques including materials modification, electrothermal management, etc., have been presented for conventional LIBs. Considering solid-state batteries are still in the development stage, the state-of-the-art safety enhancement techniques designed for LIBs are discussed in this section, in order to provide a reference for SSBs in the current stage. Notice that researchers in the fields of electronic and electrical engineering would pay more attention to electrical-related techniques including failure analysis, state estimation, cell balancing, etc., which are focused on in this section. Moreover, detailed discussions about protection, cell balancing, and lifetime improvement for LIBs are given in [62], we refer the reader to [62] for more detailed information.

##### A. Test Methods for Safety Evaluation

###### 1) Safety Test Standards and Mission-Profile Based Methods

In order to evaluate the safety performance of batteries, some safety test standards have been established for commercial batteries, such as GB 38301 [63], GB 40165 [64],

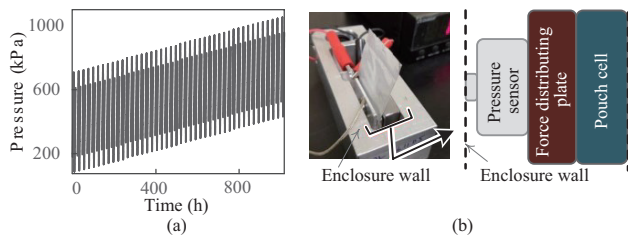


Fig. 8. Example of volume change of batteries [70]. (a) Surface pressure versus aging time for a pouch cell. (b) Experimental setup.

IEC 62133 [65], and UL 1642 [66]. Although these standards are designed for conventional LIBs, they can provide a reference for assessing SSBs at the current stage. Taking GB 38301 (standard for electric vehicles traction battery safety requirements) as an example, Table III shows the test subjects for battery cells and packs (or systems) [63], where the diagrams of temperature test, vibration test, etc., are given in Fig. 7(a)–(e).

Although the safety performance of batteries can be obtained following the above-mentioned standards, the real operating conditions cannot be reflected. Nowadays, the state-of-the-art mission-profile-based accelerated testing methods have been introduced for power electronic components and systems [67]–[69], which can be used for aging test of SSBs. A typical example of operation mission profile for EV systems is shown in Fig. 7(f) [4]. By designing a suitable power electronic circuit, the actual mission profile of SSBs can be simulated.

## 2) Characterization Methods

As discussed in Part A of Section III, with the degradation of SSBs, some electrical parameters and non-electrical parameters are changed. Besides the capacity, impedance, internal structure, and temperature, other parameters also can be used to characterize the state of batteries, such as volume. Taking a pouch cell as an example, Fig. 8(a) shows the relationship between surface pressure and aging time [70]. Here, the pressure is measured using a pressure sensor, which can reflect the volume change of batteries, as shown in Fig. 8(b). The experimental results demonstrate that the volume is also an indicator of batteries.

On the other hand, Fig. 4(d) and 4(f) show examples of scanning electron microscopy (SEM) images, which are widely used for the characterization of SSBs [71], [72]. Besides SEM, some *in situ* characterization methods are also can be used, such as X-ray photoelectron spectroscopy (XPS) [73], soft X-ray absorption spectroscopy (sXAS) [74], and neutron depth profiling (NDP) [75] measurement. Generally, the failure mechanism of SSBs can be investigated by using these state-of-the-art characterization methods.

## B. Battery Protection and Cell Balancing

### 1) Battery Protection

Similar to LIB systems, there may exist faults in SSLB systems (e.g., overvoltage, undercharge, short circuits,

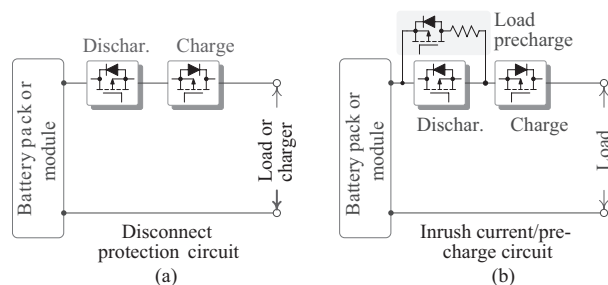


Fig. 9. Example of battery protection circuits [62], [76]. (a) Disconnect protection. (b) Inrush current/pre-charge protection.

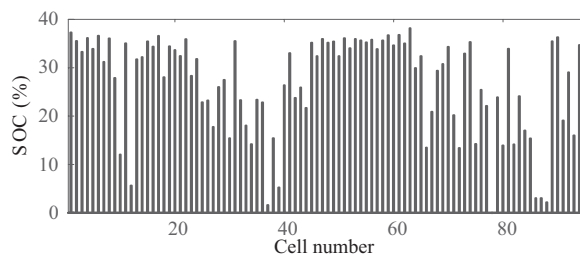


Fig. 10. Example of SOC distribution of cells in EVs after discharging [78].

overheating), which results in the demand for protection circuits. Fig. 9(a) shows a typical protection circuit for a battery system, which is also called disconnection protection [76]. Here, two MOSFETs are connected in series to form a bidirectional switch [77], and they are enabled to disconnect the circuit when a fault occurs. Generally, the charge MOSFET is used to control the flow of the charging current, and the discharge one controls the discharging current. Notice that the MOSFETs in Fig. 9(a) are placed on the high side (i.e., the positive terminal of batteries), they can also be placed on the low side (i.e., the negative terminal of batteries). Moreover, separate charge and discharge ports can also be designed for charge and discharge, respectively, which are detail discussed in [76].

Besides disconnection protection, a load inrush current protection circuit is required in a battery system, in order to limit the inrush current during the turn on phase. A typical protection circuit is shown in Fig. 9(b) [76].

### 2) Cell Balancing

Usually, the terminal voltage of a single battery cell is relatively low, a large number of cells are usually connected in series to meet the higher voltage demand of practical applications, such as EVs and BSEEs. However, there exist differences in cells due to manufacturing inconsistencies, and the differences will increase with the use of the batteries, which may result in overcharge and over-discharge. Taking the series-connected cells in EVs as an example, Fig. 10 shows the state of charge (SOC) distribution of cells after discharging [78]. Here, the cells have been utilized for 3 years. It can be seen that some cells are over discharge. Generally, the over-discharge and over charge caused by cell inconsistencies may result in premature degradation and safety issues of cells [79].



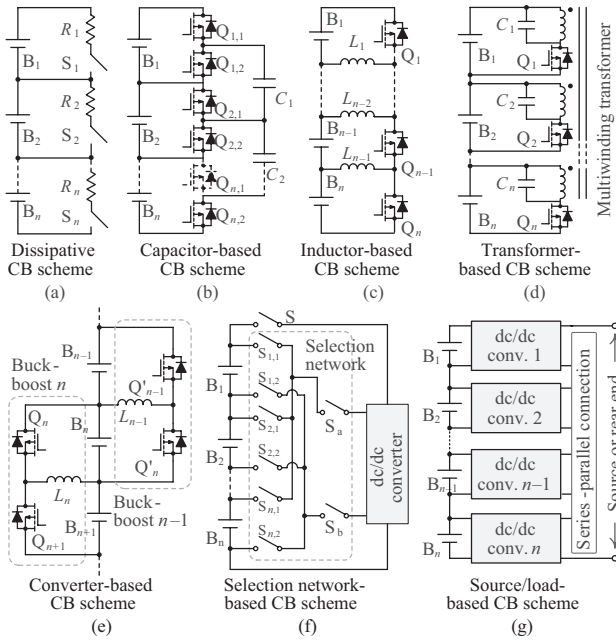


Fig. 11. Typical examples of cell balancing (CB) schemes [62]. (a) Dissipative CB scheme [62], [80]. (b) Capacitor-based CB scheme [62], [81]. (c) Inductor-based CB scheme [62], [82]. (d) Transformer-based CB scheme [62], [83]. (e) Converter-based CB scheme [62], [84]. (f) Selection network-based CB scheme [62], [85]. (g) Source/load-based CB scheme [62], [86].

Therefore, it is essential to design a cell balancing (CB) circuit to reduce the difference between cells.


Fig. 11(a) shows a widely used CB circuit, i.e., dissipative CB scheme [80]. Although it has the advantage of low complexity, the extra energy on cells is consumed by resistance. The efficiency is relatively low, and it may cause heat problems for batteries. Considering this issue, various CB schemes including capacitor-based schemes [81], inductor-based schemes [82], transformer-based schemes [83], converter-based schemes [84], selection network-based schemes [85], and source/load-based schemes [86] have been presented. Typical examples are shown in Fig. 11. Notice that the examples in Fig. 11 are basic circuits, various improved schemes can be derived based on them. Detailed discussions can be found in [87], [88].

### C. State Estimation

#### 1) Typical State Estimation Methods

State estimation mainly refers to using voltage and current information of batteries or systems to estimate the key state of batteries, such as SOC, state of health (SOH), state of safety (SOS), state of power (SOP), state of energy (SOE), and state of temperature (SOT). Recently, various state estimation methods have been presented [89]–[92], which can be mainly divided into two categories, i.e., model-based methods and data-driven methods, as shown in Fig. 12.

Fig. 12(a) shows the typical procedure of model-based methods, which mainly includes two steps, i.e., battery modeling and parameter identifications [89], [90]. Firstly, a parameter model of batteries is built. Then, the parameters are

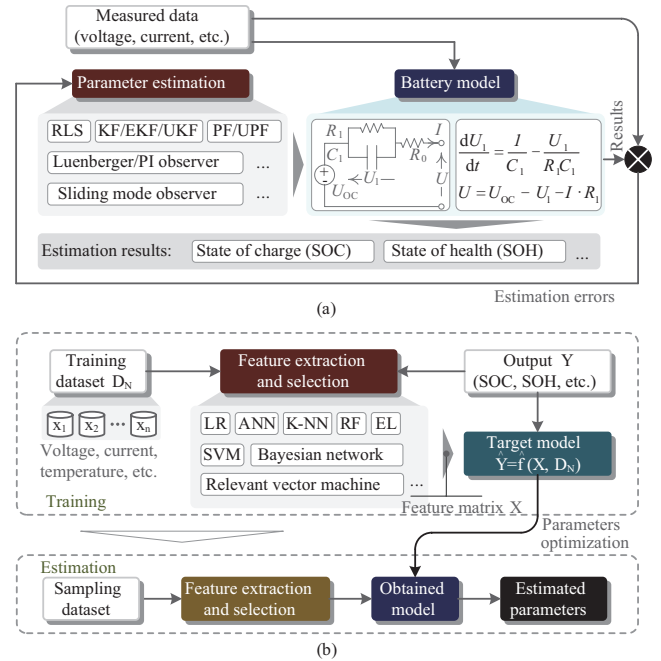


Note 1: Recursive least square (RLS), Kalman filtering (KF), extended KF(EKF), unscented KF (UKF), proportional integral (PI), linear regression (LR), artificial neural network (ANN), k-nearest neighbor regression (k-NN), randomforest (RF), ensemble learning (EL), support vector machine (SVM).

Note 2: The battery model in Fig. (a) is just for illustration. Actually, many different equivalent circuit models exist for different battery types.  $U_{oc}$ ,  $R_0$ ,  $R_1$ ,  $C_1$ ,  $U_1$  represent open-circuit voltage, ohmic resistance, polarization resistance, polarization capacitance, and polarization voltage, respectively.  $U$  and  $I$  denote terminal voltage and loop current, respectively.

Fig. 12. Typical state estimation methods for batteries. (a) Model-based method [89], [90]. (b) Data-driven method [91], [92].

estimated using parameters identification algorithms, such as recursive least square (RLS), Kalman filtering (KF), extended KF (EKF), unscented KF (UKF), proportional-integral (PI) observer, sliding mode observer, etc. [89], [90], [93]. Notice that the parameter model in Fig. 9(a) is the basic Thevenin model, which is an equivalent circuit model. Besides it, more complex second-order RC equivalent circuits, and fractional-order equivalent circuit models are also widely used for LIBs [94]. Moreover, physics-based models can effectively simulate the internal electrochemical reactions of batteries, which are also widely used in state estimation [95]. For SSLBs, physics-based models have been drawing great attention [96], [97]. Fig. 13 shows an example of a physic model of Li metal SSB [97]. Based on the method shown in Fig. 12(a), the state parameters of SSBs can be estimated.

Fig. 12(b) shows the typical procedure of data-driven methods, which mainly consist of two parts, i.e., the data training and parameters estimation. Firstly, raw data (e.g., voltage, current, temperature, etc.) and state information (e.g., SOC, SOH, aging data, etc.) of batteries are collected as training datasets [91], [92]. Then, some state-of-the-art artificial intelligence (AI) algorithms are used to obtain the target model, such as linear regression (LR), artificial neural network (ANN), k-nearest neighbor regression (k-NN), random forest (RF), ensemble learning (EL), support vector machine (SVM), etc. [91], [92]. According to the obtained estimation model, the

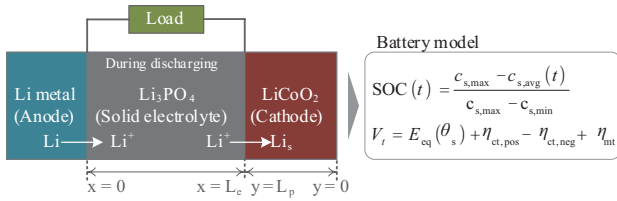

Note 1: The SSB is seen as a sandwich consisting of an anode (Li metal), a solid electrolyte ( $\text{Li}_3\text{PO}_4$ ), and a cathode ( $\text{LiCoO}_2$ ). During discharge, metallic lithium is oxidized to  $\text{Li}^+$  ions at the negative electrode, and electrons are going to the external circuit.  $\text{Li}^+$  ions pass through the solid electrolyte, tetravalent cobalt is reduced to trivalent cobalt at the positive electrode.

Note 2:  $x$  and  $y$  are defined in the electrolyte and cathode regions, in order to derive the governing equations.  $L_c$  and  $L_p$  represent the values of  $x$  and  $y$ , respectively. SOC,  $t$ ,  $V_i$  denote the state of charge, time, and battery terminal voltage, respectively.  $c_s$ ,  $E_{eq}$ ,  $\theta_s$ ,  $\eta$  are the electrochemical parameters.

Fig. 13. Example of a physics-based model of SSBs [96].

parameters of models can be updated by actual data. Then, the state parameters can be obtained based on the built model and sampling datasets. Notice that the data training is performed offline, and the state estimation can be realized either offline or online.

## 2) Power Electronics-Based Online Monitoring

Electrochemical impedance spectroscopy (EIS) is related to the internal physical and chemical processes of batteries, which can be used to analyze the state information of batteries, such as SOC, SOH, temperature, overcharge, etc. [98]–[101]. Taking SOC and SOH as examples, Fig. 14(a) shows the relationships between EIS and SOC/SOH [98], which demonstrates that the EIS can reflect the state information of batteries.

Fig. 14(b) shows the typical test method of EIS. Usually, an excitation signal  $i_b$  (or  $v_b$ ) is injected into a battery, and the corresponding response signal  $v_b$  (or  $i_b$ ) is obtained. Then the impedance  $z(f)$  at each frequency  $f$  is calculated using the excitation signal and response signal, i.e.,

$$z(f) = v_b(f)/i_b(f) \quad (1)$$

where,  $v_b$  and  $i_b$  represent the voltage and current of batteries. Based on (1), the EIS of a battery can be obtained. Although EIS can be measured using industrial instruments including electrochemical workstations, spectrum analyzers, impedance analyzers, etc., it cannot realize the real-time measurement during battery operation.

It is well known that power electronic (PE) circuits are widely used in battery systems to realize the functions of energy interaction, cell balancing, and battery protection. PE-based online monitoring refers to utilizing the electrical signals of PE circuits to realize online EIS measurement. Generally, the PE-based EIS monitoring can be derived into two categories, i.e., converter signal-based methods and perturbation injection-based methods.

For converter signal-based methods, the EIS is measured using the existing multifrequency signal in converter systems, such as harmonic, ripple, etc. Taking a battery-feed electric-vehicle drive system as an example, Fig. 14(c) shows the

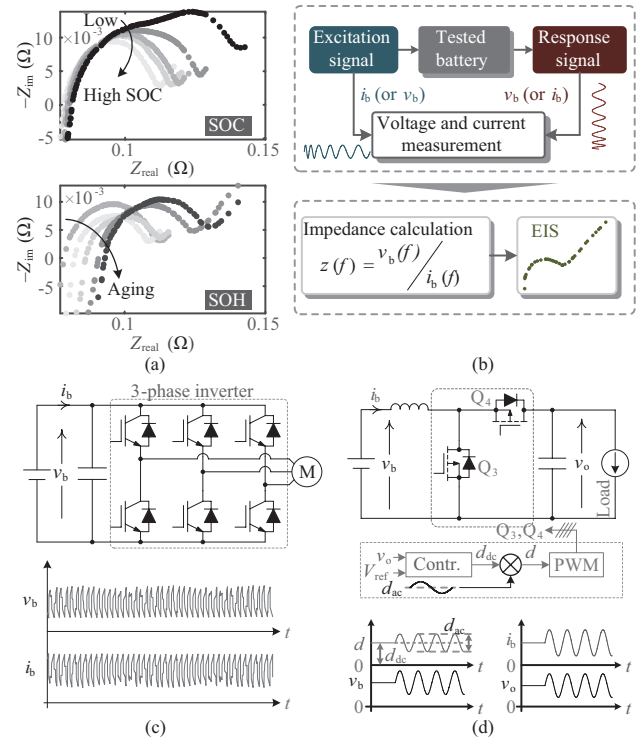


Fig. 14. Examples of EIS-based state estimation and power electronics-based EIS measurement [62]. (a) Example of EIS-based state estimation [62], [98]. (b) Typical EIS measurement method. (c) Interface converter-based EIS measurement [62], [102]. (d) Perturbation injection-based EIS measurement [62], [103].

circuit topology and typical waveforms of battery voltage  $v_b$  and battery current  $i_b$  [102]. It can be seen that  $v_b$  and  $i_b$  frequently vary due to driver or controller response, which generates abundant multifrequency information on batteries. Then, the EIS can be obtained using (1) and signal processing algorithms, such as fast Fourier transform (FFT).

For perturbation injection-based methods, perturbation signals are usually added to controllers or batteries, in order to generate multifrequency excitations. Fig. 14(d) shows an implementation example, where a buck-boost converter is used to realize the energy interaction between battery and load [103]. Here, a small perturbation signal is added to the steady-state duty cycle, which results in generating a perturbation superimposed over the battery voltage  $v_b$  and battery current  $i_b$ . Similarly, the broadband excitation signal batteries can be generated by adding a perturbation to the reference point of converters [104]. Moreover, the perturbation current can also directly add to batteries by specially designed converters [105], [106].

Besides the interface converters, cell balancing circuits also can be used for online EIS measurement [107]–[109]. Notice that converter signal-based methods are more suitable for battery-feed adjustable speed drive (ASD) systems, such as EVs, due to there exist abundant frequency information (including ripple, harmonic, and loading profile) in the system. For other applications without abundant frequency information (e.g., BESSs), perturbation injection-based methods are more suitable.

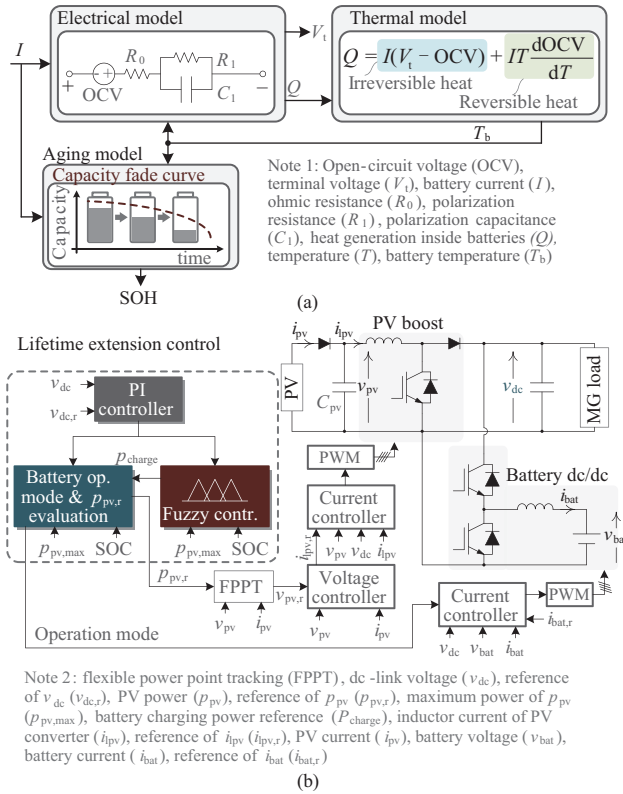


Fig. 15. Electrothermal-aging coupling model of a LIB and example of a lifetime improvement scheme. (a) Electrothermal-aging coupling model of a LIB [62], [117]. (b) Example of a lifetime improvement scheme [62], [118].

#### D. Lifetime Improvement

Generally, the lifetime of batteries is affected by electrical stress, such as ripples, harmonics, and charging/discharging strategies. Recent studies have demonstrated that high-frequency (greater than 10 Hz) ripples and harmonics almost have no adverse influence on LIBs' lifetime when the root mean square (RMS) values of ripples/harmonics are equal to a dc current [110], [111]. From the perspective of charging strategies, it is demonstrated that the lifetime of batteries is dependent on the RMS value of the charging current, which is not related to the charging profile [112], such as constant current-constant voltage (CC-CV) charging [113], pulse-current (PC) charging [114], and sinusoidal ripple current (SRC) charging [115].

Although it is essential to reduce the RMS value of the charging current from the perspective of safety, it may reduce other performances of batteries (e.g., charging speed). Therefore, a tradeoff between safety, speed, etc., should be considered. In [116], an electrothermal-aging coupling model of a LIB is built, as shown in Fig. 15(a). Then the optimal charging parameters are obtained using a multi-objective biogeography-based optimization algorithm, which guarantees safety and charging speed at the same time. Similar charging optimization schemes can be found in [117].

From the perspective of operation, the lifetime of batteries can be improved by specially designed control strategies.

Referring to the example shown in Fig. 15(b) [118], a fuzzy logic control algorithm is used to adjust the charging current and the PV is primarily employed, in order to reduce the stress of batteries and improve their lifetimes.

#### V. CONCLUSION

This paper reviews the advanced solid battery and its safety. First, the development of battery techniques and state-of-the-art solid-state batteries are discussed. Second, the main safety issues of solid-state lithium batteries (SSLBs) are summarized, including electrical parameters drift, internal structure change, and thermal runaway. Then, the safety performance of current-stage SSLBs is compared with conventional lithium-ion batteries (LIBs). Third, the existing safety enhancement techniques including safety test methods, battery protection, cell balancing, state estimation, and lifetime improvement for batteries have been discussed, which can be used for SSLBs. From the authors' point of view, future research challenges and research opportunities are summarized as follows.

#### A. Challenges

For solid-state batteries, the maximum challenge is that it is still in the development stage and there exist safety issues for current-stage quasi-solid-state batteries. From the perspective of battery applications instead of material design, the challenges are given in the following:

- 1) The failure behaviors and failure mechanisms of SSLBs are not very clear. There is a lack of accurate electrical models, thermal models, electrothermal models, electrochemical models, and lifetime models for current-stage SSLBs.
- 2) There is a lack of safety test standards for SSLBs.
- 3) The battery protection, cell balancing, state estimation, and lifetime improvement methods for SSLBs are referring to the existing methods for conventional LIBs. There is a lack of specially designed methods for SSLBs, which consider the characteristics of SSLBs.

#### B. Opportunities

The opportunities can be listed as follows:

- 1) Research safety/aging test methods and standards for SSLBs. The actual operating conditions of batteries should be considered, and mission-profile-based reliability test methods for power electronic reliability can be used as a reference [119].
- 2) Investigates electrical models, thermal models, electrothermal models, electrochemical models, lifetime models, etc., of SSLBs. Safety/realizability evaluation and improvement should be considered [119].
- 3) Designing of advanced state estimation and condition monitoring techniques for SSLBs. The state-of-the-art techniques for power electronic systems [120]–[123] and conventional LIB systems [124] can be used as references. Emerging artificial intelligence technology should be



considered [125].

- 4) Further research of protection and cell balancing circuits, on the basis of the schemes for conventional LIBs [62].
- 5) Designing of advanced charging and operating strategies on the basis of [117], [118], in order to improve the lifetimes of SSLBs.

## REFERENCES

- [1] J. Yang, R. Li, K. Ma, Y. Wang, and P. Xu, "Analysis and design of cascaded DC-DC converter based battery energy storage system with distributed multimode control in data center application," in *CPSS Transactions on Power Electronics and Applications*, vol. 7, no. 3, pp. 308–318, Sept. 2022.
- [2] M. T. Lawder, B. Suthar, P. W. C. Northrop, S. De, C. M. Hoff, O. Leitermann, M. L. Crow, S. Santhanagopalan, and V. R. Subramanian, "Battery energy storage system (BESS) and battery management system (BMS) for grid-scale applications," in *Proceedings of the IEEE*, vol. 102, no. 6, pp. 1014–1030, Jun. 2014.
- [3] I. Mexis and G. Todeschini, "Battery energy storage systems in the United Kingdom: a review of current state-of-the-art and future applications," in *Energies*, vol. 13, no. 14, Art. no. 3616, Jul. 2020.
- [4] F. Blaabjerg, H. Wang, I. Vernica, B. Liu, and P. Davari, "Reliability of power electronic systems for EV/HEV applications," in *Proceedings of the IEEE*, vol. 109, no. 6, pp. 1060–1076, Jun. 2021.
- [5] Y. Chen, Y. Kang, Y. Zhao, L. Wang, J. Liu, Y. Li, Z. Liang, X. He, X. Li, N. Tavajohi, *et al.*, "A review of lithium-ion battery safety concerns: the issues, strategies, and testing standards," in *Journal of Energy Chemistry*, vol. 59, pp. 83–99, Aug. 2021.
- [6] X. Feng, D. Ren, X. He, and M. Ouyang, "Mitigating thermal runaway of lithium-ion batteries," in *Joule*, vol. 4, no. 4, pp. 743–770, Mar. 2020.
- [7] *South Korea Identifies Top 4 Causes for ESS Fires*, Jun. 14, 2019. [Online]. Available: <https://liiontamer.com/south-korea-identifies-top-4-causes-that-led-to-ess-fires/>, Accessed: Nov. 2022.
- [8] P. Sun, R. Bisschop, H. Niu, and X. Huang, "A review of battery fires in electric vehicles," in *Fire Technology*, vol. 56, pp. 1361–1410, Jan. 2020.
- [9] Q. Wang, B. Jiang, B. Li, and Y. Yan, "A critical review of thermal management models and solutions of lithium-ion batteries for the development of pure electric vehicles," in *Renewable and Sustainable Energy Reviews*, vol. 64, pp. 106–128, Oct. 2016.
- [10] W. Wu, S. Wang, W. Wu, K. Chen, S. Hong, and Y. Lai, "A critical review of battery thermal performance and liquid based battery thermal management," in *Energy Conversion and Management*, vol. 182, pp. 262–281, Feb. 2019.
- [11] Y. Wang, J. Tian, Z. Sun, L. Wang, R. Xu, M. Li, and Z. Chen, "A comprehensive review of battery modeling and state estimation approaches for advanced battery management systems," in *Renewable and Sustainable Energy Reviews*, vol. 131, Art. no. 110015, Oct. 2020.
- [12] R. Xiong, W. Sun, Q. Yu, and F. Sun, "Research progress, challenges and prospects of fault diagnosis on battery system of electric vehicles," in *Applied Energy*, vol. 279, Art. no. 115855, Dec. 2020.
- [13] X. Hu, K. Zhang, K. Liu, X. Lin, S. Dey, and S. Onori, "Advanced fault diagnosis for lithium-ion battery systems: a review of fault mechanisms, fault features, and diagnosis procedures," in *IEEE Industrial Electronics Magazine*, vol. 14, no. 3, pp. 65–91, Sept. 2020.
- [14] K. Liu, Y. Liu, D. Lin, A. Pei, and Y. Cui, "Materials for lithium-ion battery safety," in *Science Advances*, vol. 4, no. 6, Art. no. eaas9820, Jun. 2018.
- [15] Q. Wang, L. Jiang, Y. Yu, and J. Sun, "Progress of enhancing the safety of lithium-ion battery from the electrolyte aspect," in *Nano Energy*, vol. 55, pp. 93–114, Jan. 2019.
- [16] M. Pastal, D. Armstrong, Z. L. Brown, J. Bu, M. R. Castell, P. Chen, A. Cocks, S. A. Corr, E. J. Cussen, and E. Dambrough, "2020 roadmap on solid-state batteries," in *Journal of Physics: Energy*, vol. 2, no. 3, Art. no. 032008, Aug. 2020.
- [17] J. G. Kim, B. Son, S. Mukherjee, N. Schuppert, A. Bates, O. Kwon, M. J. Choi, H. Y. Chung, and S. Park, "A review of lithium and non-lithium based solid state batteries," in *Journal of Power Sources*, vol. 282, pp. 299–322, May 2015.
- [18] J. Ma, B. Chen, L. Wang, and G. Cui, "Progress and prospect on failure mechanisms of solid-state lithium batteries," in *Journal of Power Sources*, vol. 392, pp. 94–115, Jul. 2018.
- [19] J. Liu, H. Yuan, H. Liu, C. Zhao, Y. Lu, X. Cheng, J. Huang, and Q. Zhang, "Unlocking the failure mechanism of solid-state lithium metal batteries," in *Advanced Energy Materials*, vol. 12, no. 4, Art. no. 2100748, Jun. 2021.
- [20] R. Chen, Q. Li, X. Yu, L. Chen, and H. Li, "Approaching practically accessible solid-state batteries: stability issues related to solid electrolytes and interfaces," in *Chemical Reviews*, vol. 120, no. 14, pp. 6820–6877, Nov. 2019.
- [21] Y. Guo, S. Wu, Y. -B. He, F. Kang, L. Chen, H. Li, and Q. -H. Yang, "Solid-state lithium batteries: safety and prospects," in *eScience*, vol. 2, no. 2, pp. 138–163, Mar. 2022.
- [22] X. Feng, M. Ouyang, X. Liu, L. Lu, Y. Xia, and X. He, "Thermal runaway mechanism of lithium-ion battery for electric vehicles: A review," in *Energy Storage Materials*, vol. 10, pp. 246–267, Jan. 2018.
- [23] W. Gao, X. Li, M. Ma, Y. Fu, J. Jiang, and C. Mi, "Case study of an electric vehicle battery thermal runaway and online internal short-circuit detection," in *IEEE Transactions on Power Electronics*, vol. 36, no. 3, pp. 2452–2455, Mar. 2021.
- [24] C. Zheng, L. Li, K. Wang, C. Wang, J. Zhang, Y. Xia, H. Huang, C. Liang, Y. Gan, X. He, *et al.*, "Interfacial reactions in inorganic all-solid-state lithium batteries," in *Batteries & Supercaps*, vol. 4, no. 1, pp. 8–38, Jan. 2021.
- [25] J. Wu and X. Yao, "Recent progress in interfaces of all-solid-state lithium batteries based on sulfide electrolytes," in *Energy Storage Science and Technology*, vol. 9, no. 2, pp. 501–514, Mar. 2020.
- [26] J. Haruyama, K. Sodeyama, L. Han, K. Takada, and Y. Tateyama, "Space-charge layer effect at interface between oxide cathode and sulfide electrolyte in all-solid-state lithium-ion battery," in *Chemistry of Materials*, vol. 26, no. 14, pp. 4248–4255, Jul. 2014.
- [27] J. Zhang, C. Zheng, L. Li, Y. Xia, H. Huang, Y. Gan, C. Liang, X. He, X. Tao, and W. Zhang, "Unraveling the intra and intercycle interfacial evolution of  $\text{Li}_6\text{PS}_5\text{Cl}$ -based all-solid-state lithium batteries," in *Advanced Energy Materials*, vol. 10, no. 4, Art. no. 1903311, Jan. 2020.
- [28] R. Koerver, I. Aygün, T. Leichtwei, C. Dietrich, W. Zhang, J. O. Binder, P. Hartmann, W. G. Zeier, and J. Janek, "Capacity fade in solid-state batteries: interphase formation and chemomechanical processes in nickel-rich layered oxide cathodes and lithium thiophosphate solid electrolytes," in *Chemistry Materials*, vol. 29, no. 13, pp. 5574–5582, Jun. 2017.
- [29] A. Sakuda, A. Hayashi, and M. Tatsumisago, "Interfacial observation between  $\text{LiCoO}_2$  electrode and  $\text{Li}_2\text{S}-\text{P}_2\text{S}_5$  solid electrolytes of all-solid-state lithium secondary batteries using transmission electron microscopy," in *Chemistry Materials*, vol. 22, no. 3, pp. 949–956, Sep. 2009.
- [30] *Solid Cell*. Beijing, China: Beijing WeLion New Energy Technology Co., Ltd., 2022. [Online]. Available: <http://www.solidstatelion.com>.
- [31] *Solid state lithium battery*. Jiangxi, China: Ganfeng LiEnergy technology Co., Ltd., 2022. [Online]. Available: [http://www.ganfengbattery.com/index\\_en.html](http://www.ganfengbattery.com/index_en.html).
- [32] M. J. Wang, E. Kazyak, N. P. Dasgupta, and J. Sakamoto, "Transitioning solid-state batteries from lab to market: linking electro-chemo-mechanics with practical considerations," in *Joule*, vol. 5, no. 6, pp. 1371–1390, Jun. 2021.
- [33] N. Boaretto, I. Garbayo, S. Valiyaveetil-SobhanRaj, A. Quintela, C. Li, M. Casas-Cabanas, and F. Aguesse, "Lithium solid-state batteries: state-of-the-art and challenges for materials, interfaces and processing," in *Journal of Power Sources*, vol. 502, Art. no. 229919, Aug. 2021.
- [34] C. Li, Z. Wang, Z. He, Y. Li, J. Mao, K. Dai, C. Yan, and J. Zheng, "An advance review of solid-state battery: challenges, progress and prospects," in *Sustainable Materials and Technologies*, vol. 29, Art. no. e00297, Sep. 2021.
- [35] A. Manthiram, X. Yu, and S. Wang, "Lithium battery chemistries enabled by solid-state electrolytes," in *Nature Reviews Materials*, vol. 2, Art. no.



- 16103, Feb. 2017.
- [36] J. Wu, J. Yang, G. Liu, Z. Wang, Z. Zhang, H. Yu, X. Yao, and X. Huang, "Review and prospective of solid-state lithium batteries in the past decade (2011–2021)," in *Energy Storage Science and Technology*, vol. 11, no. 9, pp. 2713–2745, Sep. 2020.
- [37] S. Randau, D. A. Weber, O. Kötz, R. Koerver, P. Braun, A. Weber, E. Ivers-Tiffée, T. Adermann, J. Kulisch, W. G. Zeier, *et al.*, "Benchmarking the performance of all-solid-state lithium batteries," in *Nature Energy*, vol. 5, pp. 259–270, Mar. 2020.
- [38] C. Yu, F. Zhao, J. Luo, L. Zhang, and X. Sun, "Recent development of lithium argyrodite solid-state electrolytes for solid-state batteries: Synthesis, structure, stability and dynamics," in *Nano Energy*, vol. 83, Art. no. 105858, Mar. 2021.
- [39] *Are Solid-State Cells Safer?* Solid Power, Louisville, KY, USA. [Online]. Available: <https://www.solidpowerbattery.com/solid-state-safety/>
- [40] *Product testing*. WeLion New Energy Technology Co., Ltd., Beijing, China. [Online]. Available: [http://www.solidstatelion.com/product\\_page/9.html](http://www.solidstatelion.com/product_page/9.html)
- [41] J. Lou, G. Wang, Y. Xia, C. Liang, H. Huang, Y. Gan, X. Tao, J. Zhang, and W. Zhang, "Achieving efficient and stable interface between metallic lithium and garnet-type solid electrolyte through a thin indium tin oxide interlayer," in *Journal of Power Sources*, vol. 448, Art. no. 227440, Feb. 2020.
- [42] C. Zheng, J. Zhang, Y. Xia, H. Huang, Y. Gan, C. Liang, X. He, X. Tao, and W. Zhang, "Unprecedented self-healing effect of  $\text{Li}_6\text{PS}_4\text{Cl}$ -based all-solid-state lithium battery," in *Small*, vol. 17, no. 37, Art. no. 2101326, Sep. 2021.
- [43] J. Auvergniot, A. Cassel, J. Ledeuil, V. Viallet, V. Seznec, and R. Dedryvere, "Interface stability of argyrodite  $\text{Li}_6\text{PS}_4\text{Cl}$  toward  $\text{LiCoO}_2$ ,  $\text{LiNi}_{1/3}\text{Co}_{1/3}\text{Mn}_{1/3}\text{O}_2$ , and  $\text{LiMn}_2\text{O}_4$  in bulk all-solid-state batteries," in *Chemistry Materials*, vol. 29, no. 9, pp. 3883–3890, Apr. 2017.
- [44] A. Hayashi, R. Ohtsubo, T. Ohtomo, F. Mizuno, and M. Tatsumisago, "All-solid-state rechargeable lithium batteries with  $\text{Li}_2\text{S}$  as a positive electrode material," in *Journal of Power Sources*, vol. 183, no. 1, pp. 422–426, Aug. 2007.
- [45] K. Zhu, Y. Liu, and J. Liu, "A fast charging/discharging all-solid-state lithium ion battery based on PEO-MIL-53(Al)-LiTFSI thin film electrolyte," in *RSC Advances*, vol. 80, no. 4, pp. 42278–42284, Jun. 2014.
- [46] J. Zhang, J. Zhao, L. Yue, Q. Wang, J. Chai, Z. Liu, X. Zhou, H. Li, Y. Guo, G. Cui, *et al.*, "Safety-reinforced poly (propylene carbonate)-based all-solid-state polymer electrolyte for ambient-temperature solid polymer lithium batteries," in *Advanced Energy Materials*, vol. 5, no. 24, Art. no. 1501082, Oct. 2015.
- [47] G. Oh, M. Hirayama, O. Kwon, K. Suzuki, and R. Kanno, "Bulk-type all solid-state batteries with 5 V class  $\text{LiNi}_{0.5}\text{Mn}_{1.5}\text{O}_4$  cathode and  $\text{Li}_6\text{GeP}_2\text{S}_{12}$  solid electrolyte," in *Chemistry Materials*, vol. 28, no. 8, pp. 2634–2640, Apr. 2016.
- [48] N. Boaretto, A. Bittner, C. Brinkmann, B. -E. Olsowski, J. Schulz, M. Seyfried, K. Vezzù, M. Popall, and V. D. Noto, "Highly conducting 3d-hybrid polymer electrolytes for lithium batteries based on siloxane networks and cross-linked organic polar interphases," in *Chemistry Materials*, vol. 26, no. 22, pp. 6339–6350, Nov. 2014.
- [49] C. Brissot, M. Rosso, J. Chazalviel, and S. Lascaud, "Dendritic growth mechanisms in lithium/polymer cells," in *Journal of Power Sources*, vol. 81, pp. 925–929, Sep. 1999.
- [50] M. Dollé, L. Sannier, B. Beaudoin, M. Trentin, and J. Tarascon, "Live scanning electron microscope observations of dendritic growth in lithium/polymer cells," in *Electrochemical and Solid-State Letters*, vol. 5, no. 12, pp. 286–289, Oct. 2002.
- [51] E. J. Cheng, A. Sharafi, and J. Sakamoto, "Intergranular Li metal propagation through polycrystalline  $\text{Li}_{6.25}\text{Al}_{0.25}\text{La}_3\text{Zr}_2\text{O}_{12}$  ceramic electrolyte," in *Electrochimica Acta*, vol. 223, pp. 85–91, Jan. 2017.
- [52] N. G. Yadav, N. Folastre, M. Bolmont, A. Jamali, M. Morcrette, and C. Davoisne, "Study of failure modes in two sulphide-based solid electrolyte all-solid-state batteries via in situ SEM," in *Journal of Materials Chemistry A*, vol. 10, no. 33, pp. 17142–17155, July 2022.
- [53] F. Sun, K. Dong, M. Osenberg, A. Hilger, S. Risse, Y. Lu, P. H. Kamm, M. Klaus, H. Markötter, F. García-Moreno, *et al.*, "Visualizing the morphological and compositional evolution of the interface of InLi-anode/thio-LISION electrolyte in an all-solid-state Li-S cell by in operando synchrotron X-ray tomography and energy dispersive diffraction," in *Journal of Materials Chemistry A*, vol. 6, pp. 22489–22496, Oct. 2018.
- [54] N. Sun, Q. Liu, Y. Cao, S. Lou, M. Ge, X. Xiao, W. -K. Lee, Y. Gao, G. Yin, J. Wang, *et al.*, "Anisotropically electrochemical-mechanical evolution in solid-state batteries and interfacial tailored strategy" in *Angewandte Chemie*, vol. 131, no. 51, pp. 18820–18826, Oct. 2019.
- [55] W. Zhang, D. Schröder, T. Arlt, I. Manke, R. Koerver, R. Pinedo, D. A. Weber, J. Sann, W. G. Zeier, and J. Janek, "(Electro)chemical expansion during cycling: monitoring the pressure changes in operating solid-state lithium batteries," in *Journal Materials Chemistry A*, vol. 5, no. 20, pp. 9929–9936, Mar. 2017.
- [56] Y. Wu, S. Wang, H. Li, L. Chen, and F. Wu, "Progress in thermal stability of all solid-state-Li-ion-batteries," in *InfoMat*, vol. 3, no. 8, pp. 827–853, Jun. 2021.
- [57] R. Chen, A. M. Nolan, J. Lu, J. Wang, X. Yu, Y. Mo, L. Chen, X. Huang, and H. Li, "The thermal stability of lithium solid electrolytes with metallic lithium", in *Joule*, vol. 4, no. 4, pp. 812–821, Apr. 2020.
- [58] L. Huang, T. Lu, G. Xu, X. Zhang, Z. Jiang, Z. Zhang, Y. Wang, P. Han, G. Cui, and L. Chen, "Thermal runaway routes of large-format lithium-sulfur pouch cell batteries," in *Joule*, vol. 6, no. 4, pp. 906–922, Apr. 2022.
- [59] J. Charbonnel, N. Darmet, C. Deilhes, L. Broche, M. Reytier, P. -X. Thivel, and R. Vincent, "Safety evaluation of all-solid-state batteries: an innovative methodology using in situ synchrotron X-ray radiography," in *ACS Applied Energy Materials*, vol. 5, no. 9, pp. 10862–10871, Sep. 2022.
- [60] A. Perea, M. Dontigny, and K. Zaghib, "Safety of solid-state Li metal battery: solid polymer versus liquid electrolyte," in *Journal of Power Sources*, vol. 359, no. 15, pp. 182–185, Aug. 2017.
- [61] A. M. Bates, Y. Preger, L. Torres-Castro, K. L. Harrison, S. J. Harris, and J. Hewson, "Are solid-state batteries safer than lithium-ion batteries," in *Joule*, vol. 6, no. 4, pp. 742–755, Apr. 2022.
- [62] Z. Zhao, H. Hu, Z. He, H. H. -C. Iu, P. Davari, and F. Blaabjerg, "Power electronics-based safety enhancement technologies for lithium-ion batteries: an overview from battery management perspective," in *IEEE Transactions on Power Electronics*, vol. 38, no. 7, pp. 8922–8955, Jul. 2023.
- [63] *Electric vehicles traction battery safety requirements*, National Standard of the People's Republic of China GB 38031, 2020.
- [64] *Lithium-ion cells and batteries used in stationary electronic equipments—Safety technical specification*, National Standard of the People's Republic of China GB 40165, 2021.
- [65] *Secondary cells and batteries containing alkaline or other non-acid electrolytes—Safety requirements for portable sealed secondary cells, and for batteries made from them, for use in portable applications*, IEC Standard IEC 62133-2, 2021.
- [66] *Standard for safety—Lithium batteries*, UL Standard UL 1642, 2020.
- [67] A. Sangwongwanich, Y. Shen, A. Chub, E. Liivik, D. Vinnikov, H. Wang, and F. Blaabjerg, "Design for accelerated testing of DC-link capacitors in photovoltaic inverters based on mission profiles," in *IEEE Transactions on Industry Applications*, vol. 57, no. 1, pp. 741–753, Jan.-Feb. 2021.
- [68] Z. Zhao, D. Zhou, P. Davari, J. Fang, and F. Blaabjerg, "Reliability analysis of capacitors in voltage regulator modules with consecutive load transients," in *IEEE Transactions on Power Electronics*, vol. 36, no. 3, pp. 2481–2487, Mar. 2021.
- [69] Z. Zhao, D. Zhou, H. Wang, P. Davari, and F. Blaabjerg, "Reliability improvement of voltage regulator modules by a virtual series voltage source," in *IEEE Transactions on Industrial Electronics*, vol. 69, no. 12, pp. 12641–12652, Dec. 2022.
- [70] A. Louli, J. Li, S. Trussler, C. Fell, and J. Dahn, "Volume, pressure and thickness evolution of Li-ion pouch cells with silicon-composite negative electrodes," in *Journal of The Electrochemical Society*, vol. 164, no. 12, pp. A2689–A2696, Sep. 2017.
- [71] T. Yang, C. Wang, W. Zhang, Y. Xia, Y. Gan, H. Huang, X. He, and J. Zhang, "Composite polymer electrolytes reinforced by a three-dimensional polyacrylonitrile/ $\text{Li}_{0.33}\text{La}_{0.57}\text{TiO}_3$  nanofiber framework for room-temperature dendrite-free all-solid-state lithium metal battery," in

- Rare Metals*, vol. 41, no. 6, pp. 1870–1879, Jan. 2022.
- [72] C. Wang, T. Yang, W. Zhang, H. Huang, Y. Gan, Y. Xia, X. He, and J. Zhang, “Hydrogen bonding enhanced SiO<sub>2</sub>/PEO composite electrolytes for solid-state lithium batteries,” in *Journal of Materials Chemistry A*, vol. 10, pp. 3400–3408, Jan. 2022.
- [73] S. Wenzel, T. Leichtweiss, D. Kruger, J. Sann, and J. Janek, “Interphase formation on lithium solid electrolytes—an in situ approach to study interfacial reactions by photoelectron spectroscopy,” in *Solid State Ionics*, vol. 278, pp. 98–105, Oct. 2015.
- [74] X. Liu, D. Wang, G. Liu, V. Srinivasan, Z. Liu, Z. Hussain, and W. Yang, “Distinct charge dynamics in battery electrodes revealed by in situ and operando soft X-Ray spectroscopy,” in *nature communications*, vol. 4, Art. no. 2568, Oct. 2013.
- [75] F. Han, A. S. Westover, J. Yue, X. Fan, F. Wang, M. Chi, D. N. Leonard, N. J. Dudney, H. Wang, and C. Wang, “High electronic conductivity as the origin of lithium dendrite formation within solid electrolytes,” in *nature energy*, vol. 4, pp. 187–196, Jan. 2019.
- [76] *Battery Protection Selection Guide*. Neubiberg, Germany: Infineon, 2022. [Online]. Available: [https://www.infineon.com/dgdl/Infineon-Battery\\_protection-ApplicationBrochure-v02\\_00-EN.pdf?fileId=5546d4626e651a41016e8408e91b1948](https://www.infineon.com/dgdl/Infineon-Battery_protection-ApplicationBrochure-v02_00-EN.pdf?fileId=5546d4626e651a41016e8408e91b1948).
- [77] Z. Zhao, W. Lu, W. Chen, X. Du, and H. H. -C. Iu, “Multi-period frame transient switching control for low-voltage high-current buck converter with a controlled coupled inductor,” in *IEEE Transactions on Power Electronics*, vol. 34, no. 10, pp. 9743–9757, Oct. 2019.
- [78] Y. Shang, Q. Zhang, N. Cui, B. Duan, Z. Zhou, and C. Zhang, “Multicell-to-multicell equalizers based on matrix and half-bridge LC converters for series-connected battery strings,” in *IEEE Journal of Emerging and Selected Topics in Power Electronics*, vol. 8, no. 2, pp. 1755–1766, Jun. 2020.
- [79] N. Lyu, Y. Jin, R. Xiong, S. Miao, and J. Gao, “Real-time overcharge warning and early thermal runaway prediction of Li-ion battery by online impedance measurement,” in *IEEE Transactions on Industrial Electronics*, vol. 69, no. 2, pp. 1929–1936, Feb. 2022.
- [80] Cypress Semiconductor Application Note, “Power management-battery charger with cell-balancing and fuel gauge function support,” 2017. [Online]. Available: [https://www.infineon.com/dgdl/Infineon-AN2344\\_Power\\_Management\\_Battery\\_Charger\\_with\\_Cell\\_Balancing\\_and\\_Fuel\\_Gauge\\_Function\\_Support-ApplicationNotes-v04\\_00-EN.pdf?fileId=8ac78c8c7cdc391c017d073213395601](https://www.infineon.com/dgdl/Infineon-AN2344_Power_Management_Battery_Charger_with_Cell_Balancing_and_Fuel_Gauge_Function_Support-ApplicationNotes-v04_00-EN.pdf?fileId=8ac78c8c7cdc391c017d073213395601).
- [81] C. Pascual and P. T. Krein, “Switched capacitor system for automatic series battery equalization,” in *Proceedings of APEC 97 - Applied Power Electronics Conference*, Atlanta, GA, USA, 1997, pp. 848–854.
- [82] P. A. Cassani and S. S. Williamson, “Feasibility analysis of a novel cell equalizer topology for plug-in hybrid electric vehicle energy-storage systems,” in *IEEE Transactions on Vehicular Technology*, vol. 58, no. 8, pp. 3938–3946, Oct. 2009.
- [83] S. Li, C. C. Mi, and M. Zhang, “A high-efficiency active battery-balancing circuit using multiwinding transformer,” in *IEEE Transactions on Industry Applications*, vol. 49, no. 1, pp. 198–207, Jan.-Feb. 2013.
- [84] N. H. Kutkut, “A modular nondissipative current diverter for EV battery charge equalization,” in *APEC '98 Thirteenth Annual Applied Power Electronics Conference and Exposition*, Anaheim, CA, USA, 1998, pp. 686–690.
- [85] Y. Wang, C. Zhang, Z. Chen, X. Jing, and X. Zhang, “A novel active equalization method for lithium-ion batteries in electric vehicles,” in *Applied Energy*, vol. 145, no. 1, pp. 36–42, May 2015.
- [86] W. Huang and J. A. Abu Qahouq, “Energy sharing control scheme for state-of-charge balancing of distributed battery energy storage system,” in *IEEE Transactions on Industrial Electronics*, vol. 62, no. 5, pp. 2764–2776, May 2015.
- [87] A. Turksoy, A. Teke, and A. Alkaya, “A comprehensive overview of the Dc-Dc converter-based battery charge balancing methods in electric vehicles,” in *Renewable and Sustainable Energy Reviews*, vol. 133, Art. no. 110274, Nov. 2020.
- [88] N. Ghaeminezhad, Q. Ouyang, X. Hu, G. Xu, and Z. Wang, “Active cell equalization topologies analysis for battery packs: a systematic review,” in *IEEE Transactions on Power Electronics*, vol. 36, no. 8, pp. 9119–9135, Aug. 2021.
- [89] R. Xiong, L. Li, and J. Tian, “Towards a smarter battery management system: A critical review on battery state of health monitoring methods,” in *Journal of Power Sources*, vol. 405, pp. 18–29, Nov. 2018.
- [90] X. Hu, F. Feng, K. Liu, L. Zhang, J. Xie, and B. Liu, “State estimation for advanced battery management: Key challenges and future trends,” in *Renewable and Sustainable Energy Reviews*, vol. 114, pp. 1–13, Oct. 2019.
- [91] Y. Li, K. Liu, A. M. Foley, A. Zülke, M. Berecibar, E. Nanini-Maury, J. V. Mierlo, and H. E. Hoster, “Data-driven health estimation and lifetime prediction of lithium-ion batteries: a review,” in *Renewable and Sustainable Energy Reviews*, vol. 113, Art. no. 109254, 2019.
- [92] X. Sui, S. He, S. B. Vilsen, J. Meng, R. Teodorescu, and D.-I. Stroe, “A review of non-probabilistic machine learning-based state of health estimation techniques for lithium-ion battery,” in *Applied Energy*, vol. 300, Art. no. 117346, 2021.
- [93] J. Meng, M. Ricco, G. Luo, M. Swierczynski, D. -I. Stroe, A. -I. Stroe, and R. Teodorescu, “An overview and comparison of online implementable SOC estimation methods for lithium-ion battery,” in *IEEE Transactions on Industry Applications*, vol. 54, no. 2, pp. 1583–1591, Mar.-Apr. 2018.
- [94] Y. Wang, K. Li, P. Peng, and Z. Chen, “Health diagnosis for lithium-ion battery by combining partial incremental capacity and deep belief network during insufficient discharge profile,” in *IEEE Transactions on Industrial Electronics*, vol. 70, no. 11, pp. 11242–11250, Nov. 2023.
- [95] X. Han, M. Ouyang, L. Lu, and J. Li, “Simplification of physics-based electrochemical model for lithium-ion battery on electric vehicle. Part II: pseudo-two-dimensional model simplification and state of charge estimation,” in *Journal of Power Sources*, vol. 278, pp. 814–825, 2015.
- [96] Y. Kim, X. Lin, A. Abbaslinejad, S. U. Kim, and S. H. Chung, “On state estimation of all solid-state batteries,” in *Electrochimica Acta*, vol. 317, pp. 663–672, Sep. 2019.
- [97] Z. Deng, X. Hu, X. Lin, Y. Kim, and J. Li, “Sensitivity analysis and joint estimation of parameters and states for all-solid-state batteries,” in *IEEE Transactions on Transportation Electrification*, vol. 7, no. 3, pp. 1314–1323, Sept. 2021.
- [98] M. Galeotti, L. Cinà, C. Giammanco, S. Cordiner, and A. Di Carlo, “Performance analysis and SOH (state of health) evaluation of lithium polymer batteries through electrochemical impedance spectroscopy,” in *Energy*, vol. 89, pp. 678–686, Sept. 2015.
- [99] Y. Fu, J. Xu, M. Shi, and X. Mei, “A fast impedance calculation-based battery state-of-health estimation method,” in *IEEE Transactions on Industrial Electronics*, vol. 69, no. 7, pp. 7019–7028, Jul. 2022.
- [100] J. Zhu, Z. Sun, X. Wei, and H. Dai, “A new lithium-ion battery internal temperature on-line estimate method based on electrochemical impedance spectroscopy measurement,” in *Journal of Power Sources*, vol. 274, pp. 990–1004, 2015.
- [101] X. Kong, G. L. Plett, M. S. Trimboli, Z. Zhang, D. Qiao, T. Zhao, and Y. Zheng, “Pseudo-two-dimensional model and impedance diagnosis of micro internal short circuit in lithium-ion cells,” in *Journal of Energy Storage*, vol. 27, Art. no. 101085, 2020.
- [102] D. A. Howey, P. D. Mitcheson, V. Yufit, G. J. Offer, and N. P. Brandon, “Online measurement of battery impedance using motor controller excitation,” in *IEEE Transactions on Vehicular Technology*, vol. 63, no. 6, pp. 2557–2566, Jul. 2014.
- [103] W. Huang and J. A. Abu Qahouq, “An online battery impedance measurement method using DC-DC power converter control,” in *IEEE Transactions on Industrial Electronics*, vol. 61, no. 11, pp. 5987–5995, Nov. 2014.
- [104] J. A. A. Qahouq and Z. Xia, “Single-perturbation-cycle online battery impedance spectrum measurement method with closed-loop control of power converter,” in *IEEE Transactions on Industrial Electronics*, vol. 64, no. 9, pp. 7019–7029, Sept. 2017.
- [105] X. Wang, X. Wei, Q. Chen, and H. Dai, “A novel system for measuring alternating current impedance spectra of series-connected lithium-ion batteries with a high-power dual active bridge converter and distributed sampling units,” in *IEEE Transactions on Industrial Electronics*, vol. 68, no. 8, pp. 7380–7390, Aug. 2021.
- [106] M. Bayati, M. Abedi, G. B. Gharehpetian, and M. Farahmandrad, “Sinusoidal-ripple current control in battery charger of electric vehicles,” in *IEEE Transactions on Vehicular Technology*, vol. 69, no. 7, pp. 7201–7210, Jul. 2020.

- [107] M. A. Varnosfaderani and D. Strickland, "Online impedance spectroscopy estimation of a Dc–Dc converter connected battery using a switched capacitor-based balancing circuit," in *The Journal of Engineering*, vol. 2019, no. 7, pp. 4681–4685, Jul. 2019.
- [108] E. Din, C. Schaefer, K. Moffat, and J. T. Stauth, "A scalable active battery management system with embedded real-time electrochemical impedance spectroscopy," in *IEEE Transactions on Power Electronics*, vol. 32, no. 7, pp. 5688–5698, Jul. 2017.
- [109] R. Koch, C. Riebel, and A. Jossen, "On-line electrochemical impedance spectroscopy implementation for telecommunication power supplies," in *2015 IEEE International Telecommunications Energy Conference (INTELEC)*, Osaka, Japan, 2015, pp. 1–6.
- [110] M. J. Brand, M. H. Hofmann, S. S. Schuster, P. Keil, and A. Jossen, "The influence of current ripples on the lifetime of lithium-ion batteries," in *IEEE Transactions on Vehicular Technology*, vol. 67, no. 11, pp. 10438–10445, Nov. 2018.
- [111] A. Bessman, R. Soares, O. Wallmark, P. Svens, and G. Lindbergh, "Aging effects of AC harmonics on lithium-ion cells," in *Journal of Energy Storage*, vol. 21, pp. 741–749, Feb. 2019.
- [112] X. Huang, W. Liu, A. B. Acharya, J. Meng, R. Teodorescu, and D. -I. Stroe, "Effect of pulsed current on charging performance of lithium-ion batteries," in *IEEE Transactions on Industrial Electronics*, vol. 69, no. 10, pp. 10144–10153, Oct. 2022.
- [113] S. Lavety, R. K. Keshri, and M. A. Chaudhari, "Multistep constant current-constant voltage charging strategy for a valve regulated lead-acid battery," in *IEEE Transactions on Industry Applications*, vol. 57, no. 6, pp. 6494–6503, Nov.-Dec. 2021.
- [114] M. Bayati, M. Abedi, M. Farahmandrad, and G. B. Gharehpetian, "Delivering smooth power to pulse-current battery chargers: electric vehicles as a case in point," in *IEEE Transactions on Power Electronics*, vol. 36, no. 2, pp. 1295–1302, Feb. 2021.
- [115] H. Vazini, M. Asadi, M. Karimadini, and H. Hajisadeghian, "A fast charging of Li-ion battery based on Lyapunov function for electrical vehicle," in *IET Power Electronics*, vol. 15, no. 1, pp. 23–32, Jan. 2022.
- [116] X. Hu, Y. Zheng, X. Lin, and Y. Xie, "Optimal multistage charging of NCA/graphite lithium-ion batteries based on electrothermal-aging dynamics," in *IEEE Transactions on Transportation Electrification*, vol. 6, no. 2, pp. 427–438, Jun. 2020.
- [117] K. Liu, C. Zou, K. Li, and T. Wik, "Charging pattern optimization for lithium-ion batteries with an electrothermal-aging model," in *IEEE Transactions on Industrial Informatics*, vol. 14, no. 12, pp. 5463–5474, Dec. 2018.
- [118] H. W. Yan, G. G. Farivar, N. Beniwal, H. D. Tafti, S. Ceballos, J. Pou, and G. Konstantinou, "Battery lifetime extension in a stand-alone microgrid with flexible power point tracking of photovoltaic system," in *IEEE Journal of Emerging and Selected Topics in Power Electronics*, vol. 11, no. 2, pp. 2281–2290, Apr. 2023.
- [119] H. Wang and F. Blaabjerg, "Power electronics reliability: state of the art and outlook," in *IEEE Journal of Emerging and Selected Topics in Power Electronics*, vol. 9, no. 6, pp. 6476–6493, Dec. 2021.
- [120] Z. Zhao, P. Davari, W. Lu, H. Wang, and F. Blaabjerg, "An overview of condition monitoring techniques for capacitors in DC-link applications," in *IEEE Transactions on Power Electronics*, vol. 36, no. 4, pp. 3692–3716, Apr. 2021.
- [121] Z. Zhao, W. Lu, P. Davari, X. Du, H. H. -C. Iu, and F. Blaabjerg, "An online parameters monitoring method for output capacitor of buck converter based on large-signal load transient trajectory analysis," in *IEEE Journal of Emerging and Selected Topics in Power Electronics*, vol. 9, no. 4, pp. 4004–4015, Aug. 2021.
- [122] Z. Zhao, P. Davari, W. Lu, and F. Blaabjerg, "Online DC-link capacitance monitoring for digital-controlled boost PFC converters without additional sampling devices," in *IEEE Transactions on Industrial Electronics*, vol. 70, no. 1, pp. 907–920, Jan. 2023.
- [123] Z. Zhao, P. Davari, Y. Wang, and F. Blaabjerg, "Online capacitance monitoring for DC/DC boost converters based on low-sampling-rate approach," in *IEEE Journal of Emerging and Selected Topics in Power Electronics*, vol. 10, no. 5, pp. 5192–5204, Oct. 2022.
- [124] H. Dai, B. Jiang, X. Hu, X. Lin, X. Wei, and M. Pecht, "Advanced

battery management strategies for a sustainable energy future: Multilayer design concepts and research trends," in *Renewable and Sustainable Energy Reviews*, vol. 138, Art. no. 110480, 2021.


- [125] S. Zhao, F. Blaabjerg, and H. Wang, "An overview of artificial intelligence applications for power electronics," in *IEEE Transactions on Power Electronics*, vol. 36, no. 4, pp. 4633–4658, Apr. 2021.



**Zhaoyang Zhao** received the B.S. and M.S. degrees in electrical engineering from Northeast Agricultural University, Harbin, China, in 2014 and 2017, respectively, and the Ph.D. degree in electrical engineering from Chongqing University, China, 2020. From 2019 to 2020, he was a Visiting Ph.D. Student with the Department of Energy Technology, Aalborg University, Aalborg, Denmark. From 2021 to 2022, he was with Zhengzhou University, as an Assistant Professor. He joined Southwest Jiaotong University,

in 2022. He is currently an Associate Professor. His research interests include condition monitoring, safety and reliability assessment of power electronic converters and battery systems.

Dr. Zhao received a Prize Paper Award of the *IEEE Journal of Emerging and Selected Topics in Power Electronics* in 2021. He was a recipient of the Excellent Doctoral Dissertation of Chongqing City in 2022. He has served as a Guest Editor-in-Chief for *Microelectronics International* and a Guest Associate Editor for *CPSS Transactions on Power Electronics and Applications*. He is an Associate Editor of *Circuit World*.



**Haitao Hu** received the B.S. degree from Zhengzhou University, Zhengzhou, China, in 2010, and the Ph.D. degree from Southwest Jiaotong University, Chengdu, China, in 2014, both in electrical engineering.

He is currently a Professor with the School of Electrical Engineering, Southwest Jiaotong University. His main research interests include power quality and stability of the electric traction system.



**Zhengyou He** received the B.Sc. degree and M. Sc. degree from Chongqing University, Chongqing, China, in 1992 and 1995, respectively, and the Ph.D. degree from Southwest Jiaotong University, Chengdu, China, in 2001.

He is currently a Professor in the School of Electrical Engineering at Southwest Jiaotong University. His research interests include signal process and information theory applied to power systems, and the application of wavelet transforms in power systems.



**Hongyi Zhu** is an undergraduate and will receive the B.S. degree in electrical engineering from Southwest Jiaotong University, Chengdu, China, in 2024. His research interests include battery systems and energy harvesting.





**Pooya Davari** received the B.Sc. and M.Sc. degrees in electronic engineering in 2004 and 2008, respectively, and the Ph.D. degree in power electronics from Queensland University of Technology (QUT), Australia, in 2013. From 2005 to 2010, he was involved in several electronics and power electronics projects as a Development Engineer. From 2013 to 2014, he was with QUT, as a Lecturer. He joined Aalborg University (AAU), in 2014, as a Postdoc, where he is currently an

Associate Professor.

He has been focusing on EMI, power quality and harmonic mitigation analysis and control in power electronic systems. He has published more than 180 technical papers. Dr. Davari served as a Guest Associate Editor of *IET journal of Power Electronics*, *IEEE Access Journal*, *Journal of Electronics* and *Journal of Applied Sciences*. He is an Associate Editor of *Journal of Power Electronics*, *IET Electronics*, Editorial board member of *Journal of Applied Sciences* and *Journal of Magnetics*. He is member of the International Scientific Committee (ISC) of EPE (ECCE Europe) and a member of Joint Working Group six and Working Group eight at the IEC standardization TC77A. Dr. Davari is the recipient of Equinor 2022 Prize and 2020 IEEE EMC Society Young Professional Award for his contribution to EMI and Harmonic Mitigation and Modeling in Power Electronic Applications. He is currently Editor-in-Chief of *Circuit World Journal*. He is founder and chair of IEEE EMC Society Chapter DENMARK and Leader of EMI/EMC in Power Electronics Research Group at AAU Energy.



**Frede Blaabjerg** received the Ph.D. degree in electrical engineering from Aalborg University, Aalborg, Denmark, in 1995.

He was with ABB-Scandia, Randers, Denmark, from 1987 to 1988. He became an Assistant Professor in 1992, an Associate Professor in 1996, and a Full Professor of power electronics and drives in 1998 at Aalborg University, where he became a Villum Investigator in 2017. He is also honoris causa at Universitatea Politehnica Timisoara

(UPT), Romania, and the Tallinna University of Technology (TTU), Tallinn, Estonia. He has published more than 600 journal articles in the fields of power electronics and its applications. He is a coauthor of four monographs and editor of ten books in power electronics and its applications. His current research interests include power electronics and its applications, such as in wind turbines, PV systems, reliability, harmonics, and adjustable speed drives.

Dr. Blaabjerg received 32 IEEE Prize Paper Awards, the IEEE Power Electronics Society (PELS) Distinguished Service Award in 2009, the EPE-PEMC Council Award in 2010, the IEEE William E. Newell Power Electronics Award in 2014, the Villum Kann Rasmussen Research Award in 2014, the Global Energy Prize in 2019, and the 2020 IEEE Edison Medal. He was nominated in 2014–2019 by Thomson Reuters to be between the most 250 cited researchers in engineering in the world. He was the Editor-in-Chief of *IEEE Transactions on Power Electronics* from 2006 to 2012. He was a Distinguished Lecturer of the IEEE Power Electronics Society from 2005 to 2007 and the IEEE Industry Applications Society from 2010 to 2011 and 2017 to 2018. From 2019 to 2020, he has served as the President of the IEEE Power Electronics Society. He is also the Vice-President of the Danish Academy of Technical Sciences.

He is nominated in 2014–2020 by Thomson Reuters to be between the most 250 cited researchers in Engineering in the world.