

Aalborg Universitet



**AALBORG UNIVERSITY**  
DENMARK

## Thermal properties of common building materials

Johra, Hicham

*Publication date:*  
2019

*Document Version*  
Publisher's PDF, also known as Version of record

[Link to publication from Aalborg University](#)

*Citation for published version (APA):*

Johra, H. (2019). *Thermal properties of common building materials*. Department of Civil Engineering, Aalborg University. DCE Technical Reports No. 216

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

### Take down policy

If you believe that this document breaches copyright please contact us at [vbn@aub.aau.dk](mailto:vbn@aub.aau.dk) providing details, and we will remove access to the work immediately and investigate your claim.

# Thermal properties of common building materials

Hicham Johra





Aalborg University  
Department of Civil Engineering  
Architectural Engineering

**DCE Technical Report No. 216**

# **Thermal properties of common building materials**

by

Hicham Johra

January 2019

© Aalborg University

## Scientific Publications at the Department of Civil Engineering

**Technical Reports** are published for timely dissemination of research results and scientific work carried out at the Department of Civil Engineering (DCE) at Aalborg University. This medium allows publication of more detailed explanations and results than typically allowed in scientific journals.

**Technical Memoranda** are produced to enable the preliminary dissemination of scientific work by the personnel of the DCE where such release is deemed to be appropriate. Documents of this kind may be incomplete or temporary versions of papers—or part of continuing work. This should be kept in mind when references are given to publications of this kind.

**Contract Reports** are produced to report scientific work carried out under contract. Publications of this kind contain confidential matter and are reserved for the sponsors and the DCE. Therefore, Contract Reports are generally not available for public circulation.

**Lecture Notes** contain material produced by the lecturers at the DCE for educational purposes. This may be scientific notes, lecture books, example problems or manuals for laboratory work, or computer programs developed at the DCE.

**Theses** are monographs or collections of papers published to report the scientific work carried out at the DCE to obtain a degree as either PhD or Doctor of Technology. The thesis is publicly available after the defence of the degree.

**Latest News** is published to enable rapid communication of information about scientific work carried out at the DCE. This includes the status of research projects, developments in the laboratories, information about collaborative work and recent research results.

Published 2019 by  
Aalborg University  
Department of Civil Engineering  
Thomas Manns Vej 23  
DK-9220 Aalborg Ø, Denmark

Printed in Aalborg at Aalborg University

ISSN 1901-726X  
DCE Technical Report No. 216

Contents

Contents ..... 5

1. Introduction..... 6

2. Data overview..... 7

3. Thermo-physical material properties of the indoor content and furniture elements ..... 12

References ..... 13

## 1. Introduction

The aim of this technical report is to provide a large collection of the main thermos-physical properties of various common construction materials and materials composing the elements inside the indoor environment of residential and office buildings. The Excel file enclosed with this document can be easily used to find thermal properties of materials for building energy and indoor environment simulation or to analyze experimental data.

The main thermo-physical properties which are needed for thermodynamics calculations, and compiled in this database are the mass density [ $\text{kg/m}^3$ ], the thermal conductivity [ $\text{W/m.K}$ ] and the specific heat capacity [ $\text{J/kg.K}$ ]. From these properties are calculated the volumetric heat capacity [ $\text{kJ/m}^3.\text{K}$ ] and the thermal diffusivity [ $\text{mm}^2/\text{s}$ ]. These material thermo-physical properties are stated for normal conditions of pressure (atmospheric pressure) and ambient temperature between 10 °C and 40 °C.

The thermo-physical properties of these construction materials are compiled from various sources [1] listed in the references section, but also measurements carried out in the Laboratory of Building Energy and Indoor Environment in the Department of Civil Engineering at Aalborg University (Denmark). In addition, suggestions are made for the thermos-physical properties of the materials composing the indoor content and furniture elements present in the built environment [35][36]. Some materials may have multiple entries with variations in the estimates of the thermo-physical properties. These variations between the different sources emphasize the difficulty to accurately determine the thermo-physical properties of building materials. In addition, these thermo-physical properties can vary significantly with temperature and humidity. For some material entries, only a part of the thermo-physical properties are indicated in the source and therefore compiled in this database.

The materials of this database are classified into 13 categories:

- Insulation
- Cellular glass / mineral
- Textile
- Paper / cardboard
- Polymer foam
- Wood
- Plastic / polymer
- Plaster
- Ceramic
- Structure material
- Natural stone
- Metal
- Carbon structure

In each category, the material entries are ordered alphabetically by name.

## 2. Data overview

One can see in the following figures an overview of the different thermo-physical properties of the different material categories. As illustrated in *Figure 1 - 4*, there is a clear correlation between material density and thermal conductivity. Apart from metals and ceramics, most of the building materials have a certain degree of porosity. Consequently, their thermal conductivity is mainly determined by the air and water content of these pores, which is directly correlated to their porosity and, therefore, to their density. Higher porosity (lower density) with air-filled cavities can lead to a higher amount of air. The latter having a very low thermal conductivity, it drives the entire thermal conductivity of the porous material down. On the other hand, the specific heat capacity of the material is more difficult to assess. It can be noted that the same value of specific heat capacity is often given for a whole category of material in the same source. In addition, one can see in *Figure 5* that there is no clear correlation between the density and the specific heat capacity of common construction materials [35].

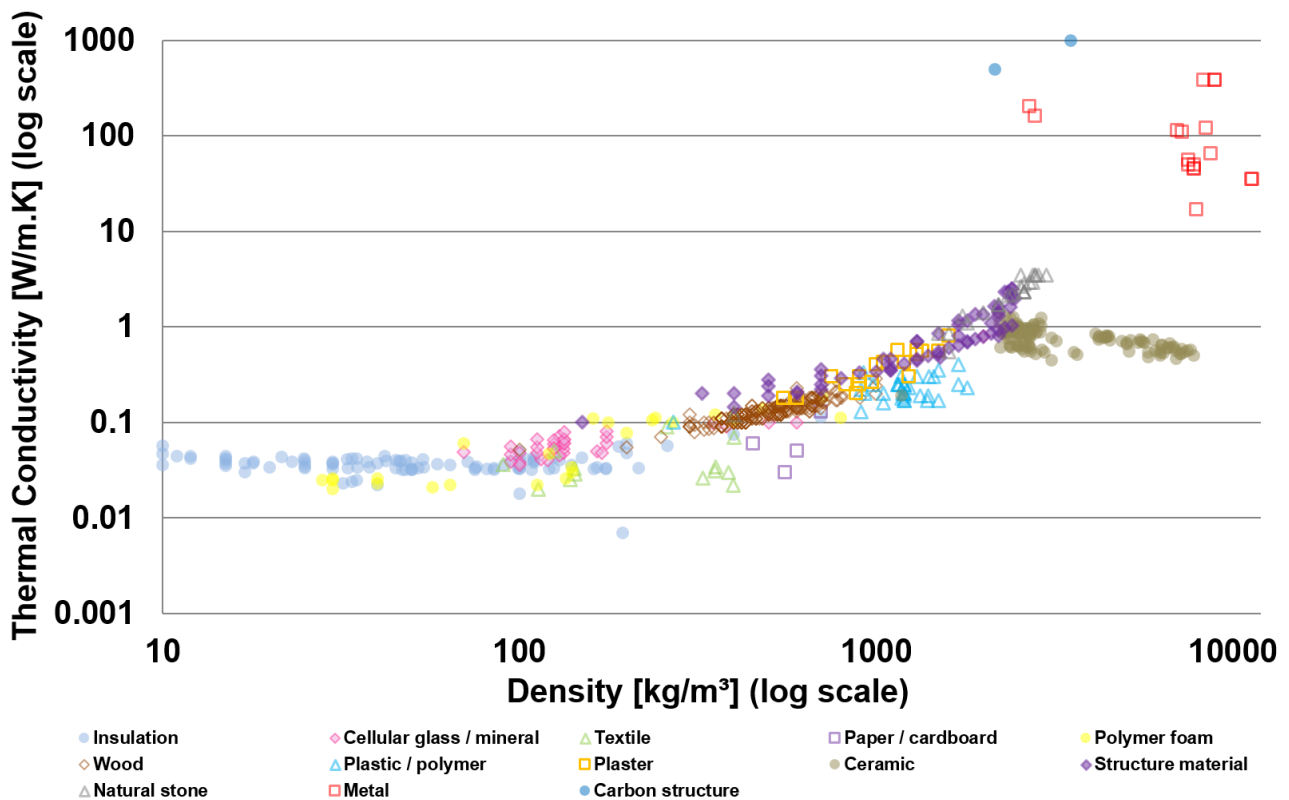


Figure 1: Overview of the material thermal conductivity as function of density.



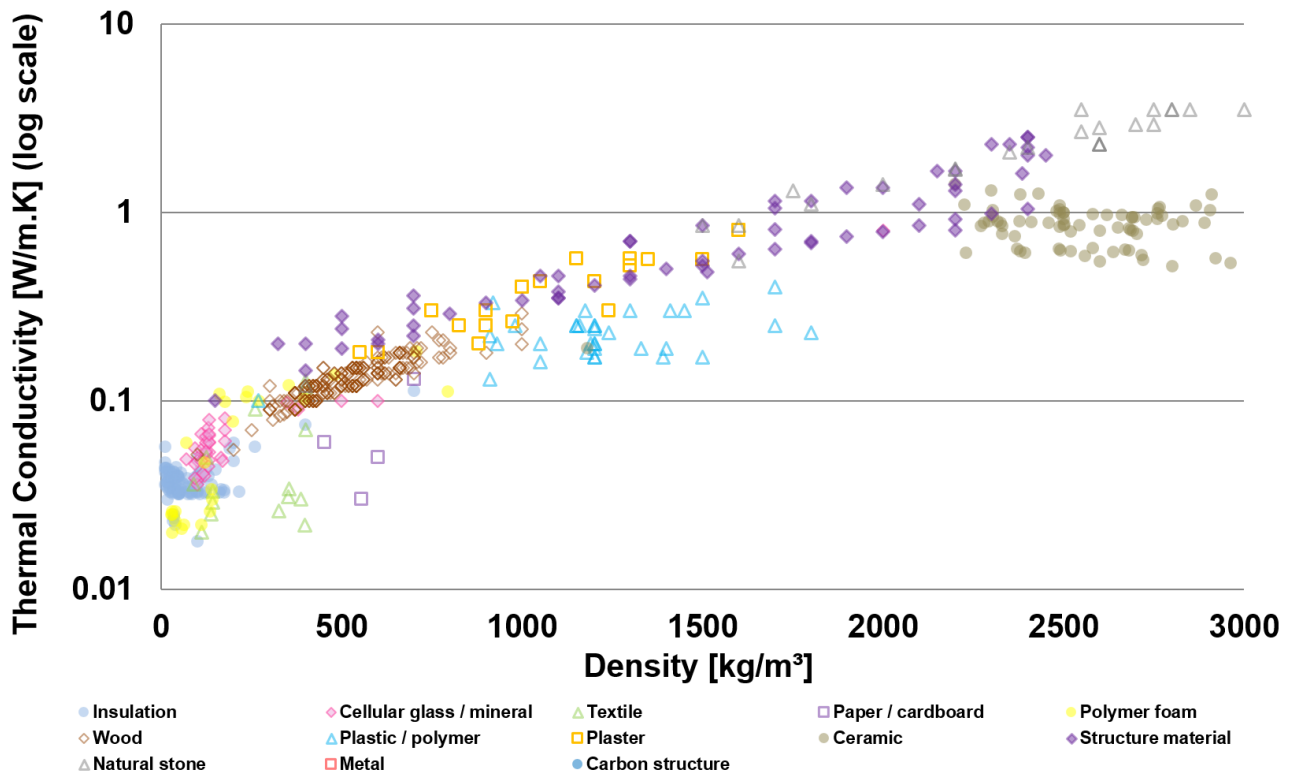


Figure 2: Overview of the material thermal conductivity as function of density.

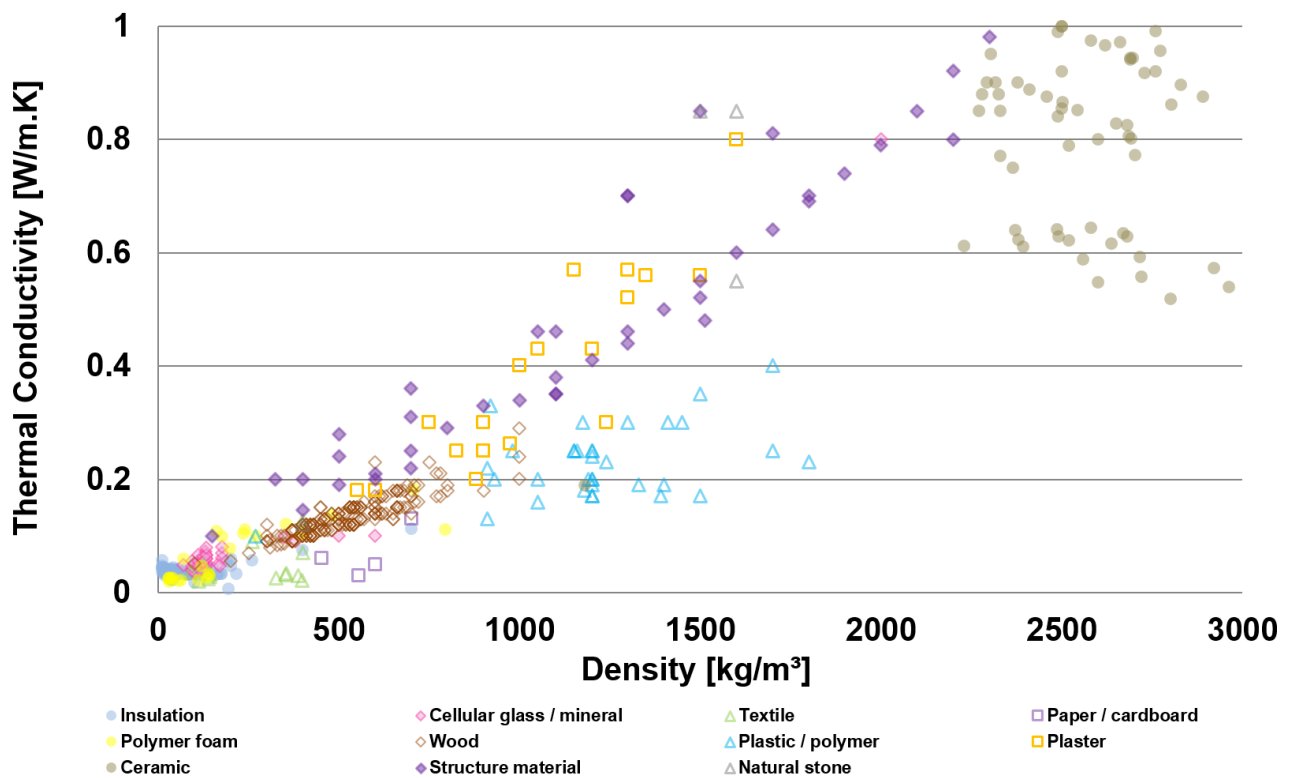


Figure 3: Overview of the material thermal conductivity as function of density.

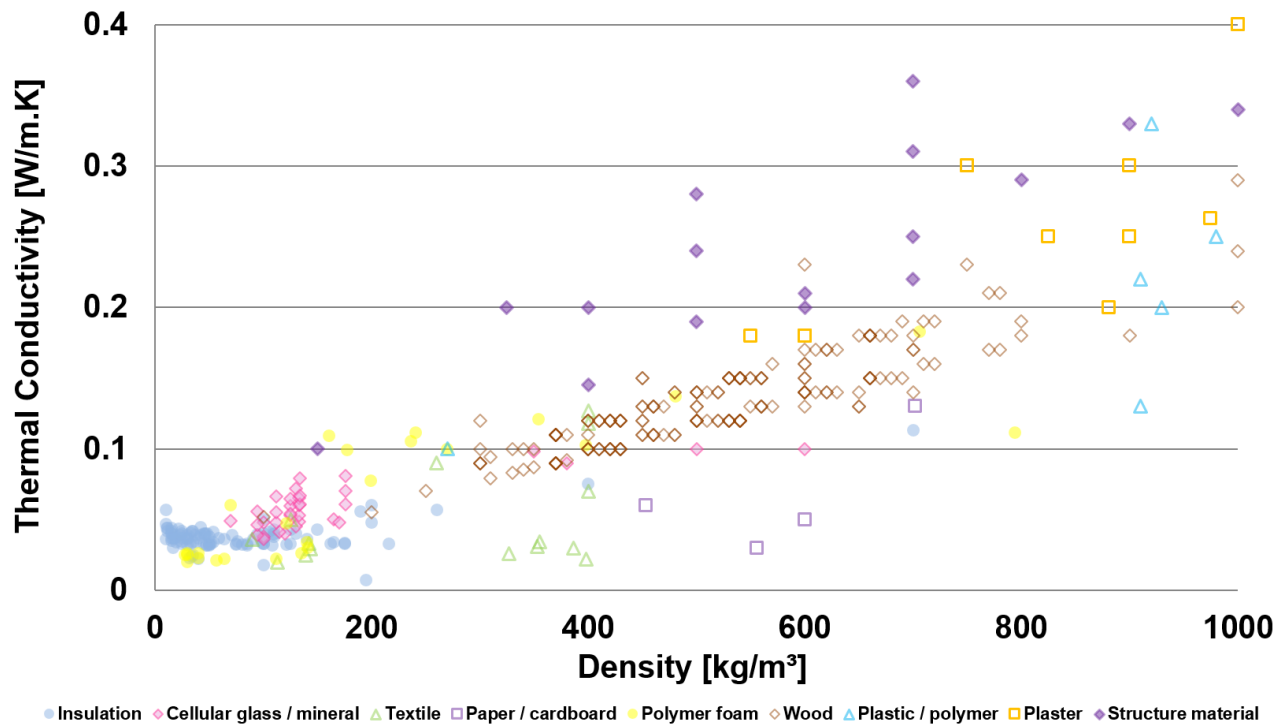


Figure 4: Overview of the material thermal conductivity as function of density.

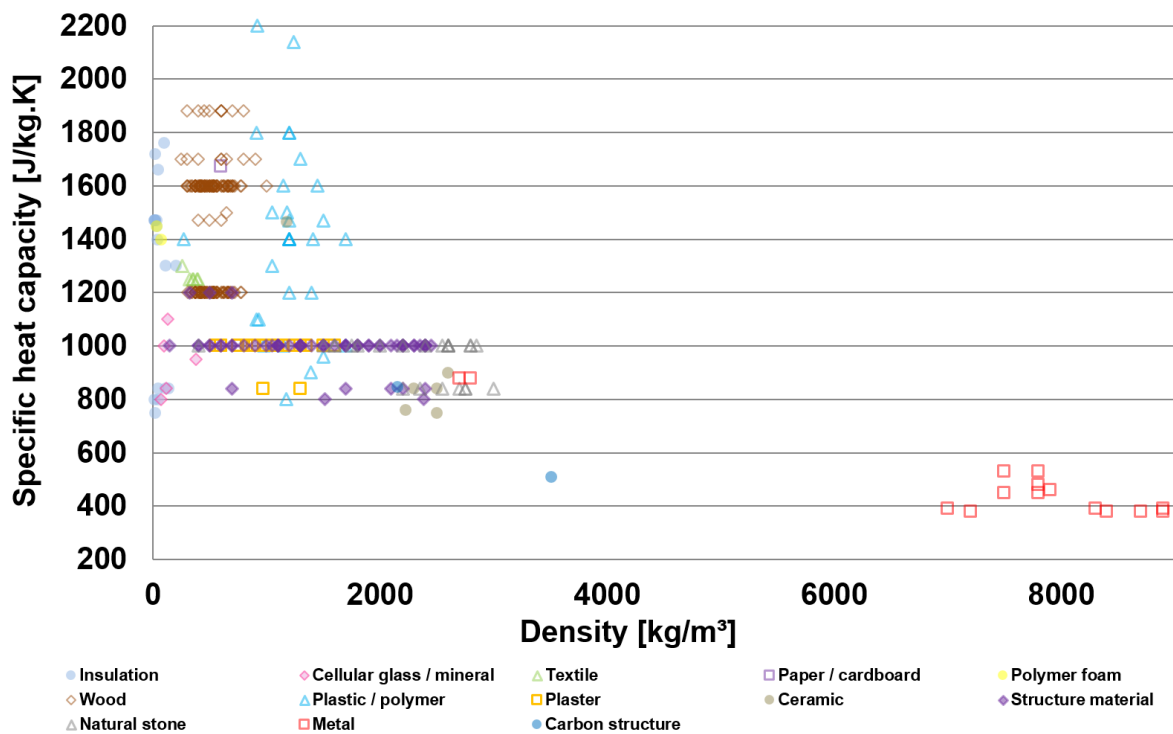


Figure 5: Overview of the material specific heat capacity as function of density.

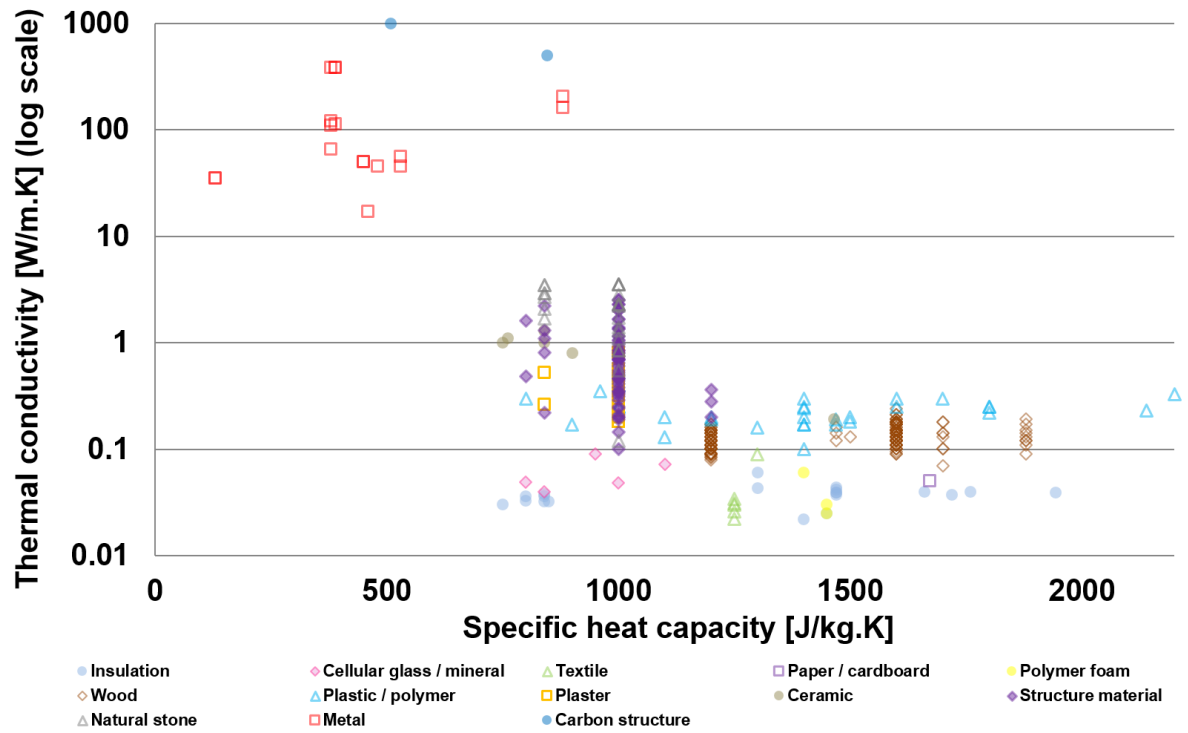


Figure 6: Overview of the material thermal conductivity as function of specific heat capacity.

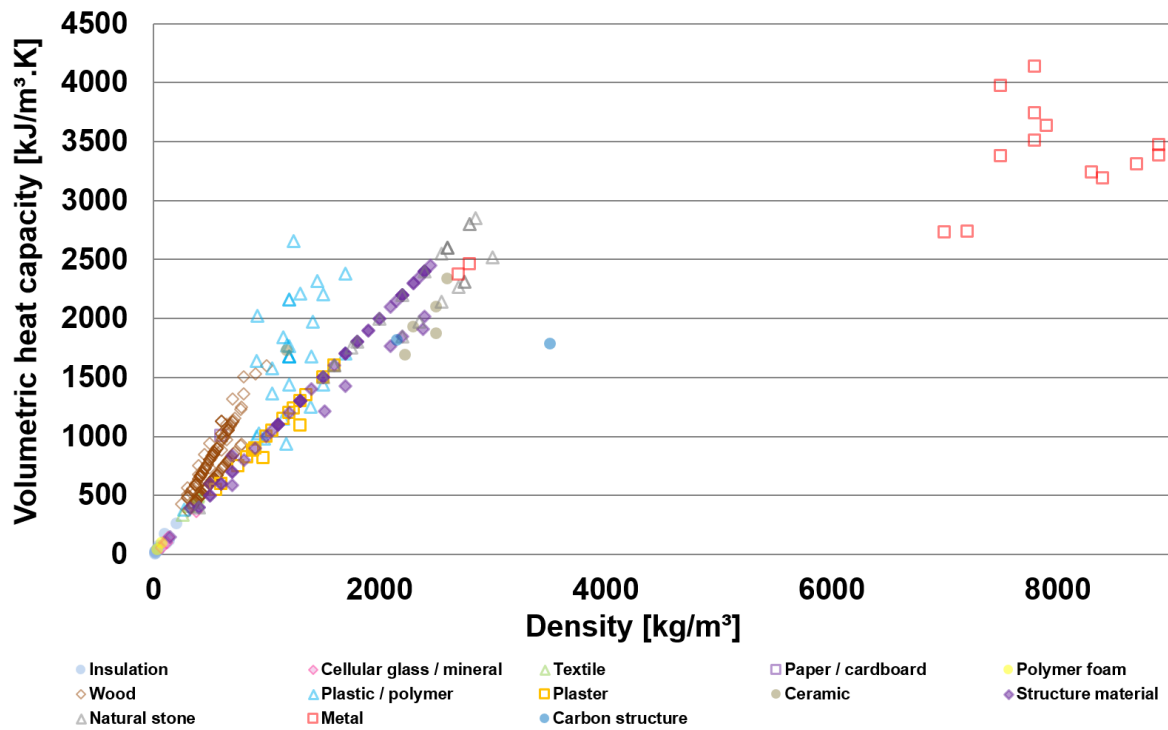


Figure 7: Overview of the material volumetric heat capacity as function of density.

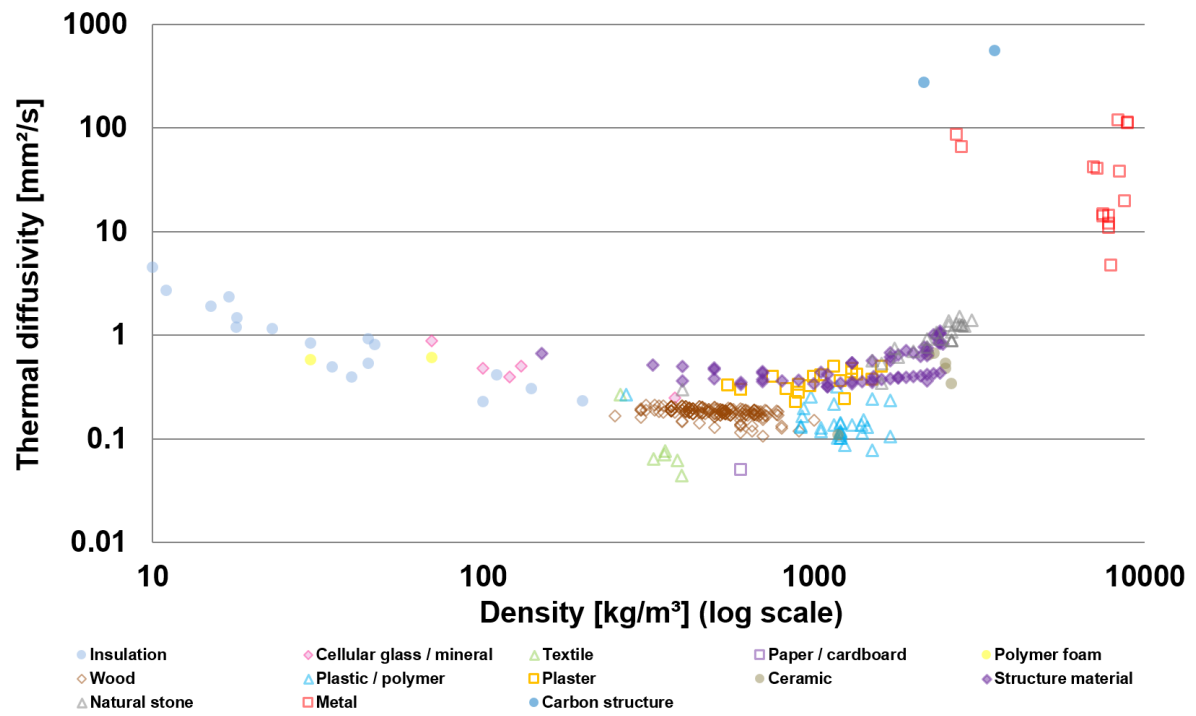


Figure 8: Overview of the material thermal diffusivity as function of density.

### 3. Thermo-physical material properties of the indoor content and furniture elements

The indoor content and furnishing elements present inside the built environment often have complex geometries with various types of material. One can find in *Table 1* recommendations for the thermo-physical properties of these indoor content elements. It is considered that the materials composing the indoor content elements can be classified into 4 main categories: light material, wood / plastic material, concrete / glass material, metal material. In addition, the properties of an equivalent indoor content material (which would therefore account for the equivalent thermo-physical properties of the overall indoor content elements) is given. For all categories, indications on the dimensions, effective thermal inertia and amount in buildings (mass relative to floor surface area) are given. These recommendations are valid for both residential and office buildings [35][36].

*Table 1: Thermo-physical properties of the representative indoor content material categories [36].*

Material category	Room mass content (kg/m <sup>2</sup> floor area)	Surface area (m <sup>2</sup> /m <sup>2</sup> floor area)	Material density (kg/m <sup>3</sup> )	Material thermal conductivity (W/m.K)	Material specific heat capacity (J/kg.K)	Planar element thickness (cm)	Daily effective thermal inertia (kJ/K.m <sup>2</sup> floor area)
<b>Light material</b>	7 (0.5–14)	0.3 (0.1–0.6)	80 (20–140)	0.03	1400	10 (0.5–24)	3 (0.2–7)
<b>Wood / plastic material</b>	30 (8–80)	1.4 (0.5–2)	800 (400–1200)	0.2 (0.1–0.3)	1400	1.8 (1–5)	26 (9–45)
<b>Concrete / glass material</b>	1 (0.5–2)	0.03 (0.01–0.04)	2000 (1500–2500)	1.25 (0.5–2)	950	1 (0.2–2)	0.1 (0.05–0.2)
<b>Metal material</b>	2 (1–5)	0.02 (0.01–0.03)	8000	60	450	0.2 (0.1–0.3)	0.1 (0.05–0.4)
<b>Equivalent indoor content material</b>	40 (10–100)	1.8 (0.8–2.8)	600 (150–1500)	0.3 (0.1–0.5)	1400	4 (1–10)	30 (10–50)

## References

- [1] International Energy Agency, IEA EBC Project Annex 14 - Catalogue of Material Properties - Report - March 1991
- [2] ISO Standard 10456:2007 - Building materials and products. Hygrothermal properties. Tabulated design values and procedures for determining declared and design thermal values
- [3] ISO Standard 12524:2000 - Building materials and products. Hygrothermal properties. Tabulated design values
- [4] S.B. Stankovic, D. Popovic, G.B. Poparic. Thermal properties of textile fabrics made of natural and regenerated cellulose fibers. *Polymer Testing* 27 (2008) 41-48
- [5] Z.S. Abdel-Rehim, M.M. Saad, M. El-Shakankery, I. Hanafy. Textile fabrics as thermal insulators. *AUTEX Research Journal* 6 (2006)
- [6] A. Das, Shabaridharan, B. Biswas. Study on heat and moisture vapour transmission characteristics through multilayered fabric ensembles. *Indian Journal of Fibre & Textile Research* 36 (2011) 410-414
- [7] B. Selvakumar, V. Prabhu Raja, A.P. Senthil Kumar, P. Karthikeyan. Investigation on effective thermal conductivity of foams using transient plane heat source method. *International Journal of Research in Engineering and Technology* 3 (2014) 249-251
- [8] W. Simpson, A. TenWolde. Physical properties and moisture relations of wood. Madison, WI : USDA Forest Service, Forest Products Laboratory, 1999. General technical report FPL
- [9] Centre Scientifique et Technique du Bâtiment (CSTB). French Building Energy and Thermal Regulation 2012
- [10] H. Johra. (2019). Project CleanTechBlock 2 - thermal conductivity measurements of cellular glass samples. Aalborg: Aalborg University, Department of Civil Engineering. DCE Technical reports, No. 263
- [11] Fundamentals of inorganic glasses, 2nd, Varshneya, p. 276, Originally from Handbook of Glass Properties, Bansal and Doremus 1986
- [12] Ammar et al. Thermal Conductivity of some silicate glasses in relation to composition and structure. *JNCS* 53 (1982) 165-172
- [13] M.M. Ammar, S.A. Gharib, M.M. Halawa, H.A. El-Batal, K. El-Badry. Thermal Conductivity of Silicate and Borate Glasses. *Communications of the American Ceramic Society* (1983) C-76
- [14] Ghoneim et al. Effect of transition metal oxides on the thermal conductivity of glass. *Thermochimica Acta* 71 (1983) 43-51
- [15] Salman et al. Thermal Conductivity of Lithium Iron Silicate Glasses. *Thermochimica Acta* 72 (1984) 269-276
- [16] S.M. Salman, S. Gharib. Some Physical Properties Concerning the Thermal Conductivity Data of BaO-Containing Silicate Glasses in relation to Structure. *Thermochimica Acta* 82 (1984) 345-355
- [17] S.M. Salman, S. Gharib. Thermal conductivity of some Multicomponent Silicate Glasses. *Thermochimica Acta* 77 (1984) 227-239
- [18] N.A. Ghoneim, M.M. Halawa. Effect of Boron Oxide on the thermal conductivity of some sodium silicate glasses. *Thermochimica Acta* 83 (1985) 341-345
- [19] Primenko. Theoretical Method of Determining the temperature dependence of the thermal conductivity of Glasses. UDC 666.11.01:536.21 (1981)
- [20] Salama et al. Thermal conductivity of some silicate glasses and their respective crystalline products. *JNCS* 93 (1987) 203-214

- [21]H. Kiyohashi, N. Hayakawa, S. Aratani, H. Masuda. Thermal conductivity of heat-absorbed soda-lime-silicate glasses at high temperatures. *High temperatures - High pressures* 34 (2002) 167-176
- [22]Hiroshima et al. Thermal conductivity of mixed alkali silicate glasses at low temperature. *JNCS* 354 (2008) 341-344
- [23]Kim and Morita. Temperature dependence and cation effects in the thermal conductivity of glassy and molten alkali borates. *JNCS* 471 (2017) 187-194
- [24]C.C. Yu, J.J. Freeman. Thermal conductivity and specific heat of glasses. *Phys. Rev. B* 36, 14 (1987) 7620-7624
- [25]Terai et al. Thermal conductivity of mixed alkali glasses. *American Ceramic Society Bulletin* vol. 58 no. 11 (1979) 1125
- [26]CRC Handbook of Chemistry and Physics 85th (2005)
- [27]M. Susa, M. Watanabe, S. Ozawa, R. Endo. Thermal conductivity of CaO-SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> glassy slags: Its dependence on molar ratios of Al<sub>2</sub>O<sub>3</sub>/CaO and SiO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub>. *Ironmaking and Steelmaking* vol.34 no. 2 (2007) 124-130
- [28]P.F. Van Velden. Thermal conductivities of some lead and bismuth glasses. *Glass Technology* vol. 6 (1965) 166-169
- [29]M.M. Ammar, M.M. Halawa, N.A. Ghoneim, A.F. Abbas, H.A. El Batal. Thermal conductivity of Lead Borate Glasses. *Communications of the american ceramic society* (October 1982) 174-175
- [30]M.M. Ammar et al. Thermal Conductivity of some sodium aluminosilicate glasses. *Sprechsaal* vol 115 (1982) 692-693
- [31]M.M. Ammar et al. Thermal conductivity of some titania and lithia glasses. *Glass and ceramics bulletin* vol. 22 no. 1 (1975) 10-13
- [32]A. Karamanos, S. Hاديarakou, A.M. Papadopoulos. The impact of temperature and moisture on the thermal performance of stone wool. *Energy and Buildings* 40 (2008) 1402-1411
- [33]A. Abdou, I. Budaiwi. The variation of thermal conductivity of fibrous insulation materials under different levels of moisture content. *Construction and Building Materials* 43 (2013) 533-544
- [34]E. Carattin, M. Franz, S. Luciano. Materiali isolanti, nuove tendenze in architettura. *Archivio delle Tecniche e dei Materiali per l'architettura e il disegno industriale*. Università Iuav di Venezia.
- [35]H. Johra, P. Heiselberg. Influence of internal thermal mass on the indoor thermal dynamics and integration of phase change materials in furniture for building energy storage: A review. *Renewable and Sustainable Energy Reviews* 69 (2017) 19-32.  
<https://doi.org/10.1016/j.rser.2016.11.145>
- [36]H. Johra, P. Heiselberg, J. Le Dréau. Numerical analysis of the impact of thermal inertia from the furniture / indoor content and phase change materials on the building energy flexibility. In *Proceedings of 15th IBPSA Conference, International Building Performance Simulation Association, San Francisco, CA, USA. Aug. 7-9, 2017.*  
<https://doi.org/10.26868/25222708.2017.012>