



Aalborg Universitet

AALBORG UNIVERSITY
DENMARK

Sensitivity Analysis of Cartilage Creep Material Properties Prediction in Unconfined Compression

Impact of Data Quantity

Seiferheld, Bo Eitel; Andersen, Michael Skipper

Published in:
Program & Abstracts

Publication date:
2023

Document Version
Accepted author manuscript, peer reviewed version

[Link to publication from Aalborg University](#)

Citation for published version (APA):
Seiferheld, B. E., & Andersen, M. S. (2023). Sensitivity Analysis of Cartilage Creep Material Properties Prediction in Unconfined Compression: Impact of Data Quantity. In *Program & Abstracts: 15th Annual Meeting of the Danish Society of Biomechanics*. (pp. 39)

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal -

Take down policy

If you believe that this document breaches copyright please contact us at vbn@aub.aau.dk providing details, and we will remove access to the work immediately and investigate your claim.

Sensitivity Analysis of Cartilage Creep Material Properties Prediction in Unconfined Compression: Impact of Data Quantity

Bo E. Seiferheld^{1*} and Michael S. Andersen¹

¹Department of Materials and Production, Aalborg University, Denmark

*Ph.D. student. bes@mp.aau.dk

INTRODUCTION

Osteoarthritis (OA), a prevalent and debilitating disease, involves progressive cartilage loss and altered joint features [1]. This has pushed advancements in cartilage tissue engineering for treatment and healing. Mechanical testing is crucial in the evaluation, but inconsistent testing techniques, across studies, leads to data misinterpretation and impede meaningful comparisons [2]. A recent review emphasized the need for 1 MPa creep stress with >60-min relaxation. Therefore, this study aims to assess the impact of data quantity on cartilage creep material property predictions, offering guidance for creep testing time modes.

METHODS

Ex vivo unconfined compression creep experiments were conducted using cylindrical 6-mm diameter, full-thickness cartilage samples (n = 11) extracted from bovine knees. An Instron material testing machine (Model 5944) performed creep experiments in a force-controlled setting with a preload of 0.05 MPa. After 15 minutes of preload, to reach baseline thickness and even out irregularities [3], a force ramping rate of 0.25 MPa/s reached the creep load of 1 MPa within 4 seconds. Creep load was maintained for 5 hours with continuous force and displacement recording at 10 Hz.

Experimental creep strain was split into six-time intervals (30, 60, 120, 180, 240 and 300 minutes) and fitted to two different models: (1) a standard linear solid model in Kelvin form and (2) a standard linear solid model with the elastic modulus (E_1) constrained and directly determined from the raw data. The creep equation [4] is as follows:

$$\varepsilon(t) = \frac{\sigma_0}{E_1} + \frac{\sigma_0}{E_2} \left(1 - e^{-\frac{t}{\tau}}\right) \quad (1)$$

where ε is creep strain at time t , under constant stress, σ_0 . E_1 is the initial elastic modulus, E_2 is the steady state elastic modulus and τ is the time constant for equilibrium. MATLAB 2022b was used for a nonlinear least-squares curve-fitting.

RESULTS AND DISCUSSION

The samples exhibited a baseline thickness of 2.06 ± 0.56 mm and reached a mean strain of 0.59 ± 0.06 at creep equilibrium. The initial strain following the ramp-up to the creep load averaged 0.14 ± 0.06 , with an associated elastic modulus of 7.12 ± 2.62 MPa. All samples reached a well-defined

equilibrium, as evidenced by less than 0.6 microns of deformation over one minute, achieved after 124 ± 23 minutes of loading, with a corresponding strain of 0.56 ± 0.06 , only 5% deviating from the final creep strain.

The results highlight a noteworthy observation: Model 1 tends to gradually overestimate E_1 with optimiser bias toward fitting the viscous component, ultimately improving model fit. However, this inclination brings the solution closer to E_2 and τ . Conversely, Model 2 exhibits a fitting bias towards the linear elastic region, resulting in an underestimation of the viscous properties.

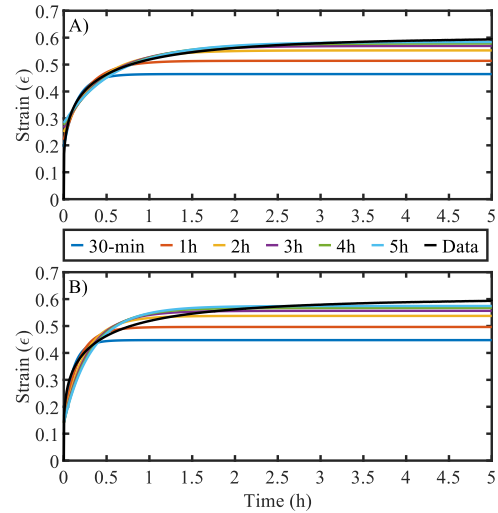


Fig. 1 Predicted strain based on six different time intervals with model 1 (A) and model 2 (B) and corresponding ground truth data in black.

CONCLUSIONS

For unconfined creep testing, it is advisable to maintain the stress for at least 2 hours to acquire sufficient information for model fitting. Lastly, setting a clear criterion for defining equilibrium and enrolling only those samples that meet this criterion are recommended.

REFERENCES

1. Glyn-Jones et al. *The Lancet* **386**: 376-387, 2015.
2. Patel et al. *Tissue Eng Part C Methods* **25**: 593-608, 2019.
3. Athanasiou et al. *J. Ortho Res* **9**: 330-340, 1991.
4. Gong et al. *J. Healthc Eng* **2019**: 1-9, 2019.

Table 1 Cartilage material properties at different time intervals with the corresponding R^2 values.

	Model 1				Model 2		
	E_1 (MPa)	E_2 (MPa)	τ (sec)	R^2	E_2 (MPa)	τ (sec)	R^2
30-min	5.64 ± 1.59	3.75 ± 0.47	565 ± 87	0.72 ± 0.08	3.31 ± 0.40	395 ± 73	0.62 ± 0.08
60-min	4.87 ± 1.26	3.46 ± 0.39	943 ± 124	0.86 ± 0.05	2.85 ± 0.31	614 ± 112	0.75 ± 0.07
120-min	4.25 ± 0.99	3.33 ± 0.35	1464 ± 226	0.94 ± 0.02	2.55 ± 0.27	892 ± 168	0.85 ± 0.05
180-min	3.97 ± 0.86	3.32 ± 0.34	1818 ± 338	0.96 ± 0.01	2.43 ± 0.26	1066 ± 214	0.89 ± 0.04
240-min	3.80 ± 0.79	3.34 ± 0.33	2075 ± 429	0.97 ± 0.01	2.37 ± 0.26	1184 ± 251	0.91 ± 0.04
300-min	3.69 ± 0.75	3.35 ± 0.32	2265 ± 500	0.97 ± 0.01	2.33 ± 0.27	1268 ± 279	0.92 ± 0.03